

# Journal of Visualized Experiments

## Fabrication of 1D Photonic Crystal Cavity on a Nanofiber Using Femtosecond Laser Induced Ablation --Manuscript Draft--

<b>Manuscript Number:</b>	JoVE55136R3
<b>Full Title:</b>	Fabrication of 1D Photonic Crystal Cavity on a Nanofiber Using Femtosecond Laser Induced Ablation
<b>Article Type:</b>	Invited Methods Article - JoVE Produced Video
<b>Keywords:</b>	Quantum Optics; Nanophotonics; Nanofabrication; Laser Ablation; Photonic Crystal; Optical Nanofiber; Quantum Sensing; Quantum Information
<b>Manuscript Classifications:</b>	10.1.637.512: Nanostructures; 10.1.637.512.300: Nanofibers; 97.72.32: photon interactions with atoms and molecules; 97.74.33: photonics; 97.74.5: fiber optics; 97.77.25: quantum electrodynamics (QED)
<b>Corresponding Author:</b>	Kohzo Hakuta, Ph.D. The University of Electro-Communications Chofu, Tokyo JAPAN
<b>Corresponding Author Secondary Information:</b>	
<b>Corresponding Author E-Mail:</b>	k.hakuta@cpi.uec.ac.jp
<b>Corresponding Author's Institution:</b>	The University of Electro-Communications
<b>Corresponding Author's Secondary Institution:</b>	
<b>First Author:</b>	Kali Prasanna Nayak, Ph.D.
<b>First Author Secondary Information:</b>	
<b>Other Authors:</b>	Kali Prasanna Nayak, Ph.D. Jameesh Keloth
<b>Order of Authors Secondary Information:</b>	
<b>Abstract:</b>	We present a protocol for fabricating 1D photonic crystal (PhC) cavities on subwavelength-diameter tapered optical fibers, optical nanofibers, using femtosecond laser induced ablation. We show that thousands of periodic nano-craters are fabricated on an optical nanofiber by irradiating with just a single femtosecond laser pulse. For a typical sample, periodic nano-craters with a period of 350 nm and with diameter gradually varying from 50 nm to 250 nm over a length of 1 mm are fabricated on a nanofiber with diameter around 450-550 nm. A key aspect of such a nanofabrication is that the nanofiber itself acts as a cylindrical lens and focuses the femtosecond laser beam on its shadow surface. Moreover, the single-shot fabrication makes it immune to mechanical instabilities and other fabrication imperfections. Such periodic nano-craters on nanofiber, act as a 1D PhC and enable strong and broadband reflection while maintaining the high transmission out of the stopband. We also present a method to control the profile of the nano-crater array to fabricate apodized and defect-induced PhC cavities on the nanofiber. The strong confinement of the field, both transverse and longitudinal, in the nanofiber-based PhC cavities and the efficient integration to the fiber networks, may open new possibilities for nanophotonic applications and quantum information science.
<b>Author Comments:</b>	
<b>Additional Information:</b>	
<b>Question</b>	<b>Response</b>
If this article needs to be "in-press" by a certain date, please indicate the date	

below and explain in your cover letter.

Editor  
*JoVE*

Thursday, June 16, 2016

Dear Editor,

I am enclosing herewith a manuscript entitled "*Fabrication of 1D Photonic Crystal Cavity on a Nanofiber Using Femtosecond Laser Induced Ablation*," by K. P. Nayak, Jameesh Keloth, and K. Hakuta, which I would like to submit for publication in *JoVE*. The length of the text manuscript is 11 pages. Apart from that, 5 figures, 1 table and 1 materials list is submitted as separate files.

In this article, we present a protocol for fabricating 1D photonic crystal (PhC) cavities on subwavelength-diameter tapered optical fibers, optical nanofibers, using femtosecond laser induced ablation. We show that thousands of periodic nano-craters are fabricated on an optical nanofiber by irradiating with just a single femtosecond laser pulse. A key aspect of such a nanofabrication is that the nanofiber itself acts as a cylindrical lens and focuses the femtosecond laser beam on its shadow surface. Moreover, the single-shot fabrication makes it immune to mechanical instabilities and other fabrication imperfections. Such periodic nano-craters on nanofiber, act as a 1-D PhC cavity. Due to the strong confinement of the field and the efficient coupling to single-mode optical fibers, such nanofiber-based PhC cavities open new possibilities for quantum information science and nanoscale sensing applications. This video protocol is intended to help others implement and adapt such new type of nanofabrication technique.

Neelima Chandrayan, Science Editor of *JoVE*, has assisted us in the submission process.

Potential reviewers for the article are

- 1- Limin Tong, Zhejiang University, [phytong@zju.edu.cn](mailto:phytong@zju.edu.cn)
- 2- Gilberto Brambilla, University of Southampton, [gilberto@soton.ac.uk](mailto:gilberto@soton.ac.uk)
- 3- Luis A. Orozco, University of Maryland, [lorozco@umd.edu](mailto:lorozco@umd.edu)
- 4- Julien Laurat, Universite P. et M. Curie, [julien.laurat@upmc.fr](mailto:julien.laurat@upmc.fr)
- 5- Sile Nic Chormaich, Okinawa Institute of Science and Technology, [sile.nicchormaich@oist.jp](mailto:sile.nicchormaich@oist.jp)
- 6- Arno Rauschenbeutel, Technische Universität Wien, [arno.rauschenbeutel@ati.ac.at](mailto:arno.rauschenbeutel@ati.ac.at)

Sincerely,

Dr. Kohzo Hakuta

Professor & Director

Center for Photonic Innovations

UEC Tokyo, The University of Electro-Communications

Chofu, Tokyo 182-8585, Japan

Phone +81-42443-5447

Email: [k.hakuta@cpic.uec.ac.jp](mailto:k.hakuta@cpic.uec.ac.jp)

**TITLE:**

Fabrication of 1D Photonic Crystal Cavity on a Nanofiber Using Femtosecond Laser Induced Ablation

**AUTHORS:**

Nayak, Kali Prasanna  
Center for Photonic Innovations  
University of Electro-Communications  
Tokyo, Japan  
[kali@cpi.uec.ac.jp](mailto:kali@cpi.uec.ac.jp)

Keloth, Jameesh  
Center for Photonic Innovations  
University of Electro-Communications  
Tokyo, Japan  
[jameesh@cpi.uec.ac.jp](mailto:jameesh@cpi.uec.ac.jp)

Hakuta, Kohzo  
Center for Photonic Innovations  
University of Electro-Communications  
Tokyo, Japan  
[k.hakuta@cpi.uec.ac.jp](mailto:k.hakuta@cpi.uec.ac.jp)

**CORRESPONDING AUTHOR:**

Kohzo Hakuta  
([k.hakuta@cpi.uec.ac.jp](mailto:k.hakuta@cpi.uec.ac.jp))

**KEYWORDS:**

Quantum Optics, Nanophotonics, Nanofabrication, Laser Ablation, Photonic Crystal, Optical Nanofiber, Quantum Sensing, Quantum Information

**SHORT ABSTRACT:**

We present a protocol for fabricating 1D photonic crystal cavities on subwavelength diameter silica fibers (optical nanofibers) using femtosecond laser induced ablation.

**LONG ABSTRACT:**

We present a protocol for fabricating 1D photonic crystal (PhC) cavities on subwavelength-diameter tapered optical fibers, optical nanofibers, using femtosecond laser induced ablation. We show that thousands of periodic nano-craters are fabricated on an optical nanofiber by irradiating with just a single femtosecond laser pulse. For a typical sample, periodic nano-craters with a period of 350 nm and with diameter gradually varying from 50 nm to 250 nm over a length of 1 mm are fabricated on a nanofiber with diameter around 450-550 nm. A key aspect of such a nanofabrication is that the nanofiber itself acts as a cylindrical lens and focuses the femtosecond laser beam on its shadow surface. Moreover, the single-shot fabrication makes it immune to mechanical instabilities and other fabrication imperfections. Such periodic nano-craters on nanofiber, act as a 1D PhC and enable strong and broadband reflection while maintaining the high transmission out of the stopband. We also present a

method to control the profile of the nano-crater array to fabricate apodized and defect-induced PhC cavities on the nanofiber. The strong confinement of the field, both transverse and longitudinal, in the nanofiber-based PhC cavities and the efficient integration to the fiber networks, may open new possibilities for nanophotonic applications and quantum information science.

## **INTRODUCTION:**

Strong confinement of light in nanophotonic devices has opened new frontiers in optical science. Modern nanofabrication technologies have enabled fabrication of 1D and 2D photonic crystal (PhC) cavities for new prospects in lasing <sup>1</sup>, sensing <sup>2</sup> and optical switching applications <sup>3</sup>. Moreover, strong light-matter interaction in these PhC cavities has opened new avenues for quantum information science <sup>4</sup>. Apart from PhC cavities, plasmonic nanocavities have also shown promising prospects <sup>5,6,7</sup>. However, interfacing such cavities to fiber-based communication network remains a challenge.

In recent years, tapered single mode optical fiber with subwavelength diameter, known as optical nanofiber, has emerged as a promising nanophotonic device. Due to the strong transverse confinement of the nanofiber guided field and the ability to interact with the surrounding medium, the nanofiber is widely adapted and investigated for various nanophotonic applications <sup>8</sup>. Apart from that, it is also strongly investigated and implemented for quantum manipulation of light and matter <sup>9</sup>. Efficient coupling of emission from quantum emitters like, single/few laser-cooled atoms and single quantum dots, into the nanofiber guided modes has been studied and demonstrated <sup>10-15</sup>. The light-matter interaction on nanofiber can be significantly improved by implementing PhC cavity structure on the nanofiber <sup>16,17</sup>.

The key advantage for such a system is the fiber-in-line technology which can be readily integrated to communication network. Light transmission of 99.95% through the tapered nanofiber has been demonstrated <sup>18</sup>. However, the nanofiber transmission is extremely susceptible to dust and contamination. Therefore, fabrication of PhC structure on nanofiber using conventional nanofabrication technique is not very fruitful. Although cavity fabrication on nanofiber using focused ion beam (FIB) milling has been demonstrated <sup>19,20</sup>, the optical quality and reproducibility is not as high.

In this video protocol, we present a recently demonstrated <sup>21,22</sup> technique to fabricate PhC cavities on nanofiber using femtosecond laser ablation. The fabrications are performed by creating a two-beam interference pattern of the femtosecond laser on the nanofiber and irradiating a single femtosecond laser pulse. The lensing effect of the nanofiber plays an important role in the feasibility of such techniques, creating ablation craters on the shadow surface of the nanofiber. For a typical sample, periodic nano-craters with a period of 350 nm and with diameter gradually varying from 50 nm to 250 nm over a length of 1 mm are fabricated on a nanofiber with diameter around 450-550 nm. Such periodic nano-craters on nanofiber, act as a 1D PhC. We also present a method to control the profile of the nano-crater array to fabricate apodized and defect-induced PhC cavities on the nanofiber.

A key aspect of such nanofabrication is the all optical fabrication, so that high optical quality can be maintained. Moreover, the fabrication is done by the irradiation of just a single

femtosecond laser pulse, making the technique immune to mechanical instabilities and other fabrication imperfections. Also this enables in-house production of PhC nanofiber cavity so that the probability of contamination can be minimized. This protocol is intended to help others implement and adapt this new type of nanofabrication technique.

Figure 1a shows the schematic diagram of the fabrication setup. The details of the fabrication setup and alignment procedures are discussed in <sup>21, 22</sup>. A femtosecond laser with 400 nm center wavelength and 120 fs pulse width is incident on a phase mask. The phase mask splits the femtosecond laser beam into 0 and  $\pm 1$  orders. A beam block is used to block the 0-order beam. The folding mirrors symmetrically recombine the  $\pm 1$ -orders at the nanofiber position, to create an interference pattern. The pitch of the phase mask is 700 nm, so the interference pattern has a pitch ( $\Lambda_G$ ) of 350 nm. The cylindrical lens focuses the femtosecond laser beam along the nanofiber. The beam size across (Y-axis) and along (Z-axis) the nanofiber is 60  $\mu\text{m}$  and 5.6 mm, respectively. The tapered fiber is mounted on a holder equipped with piezo actuator (PZT) for stretching the fiber. A top cover with glass plate is used to protect the nanofiber from dust. The holder with the tapered fiber is fixed on a fabrication bench equipped with translation (XYZ) and rotation ( $\theta$ ) stages. The  $\theta$ -stage allows rotation of the nanofiber sample in the YZ-plane. The X-stage can also control the tilt angles along XY- and XZ-plane. A CCD camera is placed at a distance of 20 cm from the nanofiber and at an angle of  $45^\circ$  in the XY-plane to monitor the nanofiber position. All the experiments are performed inside a clean booth equipped with HEPA (High-efficiency particulate arresting) filters to achieve dust-free conditions. Dust-free condition is essential to maintain the transmission of the nanofiber.

Figure 1b shows the schematic of the optical measurements. During fabrication, the optical properties are briefly monitored by launching a broadband (wavelength range: 700 - 900 nm) fiber-coupled light source into the tapered fiber and measuring the spectrum of the transmitted and reflected light using high resolution spectrum analyzer. A tunable CW laser source is used to properly resolve the cavity modes and to measure the absolute cavity transmission.

We present the protocol for the fabrication and characterization. The protocol section is divided in three subsections, nanofiber preparation, femtosecond laser fabrication and characterization of the fabricated samples.

## **PROTOCOL:**

**CAUTION:** Wear safety glasses and strictly avoid direct exposure to UV lamp and all lasers including the femtosecond laser. Wear a clean room suit and gloves to avoid contamination. Dispose any fiber trash properly in the designated trash box.

### **1. Nanofiber preparation**

1.1) Use a fiber coating stripper to strip the polymer jacket of the single mode optical fiber for a length of 5 mm at two places separated by 200 mm. Clean the two mechanically stripped parts using cleanroom wipe dipped in methanol. Dip the fiber between these two stripped parts in acetone. Wait for 10-15 min till the jacket of the fiber fall apart. Take out the fiber

from acetone and clean the entire stripped part using cleanroom wipe dipped in methanol.

1.2) Set the stripped fiber on the two stages of the Optical Nanofiber Manufacture Equipment (ONME) to fabricate the nanofiber.

1.2.1) Launch the probe laser into the fiber and monitor the transmission using the photodiode and record the transmission data in the computer using the ADC card. Start the gas flow using the ONME software and ignite the flame. Load the pre-optimized parameter in the ONME software for the fabrication of tapered fiber with waist diameter of 500 nm and start the fabrication process.

Note: The ONME is a commercially available device, designed to fabricate tapered optical fibers using standard heat and pull technique. It uses oxyhydrogen flame to heat the fiber and two motorized stages to pull the fiber. The gas flow and the stage movements are controlled by computer program. The pre-optimized parameters may be obtained from the vendor, upon special request.

1.3) After the fabrication, catch the tapered fiber to the nanofiber holder using the UV curable epoxy. Cover the nanofiber holder using the top cover with glass plate (shown in the Figure 1a). Put the sample inside a clean box and transfer to the femtosecond laser fabrication unit.

## **2. Femtosecond laser fabrication**

2.1) Alignment of the fabrication setup

2.1.1) Put a glass plate on the fabrication bench at a height of 15 mm. Irradiate the femtosecond laser for 5 s at pulse energy of 1 mJ. Identify the femtosecond laser induced ablation from the white light generation, and the appearance of ablation pattern as a damage-line on the glass plate.

2.1.2) Repeat the procedure by changing the height of the glass plate using the X-stage of the fabrication bench. For each fabrication, translate the Y-stage of the fabrication bench by 1 mm to make the fabrication in a new position.

2.1.3) Find the height for the strongest ablation line. At this position, fine tune the tilt angle and position of one of the folding mirrors to maximize the ablation. Also, fine tune the tilt of the X-stage of the fabrication bench to maximize the ablation.

Note: The tilt angle of the folding mirror is tuned using the kinematic mirror holder tuning knobs and the position of the mirror is tuned by translating the Z-stage on which it is mounted.

2.1.4) After the optimization, mark the position of the ablation line on the CCD camera software and remove the glass plate.

Note: The control software for the CCD camera enables image capture and drawing marks on the captured image. It also enables saving the data of the captured image and the markings. Since the X-stage of the fabrication bench does not have absolute position reference, the CCD image is used as the position reference in the X-axis. The resolution of the CCD image is 10

μm per pixel.

2.1.5) Using the Platinum (Pt)-coater, coat the glass plate for 60 s to deposit a 25 nm layer of Pt on the glass plate. Image the ablation pattern on the glass plate using a scanning electron microscope (SEM). If the ablation pattern shows periodic structure with a period of 350 nm (the expected interference fringe pattern) then the alignment is optimized. Else repeat the procedure (from Step 2.1.1 to 2.1.4) for lower pulse energies (down to 300 μJ) until a periodic ablation pattern is seen.

## 2.2) Fabrication of apodized PhC cavity

2.2.1) Place the tapered fiber on the fabrication bench approximately parallel to the ablation line marked on the CCD camera.

2.2.2) Send a probe laser (power = 1 mW) through the tapered fiber and observe the scattering from the tapered fiber on the CCD camera. The strongest scattering part corresponds to the nanofiber region due to its subwavelength diameter.

2.2.3) Translate the Z-stage of the fabrication bench to center the nanofiber to the ablation line position marked on the CCD camera.

2.2.4) Switch off the probe laser and irradiate the femtosecond laser with minimum pulse energy (< 10 μJ). Translate Y-stage to overlap the nanofiber with the femtosecond laser beam. The overlap is identified by the illumination of the nanofiber, observed on the CCD camera.

Note: The nanofiber is now aligned with respect to the femtosecond laser beam along Y and Z-axis.

2.2.5) In order to align the nanofiber along the X-axis, translate the X-stage to overlap the nanofiber position to the ablation line position marked on the CCD camera.

2.2.6) Translate the Y-stage to maximize the overlap of nanofiber with the femtosecond laser. Observe the reflection of the two first orders from the nanofiber (appears as two bright spots on the glass plate of the top cover). Observe the movement of these reflection spots while translating the Y-stage back and forth.

Note: If these spots move towards one side then nanofiber is not parallel to the ablation line. In this case, rotate the rotation stage to make the nanofiber parallel to the ablation line. When they are parallel, the reflection spots will appear as a flash.

2.2.7) After making the nanofiber parallel to the ablation line, translate the Y-stage to maximize the overlap between the femtosecond laser beam and nanofiber, by measuring the power of the femtosecond laser scattered into the nanofiber guided modes using a photodiode at the end of the tapered fiber. After maximizing the overlap, rotate the rotation stage to the angle of fabrication  $\theta = 0.5$  deg.

Note: For maximum overlap between the femtosecond laser beam and nanofiber, one would expect the power of the femtosecond laser light scattered into the nanofiber guided modes to be maximized.



2.2.8) Block the femtosecond laser with the power meter and set the pulse energy to 0.27 mJ. Change the femtosecond laser settings to the single-shot irradiation mode.

Note: In this mode, only a single pulse is generated when the fire-switch is pressed, otherwise there is no laser output.

2.2.8.1) Remove the power meter from the laser beam path and fire a single femtosecond laser pulse. This completes the fabrication process.

### 2.3) Fabrication of defect-induced PhC cavity

2.3.1) Check the alignment of the setup by observing the ablation on a glass plate as described in the section 2.1. After finding the height for the strongest ablation line, insert a 0.5 mm copper wire at the center of the laser beam just before the phase mask. The copper wire should be along the Y-axis (perpendicular to the ablation line).

2.3.2) Check the ablation pattern on the glass plate while changing the position of the copper wire along the Z-axis. Fix the position of the copper wire when the ablation pattern shows a single gap at the center of the ablation line.

2.3.3) After the alignment, perform the femtosecond laser fabrication on the nanofiber following the procedure detailed in the section 2.2. For this fabrication, set the angle of fabrication to  $\theta = 0$  deg.

## 3. Characterization of the fabricated samples

### 3.1) Measurement of optical properties

3.1.1) Prepare the setup for the optical measurements as shown in Figure 1b. Launch the broadband light source into the tapered fiber and measure the transmission and reflection spectrum before and after the fabrication using the spectrum analyzer. After fabrication, the transmission spectrum will show a stopband corresponding to the Bragg resonance of the fabricated sample.

3.1.2) Rotate the paddles of the fiber inline polarizer to select the polarization and take the spectra for two orthogonal polarizations X-pol and Y-pol.

Note: For the X-pol (polarization along the nano-craters) the stopband will be blue-shifted <sup>21</sup> (towards the shorter wavelength) and the scattering from the nanofiber will be stronger. So, select the polarizations by looking at the spectrum and the CCD camera.

3.1.3) For one of the polarizations, take the transmission spectra by stretching the tapered fiber using the PZT (shown in Figure 1b). Take the spectra by stretching the tapered fiber in steps of 2  $\mu\text{m}$  until the maximum stretching length of 20  $\mu\text{m}$  (limited by the PZT scanning range). Observe that the Bragg resonance will be red-shifted (towards the longer wavelength) by stretching the tapered fiber. From these spectra, calculate the shift of the Bragg resonance, per unit stretching length.

3.1.4) For resolving the cavity modes and measuring the absolute cavity transmission, use

the tunable CW laser source. Launch the laser into the tapered fiber and monitor the transmission using a photodiode.

3.1.5) Set the laser wavelength to the red-side edge of the stopband for Y-pol and use the fiber inline polarizer to minimize the transmission. In this way, the X-pol component is suppressed and only the Y-pol is selected. Set the laser wavelength to further out of the red-side band-edge and record the transmission while stretching the tapered fiber from 0 to 20  $\mu\text{m}$ .

3.1.5.1) Repeat the measurement by changing the laser wavelength to blue-side in steps of 0.3 nm until the entire stopband is covered. From these data, reconstruct the entire spectrum using the data for the resonance shift per unit stretching length measured in step 3.1.3.

Note: For a typical sample, the stopband (Bragg resonance) along with the cavity modes shifts by 2 nm by stretching the tapered fiber by 20  $\mu\text{m}$  and the typical free spectral range for the cavity modes are between 0.05 nm to 0.5 nm. For a given wavelength of the input laser one can measure at least 3 to 4 cavity modes by stretching the tapered fiber. The frequency spacing between the modes is inferred from the data for the resonance shift per unit stretching length measured in step 3.1.3. Repeating the measurement by changing the laser wavelength in steps of 0.3 nm, at least 2 to 3 consecutive cavity modes are re-measured in the successive measurements. One can reconstruct the entire spectrum by overlaying the transmission data for the successive measurements while matching position of the re-measured cavity modes.

3.1.6) Now measure the spectrum for the other polarization using similar procedure as mentioned in steps 3.1.5 and 3.1.5.1.

### 3.2) Imaging the fabricated sample

3.2.1) Put the fabricated sample on a 2 cm long metal plate and fix the two ends of the tapered fiber to the metal plate using UV curable epoxy. Make sure the irradiation side of the sample faces the metal plate so that the shadow side can be imaged.

3.2.2) Use the Pt-coater to coat the sample for 30 s and deposit a layer of Pt with a thickness of around 10 nm. Place the sample into the SEM. Take the SEM image of the sample at every 0.1 mm over the entire fabricated region.

### REPRESENTATIVE RESULTS:

Figure 2 shows the SEM image of a typical segment of the fabricated nanofiber sample. It shows that periodic nano-craters are formed on the shadow side of the nanofiber, with a periodicity of 350 nm corresponding well to the interference pattern. The inset shows the enlarged view of the sample. The shape of the nano-craters is almost circular and the diameter of a typical nano-crater is around 210 nm.

Figure 3a shows the fabrication results for the apodized PhC cavity. The typical profile of the nano-crater array along with the corresponding nanofiber diameter for different fabrication angle ( $\theta$ ) and pulse energy are shown. The circles denote the nano-crater diameter and the squares are the corresponding nanofiber diameter. The lines are the Gaussian fits to the

profiles. The data shown in black and green correspond to samples fabricated with  $\theta = 0$  deg, using pulse energy of 0.35 and 0.17 mJ, respectively. The data shown in red and blue correspond to samples fabricated with  $\theta = 0.5$  deg using pulse energy of 0.35 and 0.27 mJ, respectively. As one can see, the nano-craters are formed over a length of 2-3 mm along the nanofiber where the diameter of the nanofiber is uniform. An apodization in nano-crater diameter is observed corresponding to the Gaussian intensity distribution of the femtosecond laser beam. It is clearly seen that the diameter of the nano-craters is reduced for weaker pulse energy. Moreover, the width of the apodization profile of the nano-craters is reduced by increasing the angle of fabrication.

The fabrication result for the defect-induced PhC cavity is shown in Figure 3b. A double peak-like profile is observed. A gradual change in the diameter is observed at the outside edges of the peaks, whereas the diameter changed rapidly at the inside edge of the peaks. A defect region of 0.5 mm with no nano-craters is observed between two peaks. The length of the defect region corresponds well to the thickness of the copper wire inserted in to the femtosecond laser beam.

Figure 4 shows the transmission spectra for an apodized PhC cavity sample whose diameter profile is shown in blue in Figure 3a. Figures 4a and 4b show the typical transmission spectra for X- and Y-polarizations, respectively. The spectrum for the X-pol shows a stopband region from 793.7 to 798.8 nm, where the transmission drops to a few percent. The stopband for the Y-pol is red-shifted and broader compared to the X-pol. The sharp peaks observed in the red-side of the stopband are the cavity modes. The finesse and peak transmission of the typical cavity modes are listed in Table 1.

Figures 5a and 5b show the transmission spectra of the defect-induced PhC cavity for X- and Y-polarizations, respectively. As one can see, sharp cavity modes appear on either side of the stopband. However, the mode spacing in the blue-side is much larger than that in the red-side of the spectra. The finesse and peak transmission of the typical cavity modes are summarized in Table 1.

#### Figure Legends:

**Figure 1: Schematic diagram of the experiment.** a) Schematic diagram of the fabrication setup. A two-beam interference pattern is created on the nanofiber using a phase mask as the beam splitter and two folding mirrors (see text for details). A cylindrical lens is used to line focus the femtosecond laser along the nanofiber. A zero-order block is used to avoid any residual zero order light in the interference region. A photodiode is connected to one end of the tapered fiber to observe the scattering of the femtosecond laser into the nanofiber guided modes. A CCD camera is used to monitor the nanofiber position. b) Schematic diagram for the measurement of optical properties. The transmission and reflection spectra of the fabricated nanofiber samples are simultaneously measured by varying the polarization of the input light. PhC, PZT, NPBS and SA denote photonic crystal, piezo actuator, non-polarizing beam splitter and spectrum analyzer, respectively. This figure has been modified from<sup>21</sup>.

**Figure 2: SEM image of a fabricated sample.** SEM image of a typical sample fabricated using single-shot irradiation. The inset shows the enlarged view. The periodic nano-crater structures are observed on the shadow side of the nanofiber. This figure has been modified

from<sup>21</sup>.

**Figure 3: Diameter profile of the nano-crater array on the nanofiber along with the brief schematic of the fabrication method.** (a) The diameter profile for the apodized PhC cavity. The circles denote the nano-crater diameter and the squares are the corresponding nanofiber diameter. The lines are the Gaussian fits to the profiles. The data shown in black and green correspond to samples fabricated with  $\theta = 0$  deg, using pulse energy of 0.35 and 0.17 mJ, respectively. The data shown in red and blue correspond to samples fabricated with  $\theta = 0.5$  deg, using pulse energy of 0.35 and 0.27 mJ, respectively. (b) The diameter profile for the defect-induced PhC cavity fabricated using a pulse energy of 0.4 mJ. The blue circles and the black squares show the nano-crater diameter and the nanofiber diameter, respectively. This figure is reused from<sup>22</sup>.

**Figure 4: Transmission spectra of the apodized PhC cavity.** Transmission spectrum of apodized PhC cavity for (a) X-pol and (b) Y-pol. The parts of the spectra, marked by blue boxes are enlarged and shown in the insets. This figure is reused from <sup>22</sup>.

**Figure 5: Transmission spectra of the defect-induced PhC cavity.** Transmission spectrum of the defect-induced PhC cavity for (a) X-pol and (b) Y-pol. The parts of the spectra, marked by blue boxes are enlarged and shown in the insets. This figure is reused from <sup>22</sup>.

**Table 1: Optical characteristics of the typical cavity modes.** Table 1 summarizes the optical characteristics of typical cavity modes marked in Figures 4a, 4b, 5a and 5b. F, T, FSR, and L denote finesse, peak transmission, mode spacing, and estimated cavity length, respectively. This table is reused from<sup>22</sup>.

**Supplemental file 1: Photograph of the ONME setup.**

**Supplemental file 2: Photographs of the femtosecond laser fabrication setup.**

## DISCUSSION:

The lensing effect of the nanofiber plays an important role in the fabrication technique, thereby creating nano-craters on the shadow surface of the nanofiber (shown in Figure 2). The lensing effect of the nanofiber also makes the fabrication process robust to any mechanical instabilities in the transverse direction (Y-axis). Moreover, due to single-shot irradiation, the instabilities along the other axes do not affect the fabrication as the irradiation time is only 120 fs (i.e. pulse width). As a result, periodic nanostructures with well-defined periodicity are fabricated over several thousands of periods, without taking any special care to suppress mechanical vibrations.

Many nanofabrication techniques like FIB milling, electron beam lithography and even femtosecond laser ablation, implement point-by-point fabrication. The point-by-point fabrication is well suited for rigid samples, where the mechanical stability can be guaranteed. In case of optical nanofibers, if the tapered fiber is kept hanging without touching any rigid substrate then mechanical instabilities affects the fabrication process. On the other hand, if the nanofiber is placed on a rigid substrate then contamination from the substrate itself or due to the etching of the substrate can degrade the optical quality. In particular, with respect

to the FIB milling technique, additional drawbacks are mechanical instabilities due to charging up effects of the nanofiber and material modification due to contamination from the ion beam itself. Therefore, the protocol presented here for a single-shot optical fabrication on nanofiber is preferable to the point-by-point fabrication. However, point-by-point fabrication may be preferred for some applications where fabricating arbitrary pattern on the nanofiber is essential.

One crucial step in the protocol is the alignment of the fabrication setup. Since the fabrication is performed by femtosecond pulse with a pulse width of 120 fs, the optical path length difference between the  $\pm 1$ -orders should be minimized to ensure spatial overlap<sup>23</sup>. The path length difference should be less than 36  $\mu\text{m}$  to ensure high visibility of the interference fringe. Hence, the position and the tilt angles of the folding mirrors should be precisely controlled. Although the femtosecond laser beam size along the nanofiber is 5.6 mm the interference region is less than 1 mm along the X-axis limited by the spatial overlap of the pulses. It should also be taken care that the femtosecond laser beam is incident exactly perpendicular to the phase mask and the fabrication bench should be parallel to the phase mask. Even a tilt of 10 mrad can induce enough path length difference to wash out the interference fringe. Finally, the axis of the cylindrical lens should be precisely perpendicular to the lines on the phase mask. Otherwise it will induce a rotation angle between the line focused  $\pm 1$ -orders reducing the overlap between them.

Another critical requirement for successful fabrication is the production of high quality nanofiber. To get high finesse cavity modes, the original nanofiber transmission should be > 95% and should be free from dust or any contamination. Any contamination on nanofiber will induce irregular intensity pattern resulting in non-reproducible fabrication and may even break the nanofiber. The quality of the nanofiber is judged from the high transmission and scattering pattern of the guided modes observed on the CCD camera.

The transmission spectra, shown in Figures 4 and 5, show stopband regions where more than 98% of the input light is reflected and transmission drops to a few percent. The transmission away from the stopband is around 100% ensuring that the fabrication does not induce significant loss and maintains the optical quality of the nanofiber. Moreover, the observed high finesse cavity modes (listed in Table 1) inside the stopband further ensures the quality of the fabrication. The stopband is well understood from the Bragg reflection from the periodic nano-craters on the nanofiber. The Bragg resonance ( $\lambda_R = 2n_{\text{eff}}\Lambda_G$ ) depends on the effective index ( $n_{\text{eff}}$ ) of the guided mode and the pitch ( $\Lambda_G$ ) of the interference fringe. In the data presented in this protocol, the stopband is observed around a wavelength of 800 nm. The stopband and the cavity modes can be tuned over 10-15 nm by stretching the tapered fiber. However, to further change the resonance wavelength one must change the nanofiber diameter to realize a different  $n_{\text{eff}}$  or change the phase mask to realize a different  $\Lambda_G$ .

From the cavity modes listed in Table 1, finesse values ranging from 30 to 500 can be realized. Due to the strong transverse confinement of the nanofiber guided modes, high cooperativity / Purcell factors are expected for such finesse values<sup>16</sup>. The broadband tunability along with strong confinement of field in such a fiber-based PhC cavity offers high demand for various applications ranging from nanophotonics to quantum information science.

In conclusion, we have presented a protocol for fabricating 1D PhC cavities on subwavelength diameter silica fibers using femtosecond laser induced ablation. Such fabrication technique may be implemented to make various nanophotonic devices from micro/nanofibers and may be adapted to other nanofabrication processes.

#### ACKNOWLEDGMENTS:

This work was supported by the Japan Science and Technology Agency (JST) through the Strategic Innovation Program. KPN acknowledges support from a grant-in-aid for scientific research (Grant no. 15H05462) from the Japan Society for the Promotion of Science (JSPS).



#### DISCLOSURES:

The authors have nothing to disclose.


#### REFERENCES:



1. Painter, O. J. *et al.* Two-Dimensional Photonic Band-Gap Defect Mode Laser, *Science* **284**, 1819-1821, doi: 10.1126/science.284.5421.1819 (1999).
2. Loncar, M., Scherer, A., Qiu, Y. Photonic crystal laser sources for chemical detection, *Appl. Phys. Lett.* **82**, 4648, doi: 10.1063/1.1586781 (2003).
3. Tanabe, T., Notomi, M., Mitsugi, S., Shinya, A., Kuramochi, E. All-optical switches on a silicon chip realized using photonic crystal nanocavities, *Appl. Phys. Lett.* **87**, 151112, doi: 10.1063/1.2089185 (2005).
4. Yoshie, T. *et al.* Vacuum Rabi splitting with a single quantum dot in a photonic crystal nanocavity, *Nature* **432**, 200-203, doi: 10.1038/nature03119 (2004).
5. Akimov, A. V. *et al.* Generation of single optical plasmons in metallic nanowires coupled to quantum dots, *Nature* **450**, 402-406, doi:10.1038/nature06230 (2007).
6. Noginov, M. A. *et al.* Demonstration of a spaser-based nanolaser, *Nature* **460**, 1110-1112, doi:10.1038/nature08318 (2009).
7. Zhang, X. Y., Zhang, T., Hu, A., Song, Y. J., Duley, W. W. Controllable plasmonic antennas with ultra narrow bandwidth based on silver nano-flags, *Appl. Phys. Lett.* **101**, 153118, doi: 10.1063/1.4759122 (2012).
8. Tong, L., Zi, F., Guo, X., Lou, J. Optical microfibers and nanofibers: A tutorial, *Opt. Comm.* **285**, 4641-4647, doi: 10.1016/j.optcom.2012.07.068 (2012).
9. Morrissey, M. J. *et al.* Spectroscopy, manipulation and trapping of neutral atoms, molecules, and other particles using optical nanofibers: A review, *Sensors* **13**, 10449-10481, doi: 10.3390/s130810449 (2013).
10. Kien, F. L., Dutta Gupta, S., Balykin, V. I., Hakuta, K. Spontaneous emission of a cesium atom near a nanofiber: Efficient coupling of light to guided modes, *Phys. Rev. A* **72**, 032509, doi: 10.1103/PhysRevA.72.032509 (2005).
11. Nayak, K. P., Melentiev, P. N., Morinaga, M., Kien, F. L., Balykin, V. I., Hakuta, K. Optical nanofiber as an efficient tool for manipulating and probing atomic fluorescence, *Opt. Express* **15**, 5431-5438, doi: 10.1364/OE.15.005431 (2007).
12. Nayak, K. P., Hakuta, K. Single atoms on an optical nanofiber, *New J. Phys.* **10**, 053003, doi:10.1088/1367-2630/10/5/053003 (2008).
13. Nayak, K. P., Kien, F. L., Morinaga, M., Hakuta, K. Antibunching and bunching of photons in resonance fluorescence from a few atoms into guided modes of an optical nanofiber, *Phys. Rev. A* **79**, 021801, doi: 10.1103/PhysRevA.79.021801 (2009).
14. Yalla, R., Nayak, K. P., Hakuta, K. Fluorescence photon measurements from single

- quantum dots on an optical nanofiber, *Opt. Express* **20**, 2932-2941, doi: 10.1364/OE.20.002932 (2012).
15. Yalla, R., Kien, F. L., Morinaga, M., Hakuta, K. Efficient Channeling of Fluorescence Photons from Single Quantum Dots into Guided Modes of Optical Nanofiber, *Phys. Rev. Lett.* **109**, 063602, doi: 10.1103/PhysRevLett.109.063602 (2012).
  16. Kien, F. L., Hakuta, K. Cavity-enhanced channeling of emission from an atom into a nanofiber, *Phys. Rev. A* **80**, 053826, doi: 10.1103/PhysRevA.80.053826 (2009).
  17. Kato, S., Aoki, T. Strong coupling between a trapped single atom and an all-fiber cavity, *Phys. Rev. Lett.* **115**, 093603, doi: 10.1103/PhysRevLett.115.093603 (2015).
  18. Hoffman, J. E. *et al.* Ultrahigh transmission optical nanofibers, *AIP Advances* **4**, 067124, doi: 10.1063/1.4879799 (2014).
  19. Nayak, K. P. *et al.* Cavity formation on an optical nanofiber using focused ion beam milling technique, *Opt. Express* **19**, 14040-14050, doi: 10.1364/OE.19.014040 (2011).
  20. Kien, F. L., Nayak, K. P., Hakuta, K. Nanofibers with Bragg gratings from equidistant holes, *J. Modern Opt.* **59**, 274-286, doi: 10.1080/09500340.2011.628128 (2012).
  21. Nayak, K. P., Hakuta, K. Photonic crystal formation on optical nanofibers using femtosecond laser ablation technique, *Opt. Express* **21**, 2480-2490, doi: 10.1364/OE.21.002480 (2013).
  22. Nayak, K. P., Zhang, P., Hakuta, K. Optical nanofiber-based photonic crystal cavity, *Opt. Lett.* **39**, 232-235, doi: 10.1364/OL.39.000232 (2014).
  23. Becker, M. *et al.* Fiber Bragg grating inscription combining DUV sub-picosecond laser pulses and two-beam interferometry, *Opt. Express* **16**, 19169-19178, doi: 10.1364/OE.16.019169 (2008).

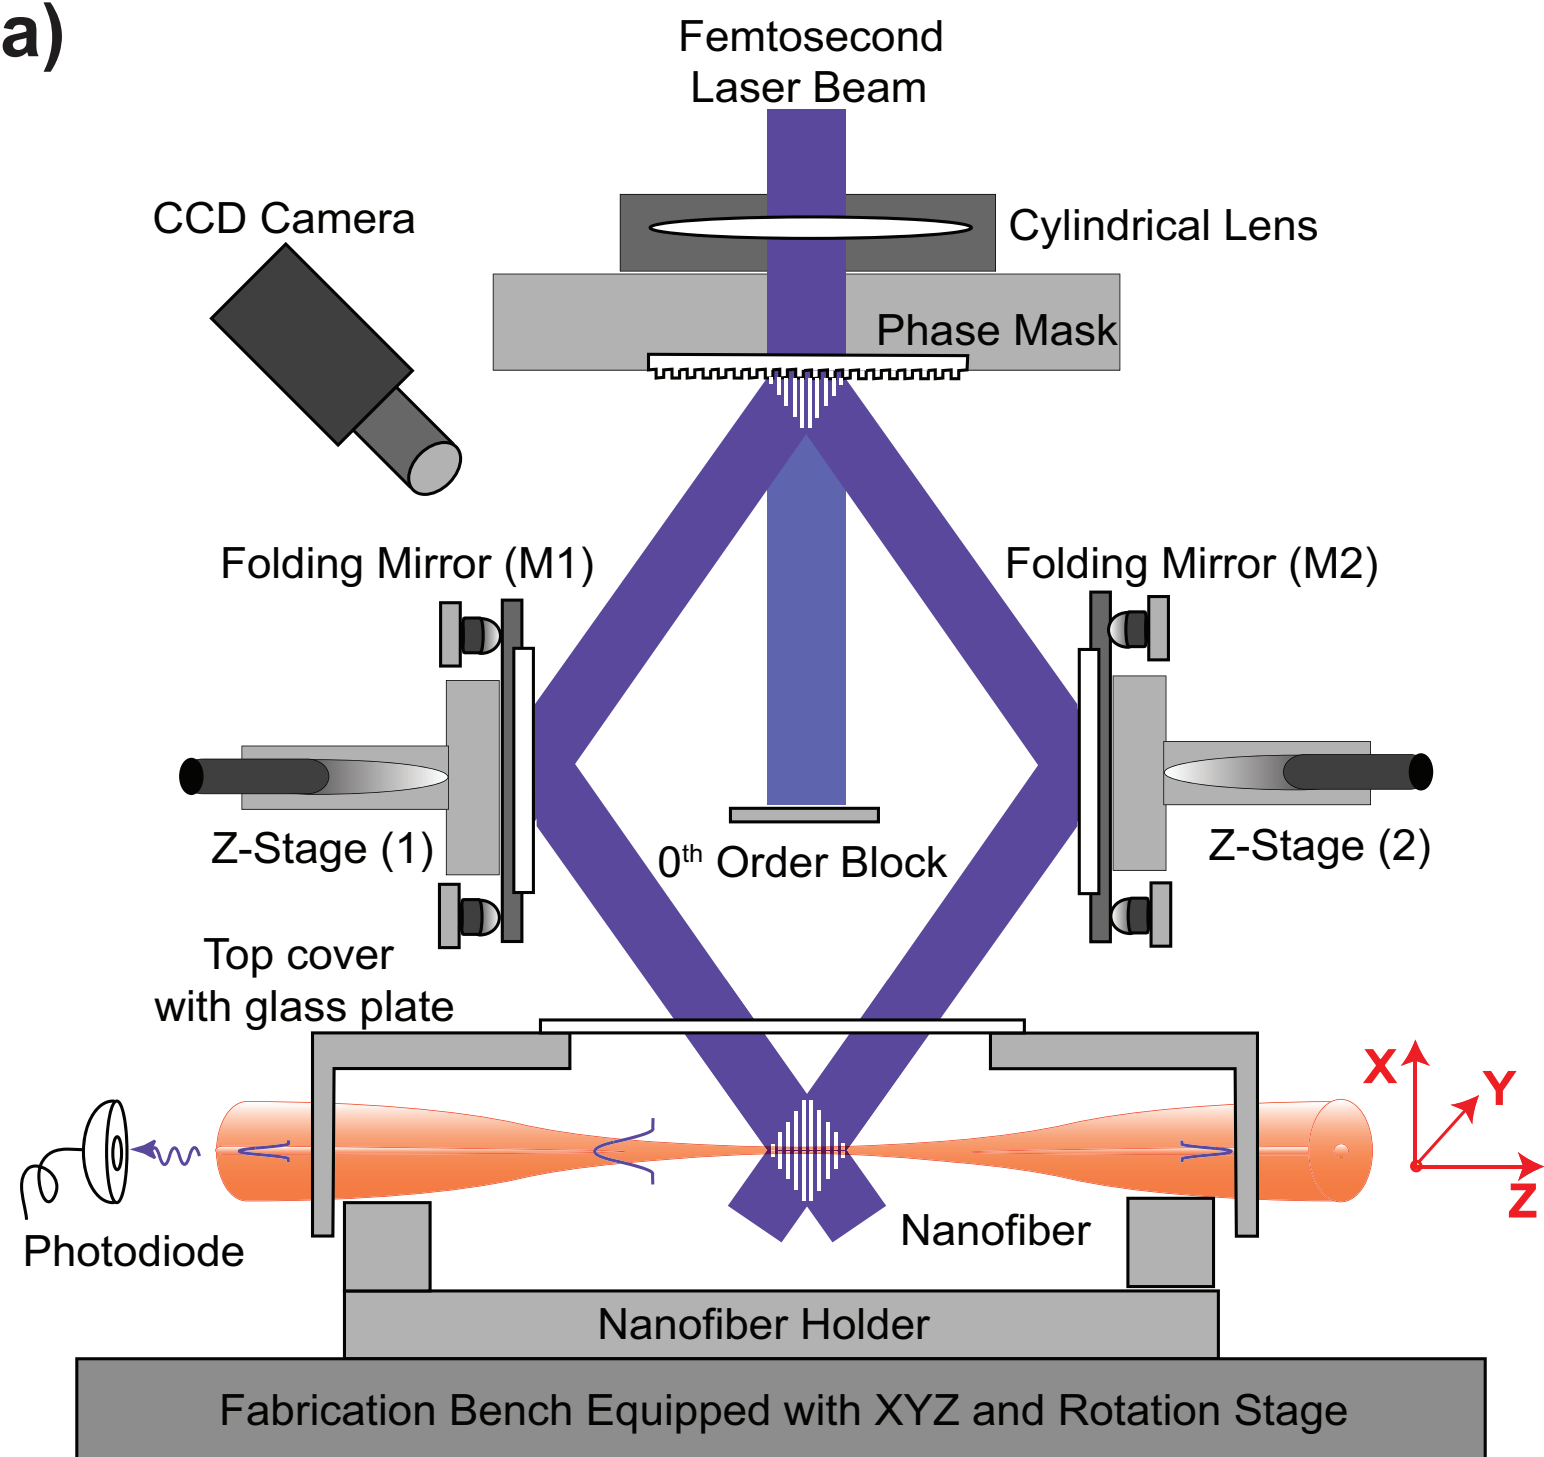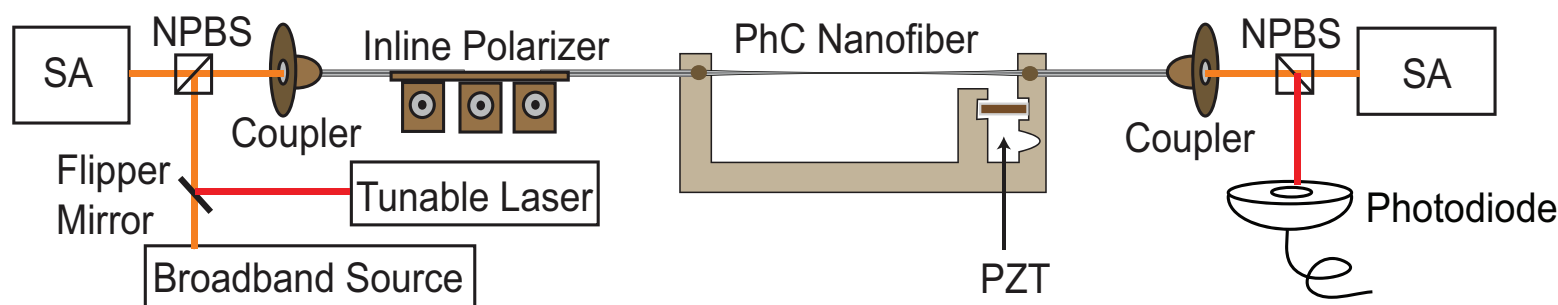**a)****b)**



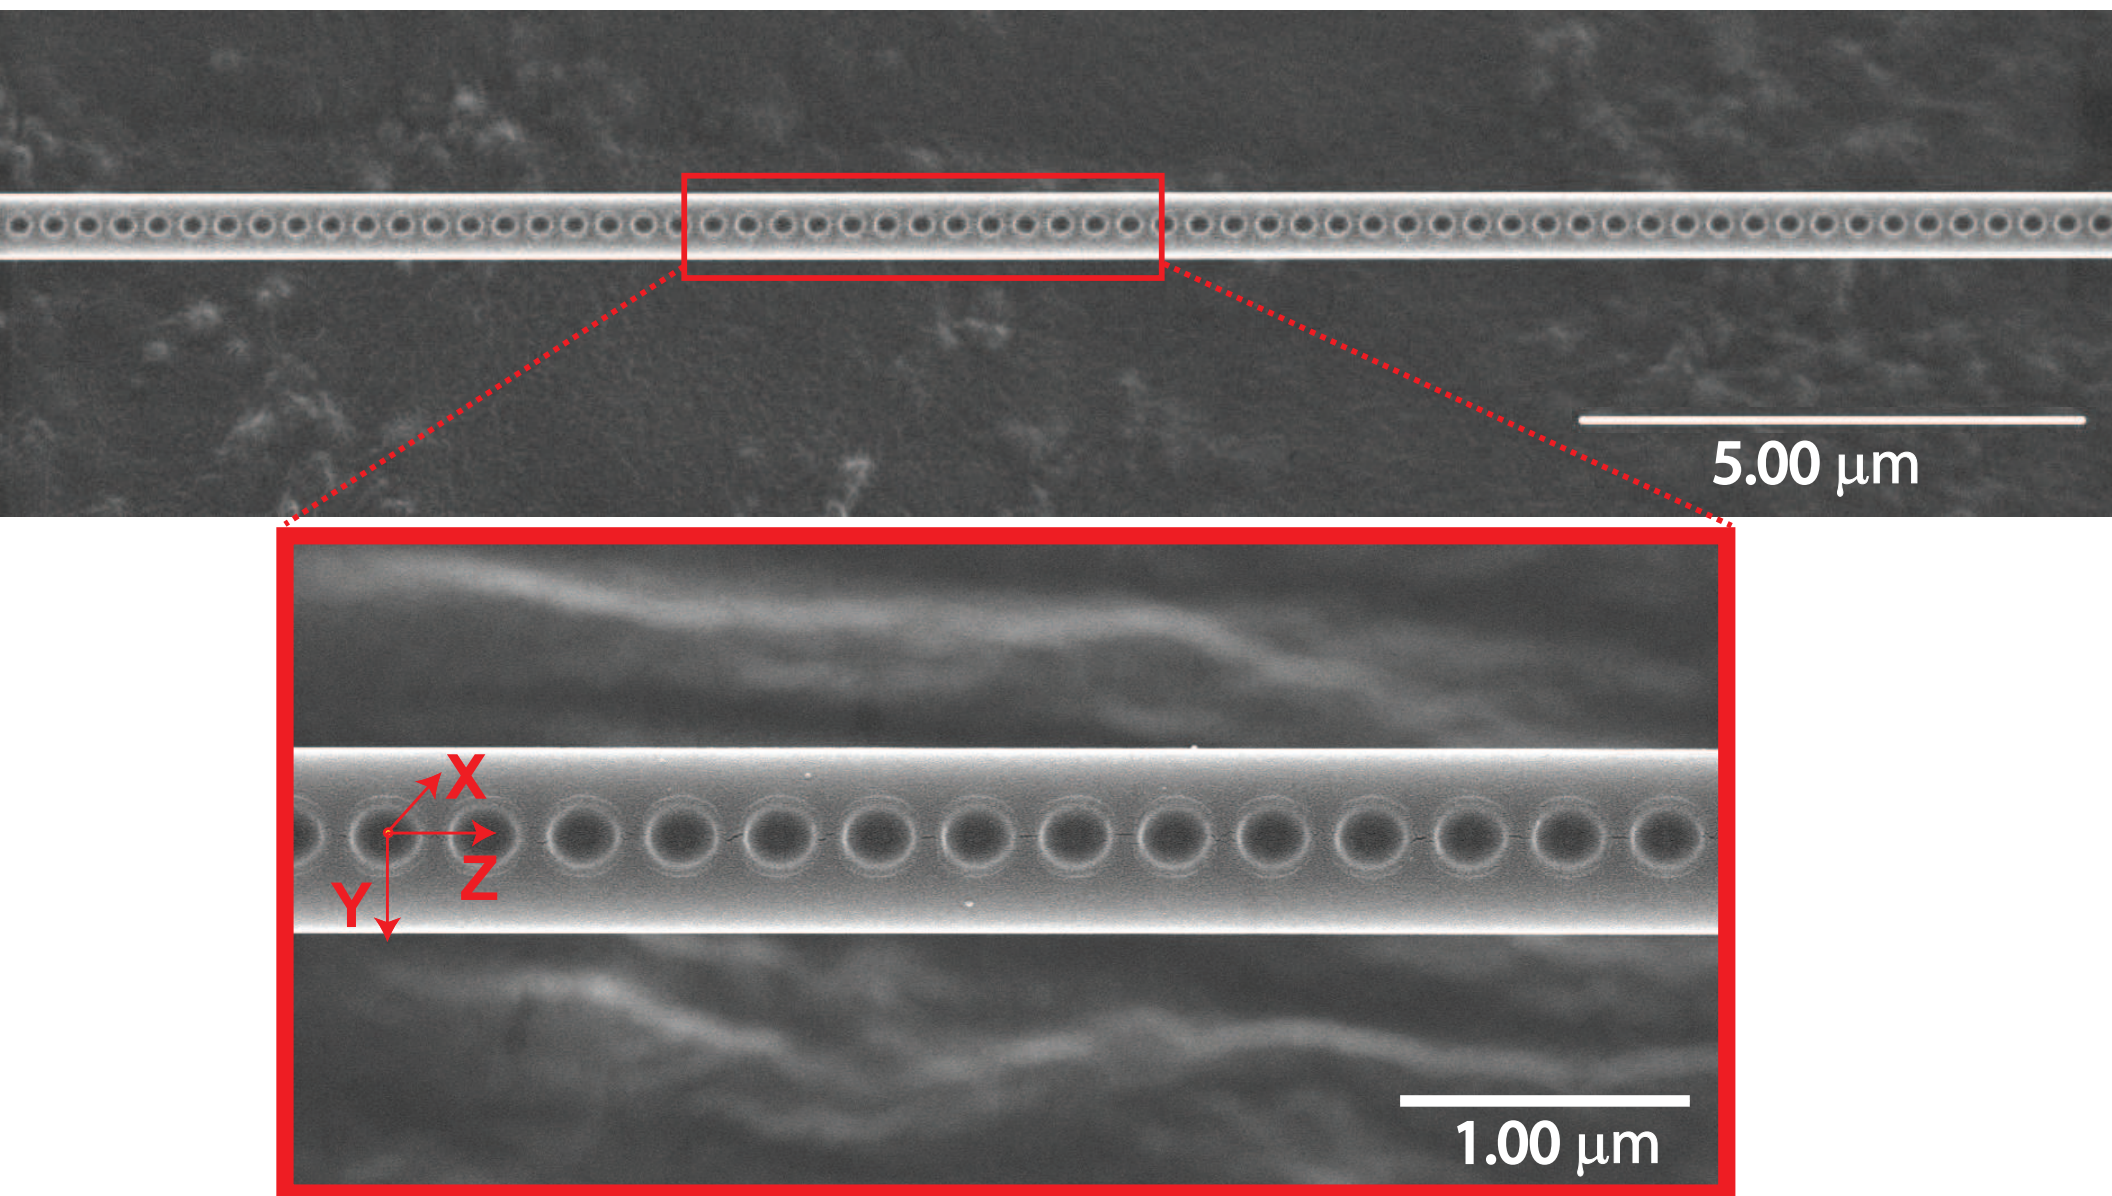

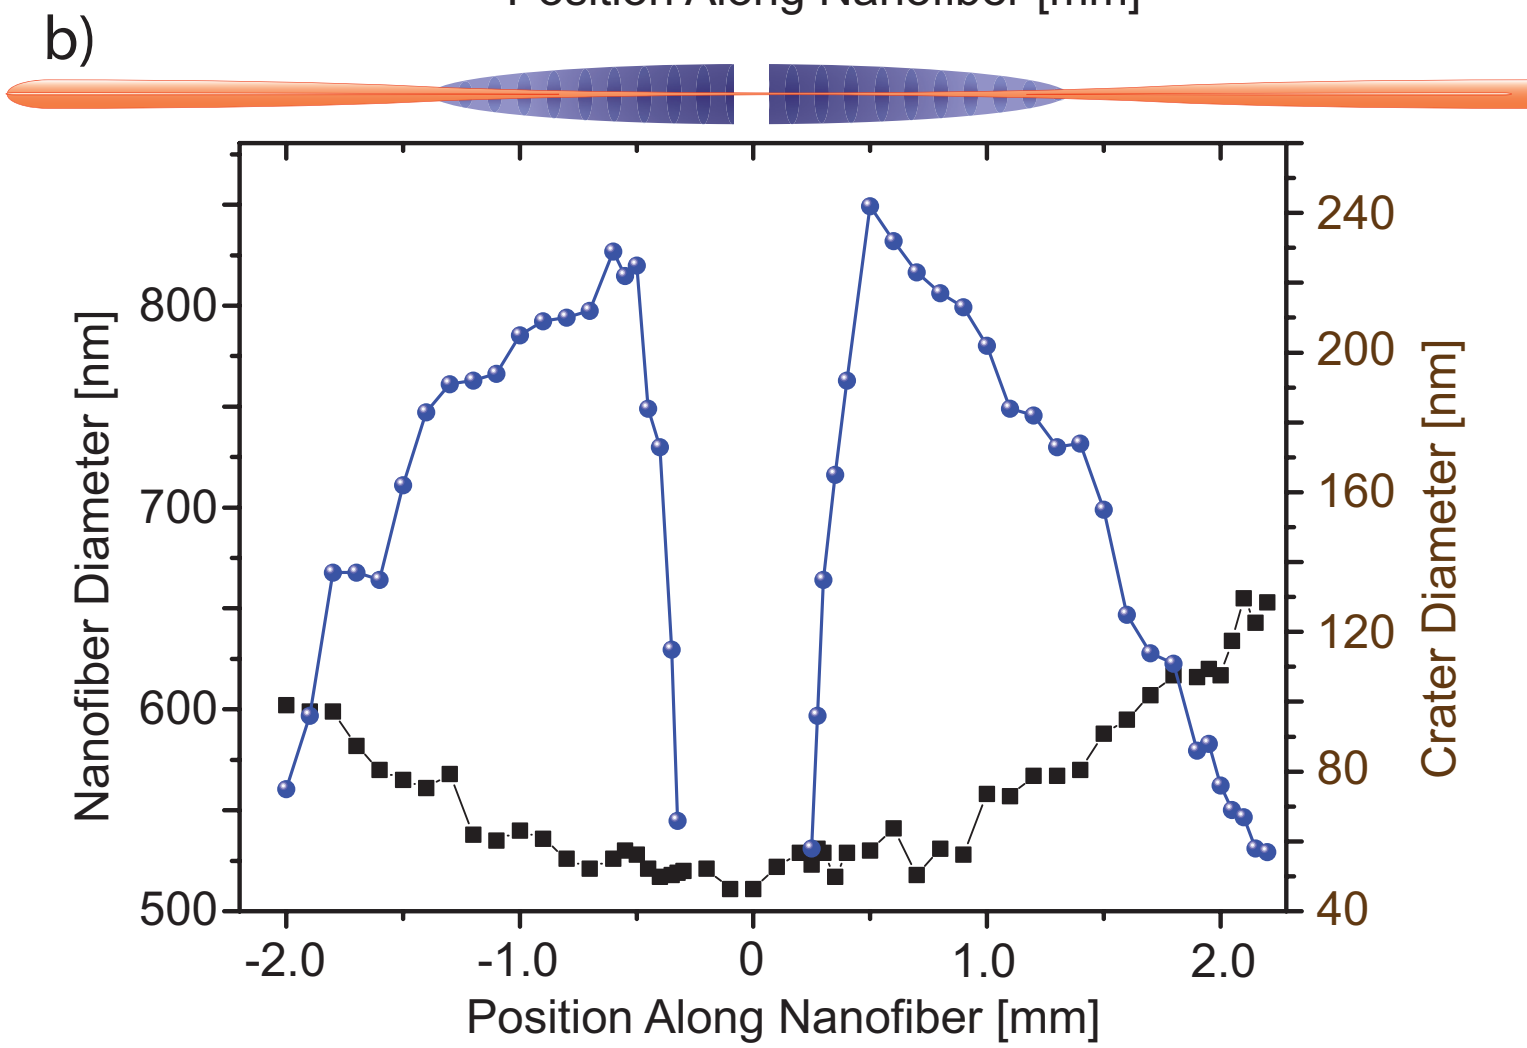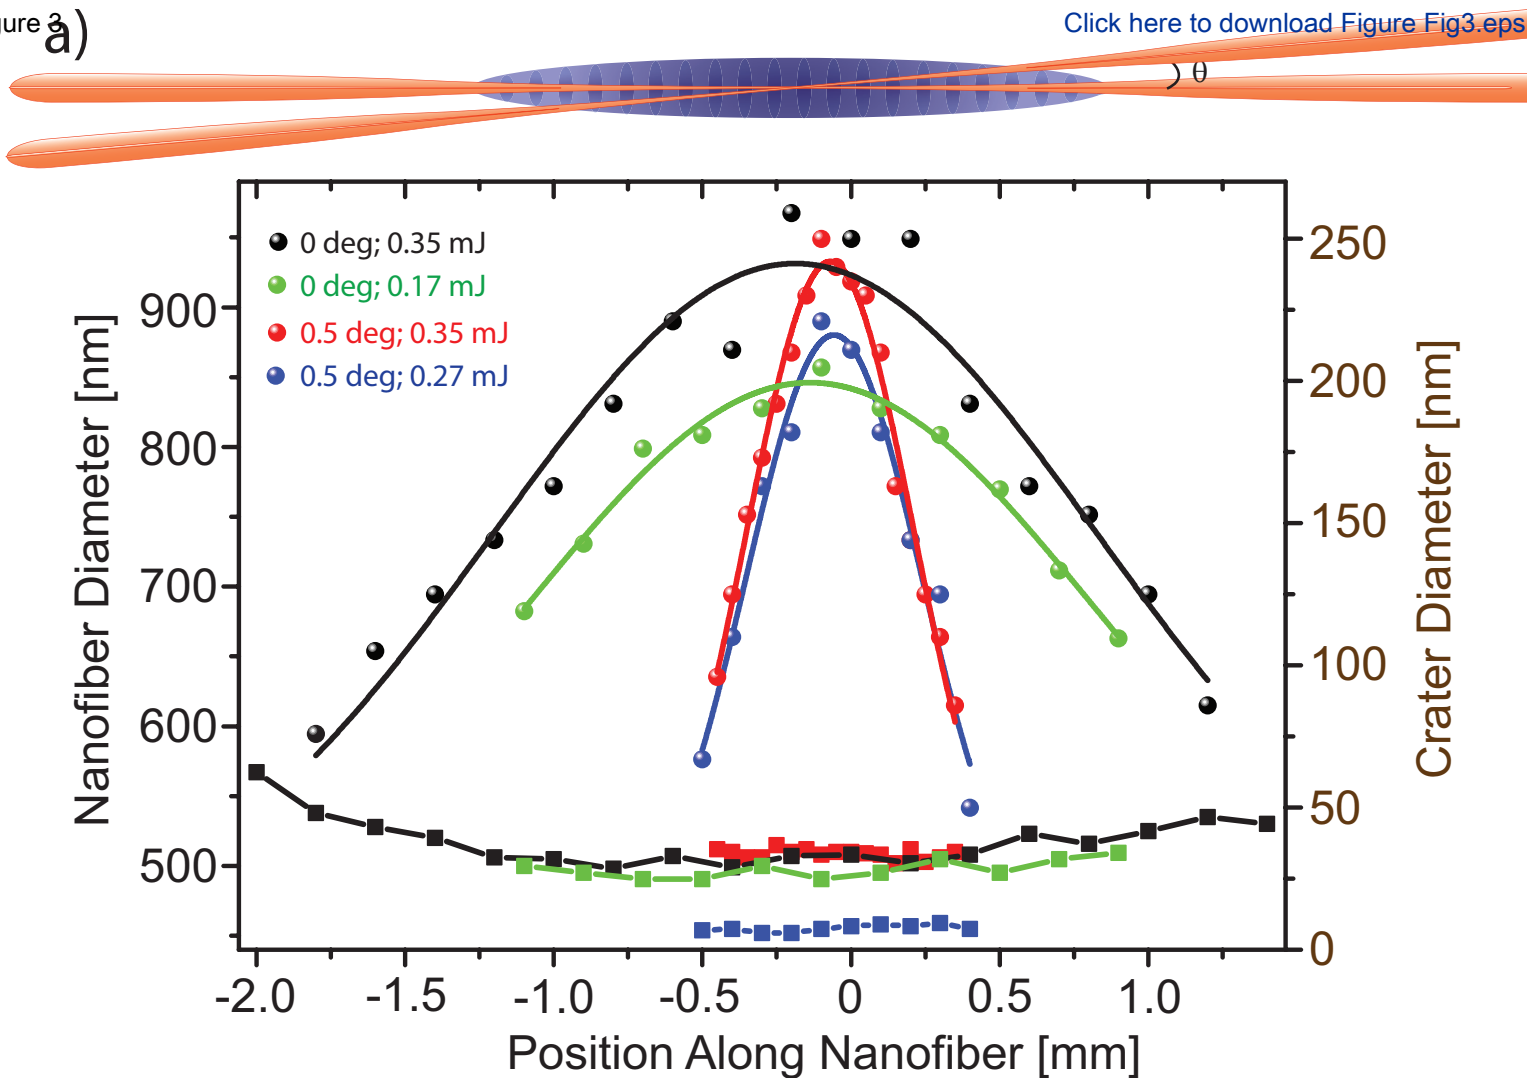


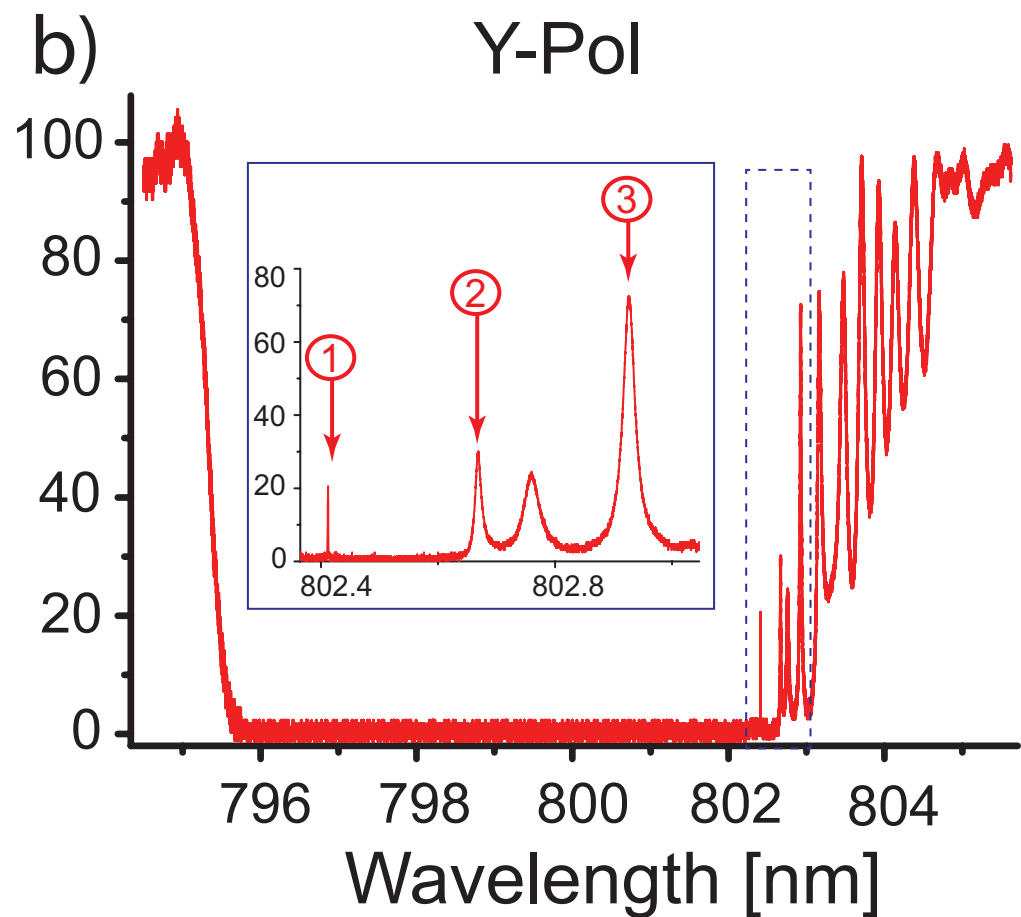


Figure 5



[Click here to download Figure Fig5.eps](#)

Figure	Mode	F	T [%]	FSR [cm <sup>-1</sup> ]	L [mm]
4(a)	(1,2,3)	(71, 39, 16)	(33, 87, 93)	7.94	0.54
4(b)	(1,2,3)	(500, 27, 11)	(21, 30, 73)	3.94	1.09
5(a)	(1,2,3,4)	(198, 115, 50, 21)	(25, 39, 64, 83)	3.34	1.28
	(A,B,C,D)	(86, 63, 48, 20)	(26, 56, 73, 90)	1.58	2.71
5(b)	(1,2,3,4)	(178, 104, 43, 22)	(17, 39, 65, 93)	3.15	1.36
	(A,B,C,D)	(48, 44, 24, 22)	(20, 38, 56, 87)	1.25	3.43

Name	Company	Model Number
Femtosecond Laser	Coherent Inc.	Libra HE
Phase Mask	Ibsen Photonics	Custom Made
Optial Nanofiber Manufacturing Equipment	Ishihara Sangyo	ONME
ADC Card	PicoTech	ADC-24
Single mode fiber	Fujikura	FutureGuide-SM
Broadband source	NKT Photonics	SuperK EXTREME
CW Tunable Laser	Coherent Inc.	MBR-110
Spectrum analyser (Transmission spectrum)	Thermo Fisher Scientific	Nicolet 8700
Spectrum analyser (Reflection spectrum)	Ocean Optics	QE65000
CCD Camera	Thorlabs	DCC1545M
Power Meter	Thorlabs	D3MM
Pt-Coater	Vacuum Device Inc.	MSP-1S
Scanning Electron Microscope	Keyence	VE-9800
UV Curable Epoxy	NTT-AT	AT8105
Photodiode	ThorLabs	PDA 36A-EC
Clean room wipe	TExWipe	TX-404
Fiber coating stripper	NTT-AT	Fiber nippers 250 um
Cover glass	Matsunami Glass IND,LTD	NEO micro cover glass 0.12-0.17 mm
PZT	NOLIAC	NAC 2011-H20
Cylindrical lens stage	NewPort	M-481-A
Y,Z stages	Chuo Precision Industrial Co., LTD.	LD-149-C7
Rotation stage	SIGMA KOKI	KSPB-1026MH
Z-stage(1), Z-stage(2)	NewPort	M-460P
Fiber coating stripper	NTT-AT	Fiber nippers 250 μm

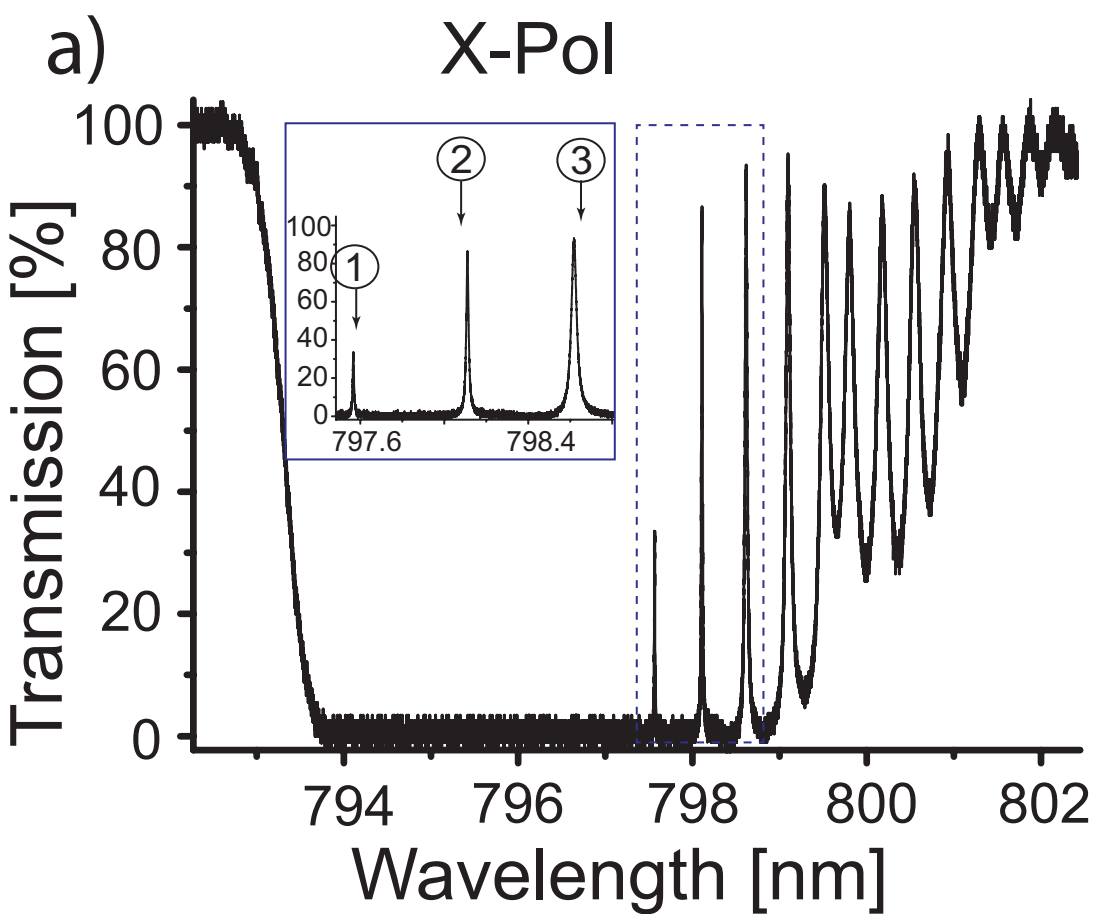

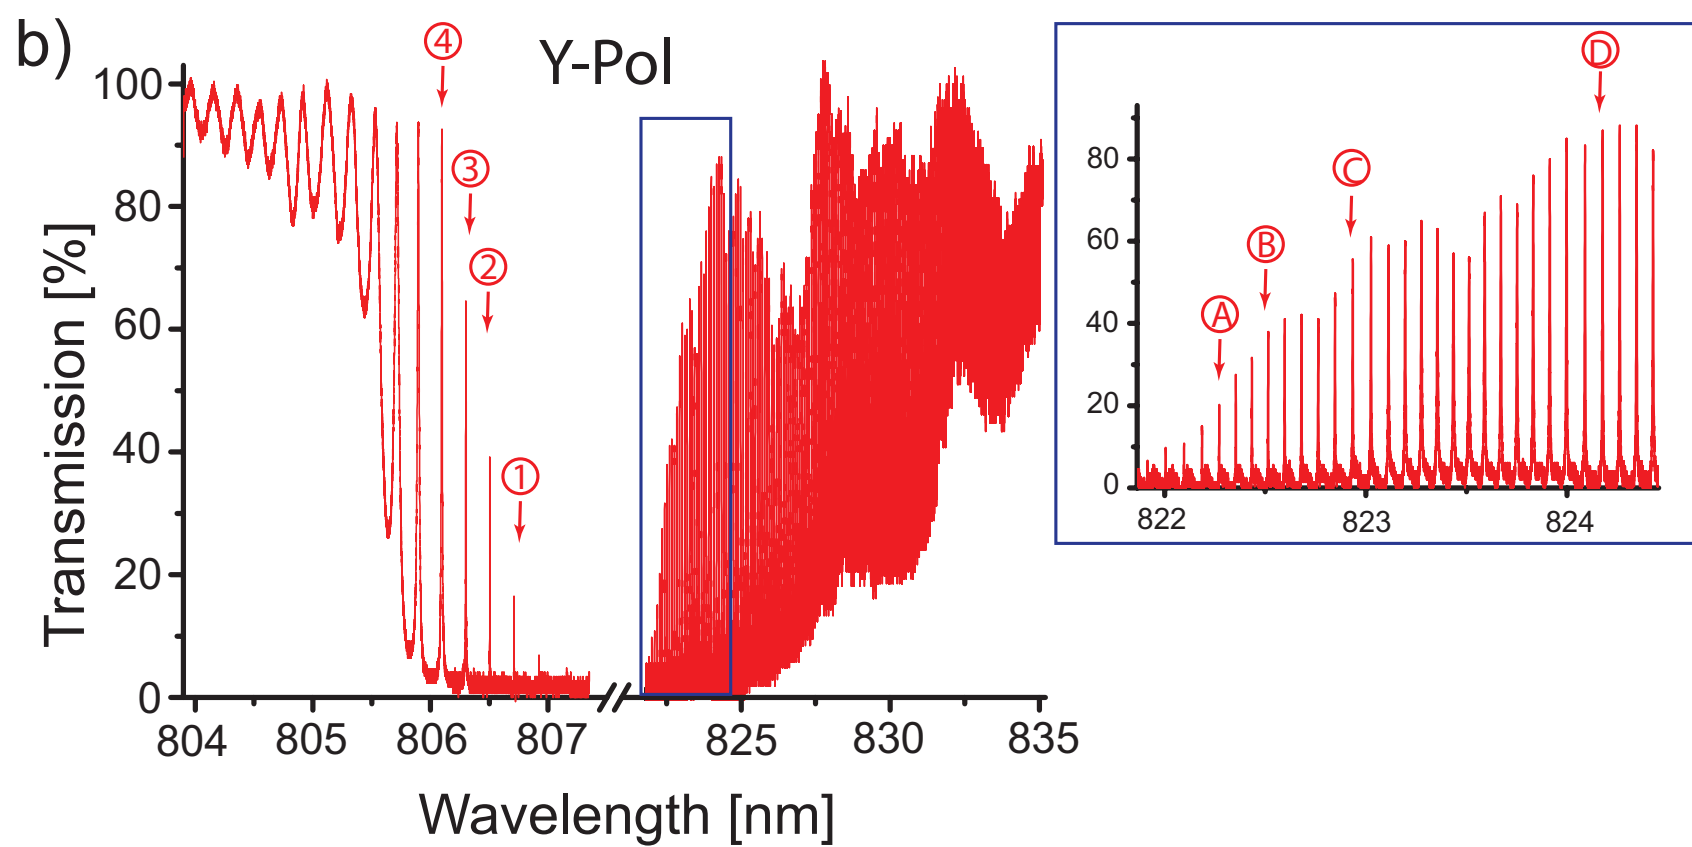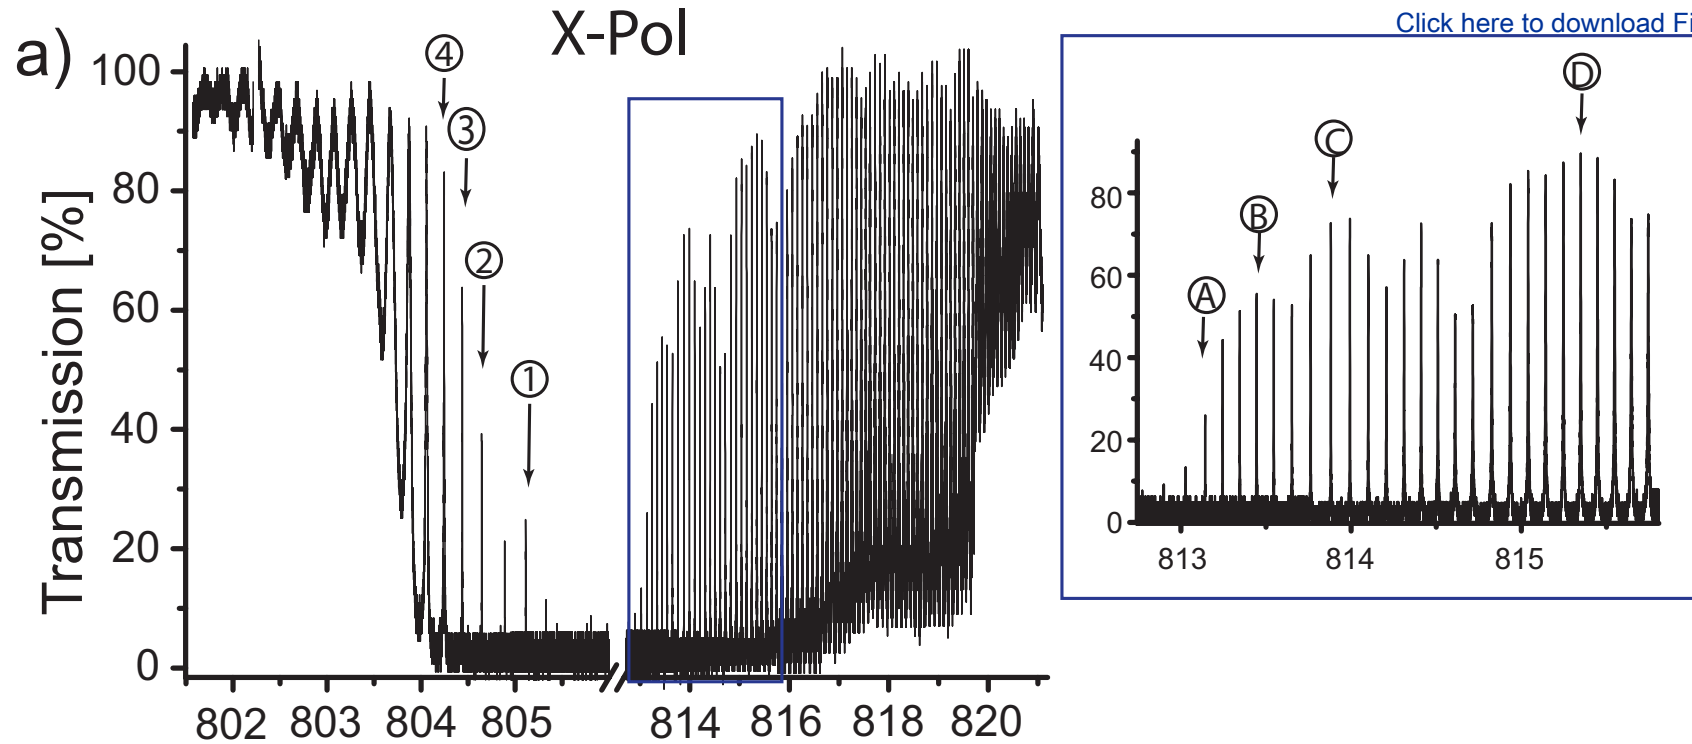

1 Alewife Center #200  
Cambridge, MA 02140  
tel. 617.945.9051  
www.jove.com

## ARTICLE AND VIDEO LICENSE AGREEMENT

Title of Article:

Fabrication of 1D Photonic Crystal Cavity on a Nanofiber Using Femtosecond Laser Induced Ablation

Author(s):

Kali Prasanna Nayak, Jameesh Keloth, and Kohzo Hakuta

Item 1 (check one box): The Author elects to have the Materials be made available (as described at <http://www.jove.com/publish>) via: ☒ Standard Access ☐ Open Access

Item 2 (check one box):

- ☒ The Author is NOT a United States government employee.
- ☐ The Author is a United States government employee and the Materials were prepared in the course of his or her duties as a United States government employee.
- ☐ The Author is a United States government employee but the Materials were NOT prepared in the course of his or her duties as a United States government employee.

### ARTICLE AND VIDEO LICENSE AGREEMENT

1. **Defined Terms.** As used in this Article and Video License Agreement, the following terms shall have the following meanings: "**Agreement**" means this Article and Video License Agreement; "**Article**" means the article specified on the last page of this Agreement, including any associated materials such as texts, figures, tables, artwork, abstracts, or summaries contained therein; "**Author**" means the author who is a signatory to this Agreement; "**Collective Work**" means a work, such as a periodical issue, anthology or encyclopedia, in which the Materials in their entirety in unmodified form, along with a number of other contributions, constituting separate and independent works in themselves, are assembled into a collective whole; "**CRC License**" means the Creative Commons Attribution-Non Commercial-No Derivs 3.0 Unported Agreement, the terms and conditions of which can be found at: <http://creativecommons.org/licenses/by-nc-nd/3.0/legalcode>; "**Derivative Work**" means a work based upon the Materials or upon the Materials and other pre-existing works, such as a translation, musical arrangement, dramatization, fictionalization, motion picture version, sound recording, art reproduction, abridgment, condensation, or any other form in which the Materials may be recast, transformed, or adapted; "**Institution**" means the institution, listed on the last page of this Agreement, by which the Author was employed at the time of the creation of the Materials; "**JoVE**" means MyJoVE Corporation, a Massachusetts corporation and the publisher of *The Journal of Visualized Experiments*; "**Materials**" means the Article and / or the Video; "**Parties**" means the Author and JoVE; "**Video**" means any video(s) made by the Author, alone or in conjunction with any other parties, or by JoVE or its affiliates or agents, individually or in collaboration with the Author or any other parties, incorporating all or any portion of the Article, and in which the Author may or may not appear.

2. **Background.** The Author, who is the author of the Article, in order to ensure the dissemination and protection of the Article, desires to have the JoVE publish the Article and create and transmit videos based on the Article. In furtherance of such goals, the Parties desire to memorialize in this Agreement the respective rights of each Party in and to the Article and the Video.

3. **Grant of Rights in Article.** In consideration of JoVE agreeing to publish the Article, the Author hereby grants to JoVE, subject to **Sections 4 and 7** below, the exclusive, royalty-free, perpetual (for the full term of copyright in the Article, including any extensions thereto) license (a) to publish, reproduce, distribute, display and store the Article in all forms, formats and media whether now known or hereafter developed (including without limitation in print, digital and electronic form) throughout the world, (b) to translate the Article into other languages, create adaptations, summaries or extracts of the Article or other Derivative Works (including, without limitation, the Video) or Collective Works based on all or any portion of the Article and exercise all of the rights set forth in (a) above in such translations, adaptations, summaries, extracts, Derivative Works or Collective Works and (c) to license others to do any or all of the above. The foregoing rights may be exercised in all media and formats, whether now known or hereafter devised, and include the right to make such modifications as are technically necessary to exercise the rights in other media and formats. If the "Open Access" box has been checked in **Item 1** above, JoVE and the Author hereby grant to the public all such rights in the Article as provided in, but subject to all limitations and requirements set forth in, the CRC License.



## ARTICLE AND VIDEO LICENSE AGREEMENT

**4. Retention of Rights in Article.** Notwithstanding the exclusive license granted to JoVE in **Section 3** above, the Author shall, with respect to the Article, retain the non-exclusive right to use all or part of the Article for the non-commercial purpose of giving lectures, presentations or teaching classes, and to post a copy of the Article on the Institution's website or the Author's personal website, in each case provided that a link to the Article on the JoVE website is provided and notice of JoVE's copyright in the Article is included. All non-copyright intellectual property rights in and to the Article, such as patent rights, shall remain with the Author.

**5. Grant of Rights in Video – Standard Access.** This **Section 5** applies if the "Standard Access" box has been checked in **Item 1** above or if no box has been checked in **Item 1** above. In consideration of JoVE agreeing to produce, display or otherwise assist with the Video, the Author hereby acknowledges and agrees that, Subject to **Section 7** below, JoVE is and shall be the sole and exclusive owner of all rights of any nature, including, without limitation, all copyrights, in and to the Video. To the extent that, by law, the Author is deemed, now or at any time in the future, to have any rights of any nature in or to the Video, the Author hereby disclaims all such rights and transfers all such rights to JoVE.

**6. Grant of Rights in Video – Open Access.** This **Section 6** applies only if the "Open Access" box has been checked in **Item 1** above. In consideration of JoVE agreeing to produce, display or otherwise assist with the Video, the Author hereby grants to JoVE, subject to **Section 7** below, the exclusive, royalty-free, perpetual (for the full term of copyright in the Article, including any extensions thereto) license (a) to publish, reproduce, distribute, display and store the Video in all forms, formats and media whether now known or hereafter developed (including without limitation in print, digital and electronic form) throughout the world, (b) to translate the Video into other languages, create adaptations, summaries or extracts of the Video or other Derivative Works or Collective Works based on all or any portion of the Video and exercise all of the rights set forth in (a) above in such translations, adaptations, summaries, extracts, Derivative Works or Collective Works and (c) to license others to do any or all of the above. The foregoing rights may be exercised in all media and formats, whether now known or hereafter devised, and include the right to make such modifications as are technically necessary to exercise the rights in other media and formats. For any Video to which this **Section 6** is applicable, JoVE and the Author hereby grant to the public all such rights in the Video as provided in, but subject to all limitations and requirements set forth in, the CRC License.

**7. Government Employees.** If the Author is a United States government employee and the Article was prepared in the course of his or her duties as a United States government employee, as indicated in **Item 2** above, and any of the licenses or grants granted by the Author hereunder exceed the scope of the 17 U.S.C. 403, then the rights granted hereunder shall be limited to the maximum rights permitted under such

statute. In such case, all provisions contained herein that are not in conflict with such statute shall remain in full force and effect, and all provisions contained herein that do so conflict shall be deemed to be amended so as to provide to JoVE the maximum rights permissible within such statute.

**8. Likeness, Privacy, Personality.** The Author hereby grants JoVE the right to use the Author's name, voice, likeness, picture, photograph, image, biography and performance in any way, commercial or otherwise, in connection with the Materials and the sale, promotion and distribution thereof. The Author hereby waives any and all rights he or she may have, relating to his or her appearance in the Video or otherwise relating to the Materials, under all applicable privacy, likeness, personality or similar laws.

**9. Author Warranties.** The Author represents and warrants that the Article is original, that it has not been published, that the copyright interest is owned by the Author (or, if more than one author is listed at the beginning of this Agreement, by such authors collectively) and has not been assigned, licensed, or otherwise transferred to any other party. The Author represents and warrants that the author(s) listed at the top of this Agreement are the only authors of the Materials. If more than one author is listed at the top of this Agreement and if any such author has not entered into a separate Article and Video License Agreement with JoVE relating to the Materials, the Author represents and warrants that the Author has been authorized by each of the other such authors to execute this Agreement on his or her behalf and to bind him or her with respect to the terms of this Agreement as if each of them had been a party hereto as an Author. The Author warrants that the use, reproduction, distribution, public or private performance or display, and/or modification of all or any portion of the Materials does not and will not violate, infringe and/or misappropriate the patent, trademark, intellectual property or other rights of any third party. The Author represents and warrants that it has and will continue to comply with all government, institutional and other regulations, including, without limitation all institutional, laboratory, hospital, ethical, human and animal treatment, privacy, and all other rules, regulations, laws, procedures or guidelines, applicable to the Materials, and that all research involving human and animal subjects has been approved by the Author's relevant institutional review board.

**10. JoVE Discretion.** If the Author requests the assistance of JoVE in producing the Video in the Author's facility, the Author shall ensure that the presence of JoVE employees, agents or independent contractors is in accordance with the relevant regulations of the Author's institution. If more than one author is listed at the beginning of this Agreement, JoVE may, in its sole discretion, elect not take any action with respect to the Article until such time as it has received complete, executed Article and Video License Agreements from each such author. JoVE reserves the right, in its absolute and sole discretion and without giving any reason therefore, to accept or decline any work submitted to JoVE. JoVE and its employees, agents and independent contractors shall have



## ARTICLE AND VIDEO LICENSE AGREEMENT

full, unfettered access to the facilities of the Author or of the Author's institution as necessary to make the Video, whether actually published or not. JoVE has sole discretion as to the method of making and publishing the Materials, including, without limitation, to all decisions regarding editing, lighting, filming, timing of publication, if any, length, quality, content and the like.

11. **Indemnification.** The Author agrees to indemnify JoVE and/or its successors and assigns from and against any and all claims, costs, and expenses, including attorney's fees, arising out of any breach of any warranty or other representations contained herein. The Author further agrees to indemnify and hold harmless JoVE from and against any and all claims, costs, and expenses, including attorney's fees, resulting from the breach by the Author of any representation or warranty contained herein or from allegations or instances of violation of intellectual property rights, damage to the Author's or the Author's institution's facilities, fraud, libel, defamation, research, equipment, experiments, property damage, personal injury, violations of institutional, laboratory, hospital, ethical, human and animal treatment, privacy or other rules, regulations, laws, procedures or guidelines, liabilities and other losses or damages related in any way to the submission of work to JoVE, making of videos by JoVE, or publication in JoVE or elsewhere by JoVE. The Author shall be responsible for, and shall hold JoVE harmless from, damages caused by lack of sterilization, lack of cleanliness or by contamination due to the making of a video by JoVE its employees, agents or independent contractors. All sterilization, cleanliness or decontamination procedures shall be solely the responsibility of the Author and shall be undertaken at the Author's


expense. All indemnifications provided herein shall include JoVE's attorney's fees and costs related to said losses or damages. Such indemnification and holding harmless shall include such losses or damages incurred by, or in connection with, acts or omissions of JoVE, its employees, agents or independent contractors.

12. **Fees.** To cover the cost incurred for publication, JoVE must receive payment before production and publication the Materials. Payment is due in 21 days of invoice. Should the Materials not be published due to an editorial or production decision, these funds will be returned to the Author. Withdrawal by the Author of any submitted Materials after final peer review approval will result in a US\$1,200 fee to cover pre-production expenses incurred by JoVE. If payment is not received by the completion of filming, production and publication of the Materials will be suspended until payment is received.

13. **Transfer, Governing Law.** This Agreement may be assigned by JoVE and shall inure to the benefits of any of JoVE's successors and assignees. This Agreement shall be governed and construed by the internal laws of the Commonwealth of Massachusetts without giving effect to any conflict of law provision thereunder. This Agreement may be executed in counterparts, each of which shall be deemed an original, but all of which together shall be deemed to be one and the same agreement. A signed copy of this Agreement delivered by facsimile, e-mail or other means of electronic transmission shall be deemed to have the same legal effect as delivery of an original signed copy of this Agreement.

A signed copy of this document must be sent with all new submissions. Only one Agreement required per submission.

### CORRESPONDING AUTHOR:

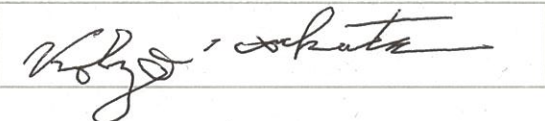Name:	Kohzo Hakuta	
Department:	Center for Photonic Innovations	
Institution:	UEC Tokyo, The University of Electro-Communications	
Article Title:	Fabrication of 1D Photonic Crystal Cavity on a Nanofiber Using Femtosecond Laser Induced Ablation	
Signature:		Date: June 16, 2016

Please submit a signed and dated copy of this license by one of the following three methods:

- 1) Upload a scanned copy of the document as a pdf on the JoVE submission site;
- 2) Fax the document to +1.866.381.2236;
- 3) Mail the document to JoVE / Attn: JoVE Editorial / 1 Alewife Center #200 / Cambridge, MA 02139

For questions, please email [submissions@jove.com](mailto:submissions@jove.com) or call +1.617.945.9051

Dear Editor,

We would like to thank the reviewers and the editors for the constructive comments and suggestions. The followings are our response to the comments and the corresponding changes to the manuscript.

**Editorial comments:**

- Your manuscript has been modified by your editor, please maintain the current formatting throughout the manuscript. **Please use the updated manuscript located in your Editorial Manager account (under “File Inventory”) for all subsequent revisions.** Updated manuscript is also attached.

- Please take this opportunity to thoroughly proofread your manuscript to ensure that there are no spelling or grammatical errors. Your JoVE editor will not copy-edit your manuscript and any errors in your submitted revision may be present in the published version.

- JoVE reference format requires that DOIs are included, when available, for all references listed in the article. This is helpful for readers to locate the included references and obtain more information. Please note that often DOIs are not listed with PubMed abstracts and as such, may not be properly included when citing directly from PubMed. In these cases, please manually include DOIs in reference information.

- Please proofread for minor grammatical errors. These include, but are not limited to:
  - Line 56: “Modern nanofabrication technology have enabled fabrication” has enabled

“Modern nanofabrication **technologies** have enabled fabrication of 1D and 2D photonic crystal (PhC) cavities for new prospects in lasing <sup>1</sup>, sensing <sup>2</sup> and optical switching applications <sup>3</sup>.”

- Line 123: “all lasers including (the) femtosecond laser. Wear (a) clean room suit and gloves”

“Wear safety glasses and strictly avoid direct exposure to UV lamp and all lasers including **the** femtosecond laser. Wear clean room **suits** and gloves to avoid contamination. Dispose any fiber trash properly in the designated trash box.”

- Line 376: “...is well preferred than the point-by-point fabrication.” ... is preferable to the...

“Therefore, the protocol presented here for a single-shot optical fabrication on nanofiber is **preferable to** the point-by-point fabrication.”

- Line 425: “...adapted to other nanofabrication process.” Processes

“Such fabrication technique may be implemented to make various nanophotonic devices from micro/nanofibers and may be adapted to other nanofabrication **processes**.”

- Visualization:

- Please un-highlight any notes which are not in the imperative tense and therefore do not have associated filmable actions, e.g. line 159, line 164. Alternatively, change these to steps, which include an imperative.

The “Notes” are un-highlighted.

- If possible, please provide photographs of the equipment setup. This can be included as supplemental material.

Two photographs are included in the supplemental material.

-----

- Detail: 1.1 “Mechanically strip the polymer jacket...” how is this done, with what tool?

“1.1) **Use the fiber coating stripper** to strip the polymer jacket of the single mode optical fiber for a length of 5 mm at two places separated by 200 mm.”

The details of the “fiber coating stripper” is added to the “Materials List”.

- Results: Figure 3: Please define what the brown and black arrows refer to.

The arrows were used to show the corresponding axes. However, it is not essential to complete the figure. So we preferred to remove them.

## **Reviewers' comments:**

### **Reviewer #1:**

#### *Manuscript Summary:*

This manuscript details the technical procedure used and described by the authors in previous publications to produce 1D photonic crystals on an optical nanofiber using femtosecond laser induced ablation.

In the introduction, an overview of the applications and the possible impact is given. Other techniques are commented along with the main advantages of the present technique and the goal of dissemination is clearly stated.

In the protocol section, the full protocol is given, including a detailed alignment procedure and the characterization method. Representative results are then presented and in a final section, the important parameters and the advantages of the technique are discussed.

The content very well fits JoVE's objectives. The results obtained are of important interest for the community working in the field of nanoscale waveguides and their applications. The detailed description given should allow independent researchers to reproduce the experiment, ensuring an efficient dissemination of the developed technique. I thus recommend the publication of this manuscript, although there is a small quantity of information which was not already given in the previous publication.

*Major Concerns:*  
N/A

*Minor Concerns:*

I have however a few comments which may improve the final version:

-Line 69: References 7-12 are publications involving authors of the present manuscript. Since a growing community have worked on these topics recently, it would be appropriate to refer to a few published work from other teams. For example, Phys. Rev. Lett. 115, 093603 seems particularly appropriate here.

The reference is included in the following sentence.

“The light-matter interaction on nanofiber can be significantly improved by implementing PhC cavity structure on the nanofiber<sup>16, 17</sup>.”

“17. Kato, S., Aoki, T. Strong coupling between a trapped single atom and an all-fiber cavity, *Phys. Rev. Lett.* **115**, 093603, doi: 10.1103/PhysRevLett.115.093603 (2015).”

-Line 106: "The beam size across the nanofiber is 60μm."

At this stage of reading, this sentence was not clear (dimension of the beam along which axis?).

The sentence is modified to properly define the dimensions of the beam along both axes.

“The beam size across (Y-axis) and along (Z-axis) the nanofiber is 60 μm and 5.6 mm, respectively.”

“Although the femtosecond laser beam size along the nanofiber is 5.6 mm the interference region is less than 1 mm along the X-axis limited by the spatial overlap of the pulses.”

-Line 111: How is the "dust free" conditions obtained?

One sentence is added to explain the dust free conditions.

“All the experiments are performed inside a clean booth equipped with HEPA (High-efficiency particulate arresting) filters to achieve dust-free conditions. Dust-free condition is essential to maintain the transmission of the nanofiber.”

-It could be nice to add a sentence giving the outline of the manuscript at the end of the introduction (first the protocol - divided in three parts, then results followed by discussion).

The following paragraph is added at the end of the introduction.

“The paper proceeds in the following way. First we present the protocol for the fabrication and characterization. The protocol section is divided in three subsections, nanofiber preparation, femtosecond laser fabrication and characterization of the fabricated samples. The protocol section is then followed by the representative results and discussions.”

-Nanofiber preparation: It is not clear whether the nanofiber fabrication bench can be simply bought. If yes, this could be stated here, since reproducing the present ablation technique will be much easier without having to develop a new nanofiber fabrication bench. (References already given in the introduction, describe how to develop such a bench although it is not stated explicitly in this manuscript.)

The “Note” following the Step 1.2.1 is modified as follows

“Note: The **ONME is a commercially available device**, designed to fabricate tapered optical fibers using standard heat and pull technique. It uses oxyhydrogen flame to heat the fiber and two motorized stages to pull the fiber. The gas flow and the stage movements are controlled by computer program. **The pre-optimized parameters may be obtained from the vendor, upon special request.**”

-Line 177: What is the typical power needed in the probe pulse to observe the scattering?

Typically we send 1 mW probe power through the nanofiber to observe the scattering. The sentence is modified as follows

“2.2.2) Send a probe laser (**power=1 mW**) through the tapered fiber and observe the scattering from the tapered fiber on the CCD camera. The strongest scattering part corresponds to the nanofiber region due to its subwavelength diameter.”

-Line 200: What is the role of theta? It is not clear at this stage of reading.



Theta is the angle between the line focused femtosecond laser and the nanofiber axis. The following sentences are added in the introduction to explain the theta and the tilt angles.

“The  $\theta$ -stage allows rotation of the nanofiber sample in the YZ-plane. The X-stage can also control the tilt angles along XY- and XZ-plane.”

-Line 230: Is there a simple physical explanation for this polarization dependent shift? Is there any study of the birefringence properties of the samples?

The Bragg resonance ( $\lambda_R = 2n_{\text{eff}}\Lambda_G$ ) depends on the effective index ( $n_{\text{eff}}$ ). The formation of nano-craters along one axis breaks the cylindrical symmetry of the fiber. The effective index along the axis containing the nano-craters will be smaller than the other orthogonal axis, resulting in a polarization dependent shift in the Bragg resonance.

Such topics are already discussed in Ref. [21]. In this manuscript we hope to emphasize on the fabrication techniques. So we avoided similar discussions as Ref. [21]. For clarity we indicated to refer the Ref. [21] in the “Note”.

“Note: For the X-pol (polarization along the nano-craters) the stopband will be blue-shifted<sup>21</sup> (towards the shorter wavelength) and the scattering from the nanofiber will be stronger. So select the polarizations by looking at the spectrum and the CCD camera.”

We have not made a detailed investigation on the birefringence properties of the samples. For our present research we are not interested in such investigations yet. But it would be interesting to study the birefringence properties for some other applications.

-Line 269: I am curious to know if the coater actually deposits a uniform 10nm layer on such a sample and what is the confidence we can have here. This is more a question for SEM specialists though.

The purpose of the coating here is to avoid charging up effect in the SEM. So the uniformity of the coating matters in the sense that it should be less than the features we want to resolve. As seen in Fig. 2 (the inset, in particular), the surface looks rather smooth and uniform at least in the scale we want to resolve the size of the nano-craters. However, at higher resolutions we do see patches of Pt-layer, with a roughness of around 2 nm.

The following sentences are modified to avoid confusions.

“3.2.1) Use the Pt-coater to coat the sample for 30 s and deposit a layer of Pt with a thickness of around 10 nm. Put the sample into the SEM. Take the SEM image of the sample at every 0.1 mm over the entire fabricated region.”

-Language: Sometimes an article is missing, or I would have chosen a different word. Note that I am not a native english speaker though. A few examples here:  
Line 77-79: I would remove the comma after "Although" and replace "such" by "as". Line 97: I would add "a" after such. Line 172: "a" after until.  
Typo line 195: "refLection". Line 233-234 replace "by" by "while".

Thanks for indicating the typos. The following sentences are modified.

“Although cavity fabrication on nanofiber using focused ion beam (FIB) milling has been demonstrated <sup>19, 20</sup>, the optical quality and reproducibility is not **as** high.”

“This video protocol is intended to help others implement and adapt such **a** new type of nanofabrication technique.”

“Else repeat the procedure (from Step 2.1.1 to 2.1.4) for lower pulse energies (down to 300  $\mu$ J) until **a** periodic ablation pattern is seen.”

“When they are parallel, the **ref**lection spots will appear as a flash.”

Line 233-234 the “by” is appropriate here. In this step (Step 3.1.3) the spectra are taken after stretching the tapered fiber. In the Step 3.1.5 the spectrum is measured while stretching the tapered fiber.

#### *Additional Comments to Authors:*

N/A

#### **Reviewer #2:**

##### *Manuscript Summary:*

This manuscript give a protocol for fabricating 1D photonic crystal cavities on tapered optical fibers by femtosecond laser induced ablation. In this protocol, the authors give a detailed describe about the fabrication processing from nanofiber preparation and femtosecond laser fabrication to the fabricated samples characterization.

##### *Major Concerns:*

1. In the nanofiber preparation part line 137, could the authors give a detailed directions about the "pre-optimized parameter", such as translation speed and gas flow.

Such descriptions are outside the scope of this manuscript. Although it is well established and adapted in many research groups and even commercially available now a days. If we wish to include such descriptions it will be sufficient for a separate manuscript.

The “Note” following the Step 1.2.1 is modified as follows,

“Note: The **ONME is a commercially available device**, designed to fabricate tapered optical fibers using standard heat and pull technique. It uses oxyhydrogen flame to heat the fiber and two motorized stages to pull the fiber. The gas flow and the stage movements are controlled by computer program. **The pre-optimized parameters may be obtained from the vendor, upon special request.**”

2. Just as the authors' discuss, the alignment of the fabrication setup is a very crucial step. At the same time, the CCD camera has a critical role in the alignment processing. So could the authors give a detailed explanation where the CCD camera was placed.

The following sentence is revised to explain the CCD camera position.

“A CCD camera is placed **at a distance of 20 cm from the nanofiber and at an angle of 45° in the XY-plane** to monitor the nanofiber position.”

3. If the results can be compared to other resonance devices, such as a plasmonic cavity (APL 101 (2012) 153118) , the research may attract wide audience.

The following sentences are added to the introduction.

“**Apart from PhC cavities, plasmonic nanocavities have also shown promising prospects<sup>5, 6, 7</sup>. However, interfacing such cavities to fiber-based communication network still remains a challenge.**”

The following references are added.

5. Akimov, A. V. *et al.* Generation of single optical plasmons in metallic nanowires coupled to quantum dots, *Nature* **450**, 402-406, doi:10.1038/nature06230 (2007).
6. Noginov, M. A. *et al.* Demonstration of a spaser-based nanolaser, *Nature* **460**, 1110-1112, doi:10.1038/nature08318 (2009).
7. Zhang, X. Y., Zhang, T., Hu, A., Song, Y. J., Duley, W. W. Controllable plasmonic antennas with ultra narrow bandwidth based on silver nano-flags, *Appl. Phys. Lett.* **101**, 153118, doi: 10.1063/1.4759122 (2012).

#### *Minor Concerns:*

1. The legend should be added in Figure 3(a) for better understanding. Beside, from line 280 to line 287, in the text part, the authors also did not mention the different of fabrication angle and laser power for these plots. And why the diameter of nanofiber has a variation under different of fabrication angle and laser power? For Figure 3(b), authors



used a copper wire to prepare the defect-induced PhC cavity. The blue has show the middle of nano-fiber did not ablated by laser, so in the schematic diagram, the middle part should not have the black points( laser ablation).

The legend is added to Figure 3(a).

The following sentences are added to the text describing the Figure 3(a).

“The circles denote the nano-crater diameter and the squares are the corresponding nanofiber diameter. The lines are the Gaussian fits to the profiles. The data shown in black and green correspond to samples fabricated with  $\theta = 0$  deg, using pulse energy of 0.35 and 0.17 mJ, respectively. The data shown in red and blue correspond to samples fabricated with  $\theta = 0.5$  deg, using pulse energy of 0.35 and 0.27 mJ, respectively.”

The diameter of the nanofiber does not depend on the fabrication angle and laser power. We have used different nanofiber diameters for fabrication. We do not observe any significant difference in fabrication condition and optical characteristics over the diameter range of 450 nm to 550 nm.

The black dashed line indicated the nanofiber axis. To avoid confusions we removed the black dashed line.

2. Figure 4(b), there is a small peak between 2 and 3. As for the issue, authors have discussed this may caused by the side-lobe-like structure in the ref 18. Could the authors use the sample fabricated with  $\theta = 0$  deg to re-measure the transmission spectrum to clarify this reason?

The additional peak (mode) between 2 and 3 might be due to the side-lobe-like structure. Such overlap occurs occasionally. For most of the fabrication ( $\theta = 0$  deg or 0.5 deg) we have not seen such mode. For example for the X-pol in Figure 4(a) we don't see such modes, at least within the range of modes we are interested in.

*Additional Comments to Authors:*

N/A

---

Attachments area

The following is the list of changes. The modified texts are marked in red.

1- The first paragraph of the Introduction section is modified as follows

“Strong confinement of light in nanophotonic devices has opened new frontiers in optical science. Modern nanofabrication **technologies** have enabled fabrication of 1D and 2D photonic crystal (PhC) cavities for new prospects in lasing <sup>1</sup>, sensing <sup>2</sup> and optical switching applications <sup>3</sup>. Moreover, strong light-matter interaction in these PhC cavities has opened new avenues for quantum information science <sup>4</sup>. **Apart from PhC cavities, plasmonic nanocavities have also shown promising prospects <sup>5, 6, 7</sup>. However, interfacing such cavities to fiber-based communication network still remains a challenge.**”

2- The following references are added in the 1<sup>st</sup> paragraph of the Introduction

5. Akimov, A. V. et al. Generation of single optical plasmons in metallic nanowires coupled to quantum dots, Nature 450, 402-406, doi:10.1038/nature06230 (2007).

6. Noginov, M. A. et al. Demonstration of a spaser-based nanolaser, Nature 460, 1110-1112, doi:10.1038/nature08318 (2009).

7. Zhang, X. Y., Zhang, T., Hu, A., Song, Y. J., Duley, W. W. Controllable plasmonic antennas with ultra narrow bandwidth based on silver nano-flags, Appl. Phys. Lett. 101, 153118, doi: 10.1063/1.4759122 (2012).

3- The following reference is added in the 2<sup>nd</sup> paragraph of the Introduction

17. Kato, S., Aoki, T. Strong coupling between a trapped single atom and an all-fiber cavity, Phys. Rev. Lett. 115, 093603, doi: 10.1103/PhysRevLett.115.093603 (2015).

4- The last sentence of the 3<sup>rd</sup> paragraph of the Introduction is modified as follows

“Although cavity fabrication on nanofiber using focused ion beam (FIB) milling has been demonstrated <sup>19, 20</sup>, the optical quality and reproducibility is not **as** high.”

5- The last sentence of the 5<sup>th</sup> paragraph of the Introduction is modified as follows

“This video protocol is intended to help others implement and adapt such **a** new type of nanofabrication technique.”

6- The 6<sup>th</sup> paragraph of the Introduction is modified as follows

“Figure 1a shows the schematic diagram of the fabrication setup. The details of the fabrication setup and alignment procedures are discussed in <sup>21, 22</sup>. A femtosecond laser with 400 nm center wavelength and 120 fs pulse width is incident on a phase mask. The phase mask splits the femtosecond laser beam into 0 and  $\pm 1$  orders. A beam block is used to block the 0-order beam. The folding mirrors symmetrically recombine the  $\pm 1$ -orders at the nanofiber position, to create an interference pattern. The pitch of the phase mask is 700 nm, so the interference pattern has a pitch ( $\Lambda_G$ ) of 350 nm. The cylindrical lens focuses the femtosecond laser beam along the nanofiber. The beam size across (Y-axis) and along (Z-axis) the nanofiber is 60  $\mu\text{m}$  and 5.6 mm, respectively. The tapered fiber is mounted on a holder equipped with piezo actuator (PZT) for stretching the fiber. A top cover with glass plate is used to protect the nanofiber from dust. The holder with the tapered fiber is fixed on a fabrication bench equipped with translation (XYZ) and rotation ( $\theta$ ) stages. The  $\theta$ -stage allows rotation of the nanofiber sample in the YZ-plane. The X-stage can also control the tilt angles along XY- and XZ-plane. A CCD camera is placed at a distance of 20 cm from the nanofiber and at an angle of 45° in the XY-plane to monitor the nanofiber position. All the experiments are performed inside a clean booth equipped with HEPA (High-efficiency particulate arresting) filters to achieve dust-free conditions. Dust-free condition is essential to maintain the transmission of the nanofiber.”

7- One paragraph is added to the end of the Introduction

“The paper proceeds in the following way. First we present the protocol for the fabrication and characterization. The protocol section is divided in three subsections, nanofiber preparation, femtosecond laser fabrication and characterization of the fabricated samples. The protocol section is then followed by the representative results and discussions.”

8- The first paragraph in the Protocol is modified as follows

“CAUTION: Wear safety glasses and strictly avoid direct exposure to UV lamp and all lasers including the femtosecond laser. Wear clean room suits and gloves to avoid contamination. Dispose any fiber trash properly in the designated trash box.”

9- The Step 1.1 in the Protocol is modified as follows

“1.1) Use the fiber coating stripper to strip the polymer jacket of the single mode optical fiber for a length of 5 mm at two places separated by 200 mm. Clean the two mechanically stripped parts using cleanroom wipe dipped in methanol. Dip the fiber between these two stripped parts in acetone. Wait for 10-15 min till the jacket of the fiber fall apart. Take out the fiber from acetone and clean the entire stripped part using cleanroom wipe dipped in methanol.”

10- The Note following the Step 1.2.1 is modified as follows

“Note: The **ONME is a commercially available device**, designed to fabricate tapered optical fibers using standard heat and pull technique. It uses oxyhydrogen flame to heat the fiber and two motorized stages to pull the fiber. The gas flow and the stage movements are controlled by computer program. **The pre-optimized parameters may be obtained from the vendor, upon special request.**”

11- All Notes in the Protocol section are un-highlighted.

12-The Step 2.1.5 is modified as follows

“2.1.5) Using the Platinum (Pt)-coater, coat the glass plate for 60 s to deposit a 25 nm layer of Pt on the glass plate. Image the ablation pattern on the glass plate using a scanning electron microscope (SEM). If the ablation pattern shows periodic structure with a period of 350 nm (the expected interference fringe pattern) then the alignment is optimized. Else repeat the procedure (from Step 2.1.1 to 2.1.4) for lower pulse energies (down to 300  $\mu$ J) until **a** periodic ablation pattern is seen.”

13-The Step 2.2.2 is modified as follows

“2.2.2) Send a probe laser (**power=1 mW**) through the tapered fiber and observe the scattering from the tapered fiber on the CCD camera. The strongest scattering part corresponds to the nanofiber region due to its subwavelength diameter.”

14-The Note following the Step 2.2.6 is modified as follows

“Note: If these spots move towards one side then nanofiber is not parallel to the ablation line. In this case, rotate the rotation stage to make the nanofiber parallel to the ablation line. When they are parallel, the **reflection** spots will appear as a flash.”

15-A reference is indicated in the Note following the Step 3.1.2

“Note: For the X-pol (polarization along the nano-craters) the stopband will be blue-shifted <sup>21</sup> (towards the shorter wavelength) and the scattering from the nanofiber will be stronger. So select the polarizations by looking at the spectrum and the CCD camera.”

16-The Step 3.2.2 is modified as follows

“3.2.2) Use the Pt-coater to coat the sample for 30 s and deposit **a layer of Pt with a thickness of around 10 nm. Put the sample into the SEM.** Take the SEM image of the sample at every 0.1 mm over the entire fabricated region.”

17-The 2<sup>nd</sup> paragraph in the Representative Results is modified as follows

“Figure 3a shows the fabrication results for the apodized PhC cavity. The typical profile of the nano-crater array along with the corresponding nanofiber diameter for different fabrication angle ( $\theta$ ) and pulse energy are shown. The circles denote the nano-crater diameter and the squares are the corresponding nanofiber diameter. The lines are the Gaussian fits to the profiles. The data shown in black and green correspond to samples fabricated with  $\theta = 0$  deg, using pulse energy of 0.35 and 0.17 mJ, respectively. The data shown in red and blue correspond to samples fabricated with  $\theta = 0.5$  deg, using pulse energy of 0.35 and 0.27 mJ, respectively. As one can see, the nano-craters are formed over a length of 2-3 mm along the nanofiber where the diameter of the nanofiber is uniform. An apodization in nano-crater diameter is observed corresponding to the Gaussian intensity distribution of the femtosecond laser beam. It is clearly seen that the diameter of the nano-craters are reduced for weaker pulse energy. Moreover, the width of the apodization profile of the nano-craters is reduced by increasing the angle of fabrication.”

18-The Figure 3 is modified. The brown and black arrows are removed. The legends are added. The black dashed line in the schematic diagram is removed.

19-One sentence is modified in the 2<sup>nd</sup> paragraph of the Discussion

“....Therefore, the protocol presented here for a single-shot optical fabrication on nanofiber is preferable to the point-by-point fabrication. However, point-by-point fabrication may be preferred for some applications where fabricating arbitrary pattern on the nanofiber is essential.”


20-One sentence is modified in the 3<sup>rd</sup> paragraph of the Discussion

“.....Although the femtosecond laser beam size along the nanofiber is 5.6 mm the interference region is less than 1 mm along the X-axis limited by the spatial overlap of the pulses. ....”

21-One sentence is modified in the last paragraph of the Discussion



“Such fabrication technique may be implemented to make various nanophotonic devices from micro/nanofibers and may be adapted to other nanofabrication processes.”


22-The Materials List is modified.

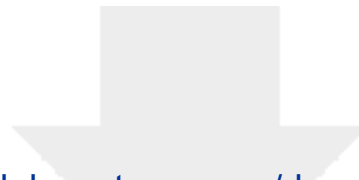

[Click here to access/download](#)

**Supplemental File (as requested by JoVE)**  
copyright permission\_OSA.pdf




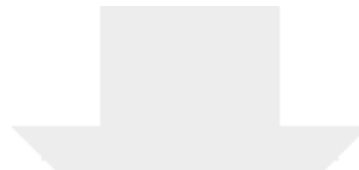

[Click here to access/download](#)

**Supplemental code file (if applicable)**  
**ONME setup.pdf**



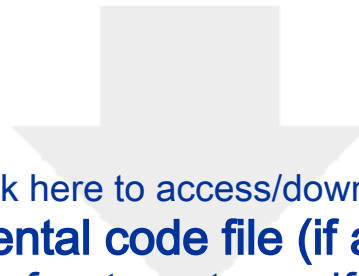

[Click here to access/download](#)

**Supplemental code file (if applicable)**  
**femto setup.pdf**

