

Journal of Visualized Experiments

Synthesis of a Thiol Building Block for the Crystallization of a Semiconducting Gyroidal Metal-Sulfur Framework --Manuscript Draft--

Article Type:	Invited Methods Article - JoVE Produced Video
Manuscript Number:	JoVE57455R1
Full Title:	Synthesis of a Thiol Building Block for the Crystallization of a Semiconducting Gyroidal Metal-Sulfur Framework
Keywords:	porous materials; semiconductors; metal-sulfur frameworks; thiol synthesis; crystal engineering; thioesters
Corresponding Author:	Zhengtao Xu City University of Hong Kong Kowloon Tong, Kowloon HONG KONG
Corresponding Author's Institution:	City University of Hong Kong
Corresponding Author E-Mail:	zhengtao@cityu.edu.hk
First Author:	Zhengtao Xu
Other Authors:	Yonghe He Jiahong Huang Jun He
Author Comments:	
Additional Information:	
Question	Response
If this article needs to be "in-press" by a certain date, please indicate the date below and explain in your cover letter.	

TITLE:

Synthesis of a Thiol Building Block for the Crystallization of a Semiconducting Gyroidal Metal-Sulfur Framework

AUTHORS AND AFFILIATIONS:

Yonghe He¹, Jiahong Huang¹, Jun He¹, Zhengtao Xu²

¹School of Chemical Engineering and Light Industry, Guangdong University of Technology, Guangzhou, China

²Department of Chemistry, City University of Hong Kong, Hong Kong, China

CORRESPONDING AUTHORS:

Zhengtao Xu (zhengtao@cityu.edu.hk)

Jun He (junhe@gdut.edu.cn)

KEYWORDS:

Thiol Synthesis, Porous Materials, Semiconductors, Metal-Organic Frameworks, Metal Dithiolene Compounds, Gyroid

SUMMARY:

Here, we present a one-pot, transition-metal-free synthesis of thiols and thioesters from aromatic halides and sodium thiomethoxide, followed by the preparation of single crystals of a metal-dithiolene network using thiol species generated *in situ* from the more stable and tractable thioester.

ABSTRACT:

We present a method for preparing thioester molecules as the masked form of the thiol linkers and their utilization for accessing a semiconducting and porous metal-dithiolene network in the highly ordered single crystalline state. Unlike the highly reactive free-standing thiols, which tend to decompose and complicate the crystallization of metal-thiolate open frameworks, the thioester reacts *in situ* to provide the thiol species, serving to mitigate the reaction between the mercaptan units and the metal centers, and to improve crystallization consequently. Specifically, the thioester was synthesized in a one-pot procedure: an aromatic bromide (hexabromotriphenylene) reacted with excess sodium thiomethoxide under vigorous conditions to first form the thioether intermediate product. The thioether was then demethylated by the excess thiomethoxide to provide the thiolate anion that was acylated to form the thioester product. The thioester was conveniently purified by standard column chromatography, and then used directly in the framework synthesis, wherein NaOH and ethylenediamine serve to revert *in situ* the thioester to the thiol linker for assembling the single-crystalline Pb(II)-dithiolene network. Compared with other methods for thiol synthesis (*e.g.*, by cleaving alkyl thioether using sodium metal and liquid ammonia), the thioester synthesis here uses simple conditions and economical reagents. Moreover, the thioester product is stable and can be conveniently handled and stored. More importantly, in contrast to the generic difficulty in accessing crystalline metal-thiolate open frameworks, we demonstrate that using the thioester for *in situ* formation of the

thiol linker greatly improves the crystallinity of the solid-state product. We intend to encourage broader research efforts on the technologically important metal-sulfur frameworks by disclosing the synthetic protocol for the thioester as well as the crystalline framework solid.

INTRODUCTION:

There is currently great interest in employing strong, polarizable metal-sulfur (*e.g.*, metal-thiolate) links for constructing open framework materials with enhanced electrocatalytic and conductive properties¹⁻¹⁰. In addition to promoting electronic interaction and transport in the extended state, the soft and covalent metal-sulfur links also impart better stability for applications in aqueous environments. Among the sulfur-equipped building blocks, symmetrical, multidentate polycyclic aromatic building blocks like 2,3,6,7,10,11-triphenylene hexathiol (HTT)^{9,11-14} not only supply highly polarizable π -electrons, but also offer distinct advantages with respect to framework design and synthesis. First, the rigid and symmetrical triphenylene core, in conjunction with the chelating dithiolene groups of HTT, serves to lock in metal ions in regular bonding motifs, simplifying the structural prediction of the prospective network^{7,15}. Together with the rigid and open geometry of the sulfur linker, framework structures with substantial porosity features can often be achieved in the solid state.

One major challenge in assembling thiol-equipped metal organic framework (MOF) materials is rooted in the synthesis of the organic linker molecules. In a classical protocol, the thiol group had to be derived from the phenol group using the Newman–Kwart rearrangement of the *O*-aryl thiocarbamate precursor¹⁶⁻¹⁸. This approach, however, involves elaborate preparative steps for the phenol precursor molecule as well as potential complications of a high-temperature solid phase transformation. Another way of making thiols utilizes reductive dealkylation of thioethers under the harsh conditions of, for example, sodium metal in liquid ammonia¹⁹⁻²², and is not compatible with the carboxyl and many other donor functions for network construction.

By comparison, the protocol presented here has multiple advantages: safety, convenience, cost-effectiveness, and compatibility with other functional groups (*e.g.*, carbonitrile and pyridinyl). By vigorously heating the generally inexpensive aromatic halide (*e.g.*, hexabromotriphenylene) and thiomethoxide anion, the thiolate anion was generated (via the methyl thioether intermediate product) and then acylated to give the stable and easy-to-handle thioester product—all in one pot.

We will also describe a procedure for utilizing the thioester molecules as the masked form of the thiol linkers for accessing a single-crystalline semiconducting and porous metal-dithiolene network. Unlike the highly reactive free-standing thiols, which tend to decompose and complicate the crystallization of metal-thiolate open frameworks, the thioester can be readily cleaved (*e.g.*, by NaOH or ethylenediamine) *in situ* to provide the thiol species, serving to mitigate the reaction between the mercaptan units and the metal centers, and to consequently improve the crystallization.

This protocol of preparing thiol/thioester has not been widely used by other groups for the emerging field of metal-sulfur frameworks, even though nucleophilic dealkylations of alkyl aryl

thioethers by thiolate anions have already been well documented by organic chemists²³⁻²⁶. By showcasing this efficient synthetic method for thioesters and their use for facilitating the crystallization of metal-sulfur networks, we wish to promote further efforts to bridge the intellectual and practical divide between synthetic organic chemistry and solid state chemistry, so as to help the speedy and healthy development of porous frameworks.

PROTOCOL:

Caution: Please consult all relevant material safety data sheets before use. Methyl disulfide and sodium thiomethoxide are strongly malodorous and should be handled in a fume hood. Sodium metal is highly reactive and requires special safety precautions against potential fire and explosion hazards. In addition to the use of a fume hood, personal protective equipment (safety glasses, gloves, lab coat, full length pants, and closed-toe shoes) should be properly employed. Portions of the following procedures involve standard, air-free handling techniques.

1. Preparation of Sodium Thiomethoxide (CH_3SNa)

1.1. Connect a 200-mL Schlenk flask to a vacuum gas manifold. Evacuate the flask and then backfill it with N_2 three times, such that the flask is filled with a slightly positive N_2 pressure.

Note: A similar method of preparing CH_3SNa was mentioned briefly in the literature, but no detailed procedures were provided^{27,28}.

1.2. Take out a block of metallic sodium from the kerosene oil reservoir. Use a paper towel to wipe off the residual oil on the surface, and use a knife to scrape off the oxide layer on the surface. Quickly cut 6.7 g of the metallic sodium (0.29 mol) into small pieces (*e.g.*, about soybean size) and immediately transfer the small pieces to the 200-mL Schlenk flask under a counter flow of N_2 . Seal the flask with a septum immediately.

Note: To reduce the exposure to air, one can cut out the sodium with some variation from the amount of 6.7 g, and adjust the amounts of THF and dimethyl disulfide according to the actual amount of sodium used.

1.3. Transfer 80 mL of an anhydrous, airless THF into the flask *via* cannula under N_2 protection from the Schlenk line. Withdraw 14.0 mL of dimethyl disulfide (0.158 moles; pre-purged with N_2) into a syringe and inject it into the flask dropwise under N_2 protection.

Caution: Dimethyl disulfide is malodorous and should be handled in a fume hood.

1.4. Replace the septum with a ground glass stopper. Stir the reaction mixture at room temperature for 24 h and then at 60 °C for 3 h.

Note: The reaction mixture became viscous while stirring at room temperature; when heated up to 60 °C, the mixture can be stirred more easily and thus speed up the reaction towards completion.

1.5. With the temperature maintained at about 60 °C, use a stream of N₂ (0.2 L/min) to blow off the majority of the THF solvent and the excess dimethyl disulfide, until a dry solid appears. Use a cold trap (*e.g.*, acetone/dry ice) to collect the THF and dimethyl disulfide in the outflow.

1.6. Evacuate the remaining solid mixture with an oil pump for about 2 h to remove the residual THF and dimethyl disulfide and then backfill it with N₂ to obtain a light-yellow solid (19.8 g, 97%). Store the solid product CH₃SNa in a nitrogen atmosphere in the dark.

Note: To protect the vacuum oil pump, a cold trap should be used during the pumping.

2. Preparation of 2,3,6,7,10,11-hexakis(pentanoylthio)triphenylene (HVaTT) as a protected thiol linker

2.1. Load 0.664 g of CH₃SNa (9.0 mmol) into a 50-mL Schlenk flask under a counter flow of N₂ (*i.e.*, connected as above to a vacuum gas manifold under N₂ protection).

Note: CH₃SNa is sensitive to air and easily absorbs water. To minimize exposure to air, one can quickly weigh out a specific amount and add it to the flask, and then adjust the quantity of the other reactant, 2,3,6,7,10,11-hexabromotriphenylene (HBT), accordingly.

Caution: Solid CH₃SNa has a strong smell and should be handled in a fume hood.

2.2. Add 0.216 g of HBT (0.30 mmol) to the flask under a counter flow of N₂, and seal the flask with a septum.

2.3. Transfer 10 mL of anhydrous and airless 1,3-dimethyl-2-imidazolidinone (DMEU) into the flask *via* cannula under N₂ protection from the Schlenk line.

2.4. Replace the septum with a regular glass stopper, and stir the reaction mixture and use a salt bath to heat it to 240 °C for 48 h under N₂.

2.5. TLC monitoring of the progress of the reaction: Under N₂, use a glass dropper to withdraw a small aliquot of the reaction mixture (about 0.1 mL) and immediately inject it into a neat liquid sample of valeroyl chloride (about 0.1 mL) in a plastic microcentrifuge vial, and then shake for 1 min; the mixture should immediately turn turbid with a grey-white color. Add 0.4 mL of deionized water and 0.1 mL of ethyl acetate, close the cap, and shake it for a few seconds.

Note: If the reaction has completed already, there will not be anything that appears between the layers of water and ethyl acetate. If not, a white insoluble substance will appear between the two layers.

2.6. Pipet out the upper portion and use it for spotting the TLC plates. Use 1:4 ethyl acetate/petroleum ether to develop the TLC plate. For a complete reaction, the target molecule shows up as a regular spot around $R_f = 0.4$ under a UV lamp.

2.7. Turn off the heating and take the reaction flask out of the salt bath to cool it to room temperature, and then use an ice bath to cool the flask down to 0 °C.

2.8. Inject 1.5 mL of valeroyl chloride (12.6 mmol) into the flask dropwise (over a period of about 2 min) with a syringe under N_2 . Keep stirring at 0 °C for 2 h. Note: adding valeroyl chloride slowly and at low temperature helps to reduce the generation of by-products.

2.9. Pour the mixture into 50 mL of ice water and extract using ethyl acetate (3×30 mL). Then wash the combined organic layer with water (6×60 mL), dry over anhydrous $MgSO_4$, and remove the volatiles by a rotary evaporator.

2.10. Isolate the oily crude product by column chromatography using 1:10 ethyl acetate/petroleum ether as the eluent, which affords a light-yellow oily product after rotary evaporation of the solvents. Use 1:4 ethyl acetate/petroleum ether to develop the TLC plate, $R_f = 0.4$. Further purify the oily product using the trituration step below.

2.11. Add 5 mL of methanol to the oily product, and sonicate for 2 min. Collect the resultant off-white solid using suction filtration (yield: 59%).

3. Preparation of Single Crystals of the HTT-Pb Framework Material

3.1. Mix 11.4 mg of $PbOAc \cdot 3H_2O$ (0.030 mmol) in 1.0 mL of ethylene diamine in a vial to make a clear solution.

3.2. Load 9.1 mg of $HVaTT$ (0.010 mmol), 2.0 mL of pre-degassed methanol solution of NaOH (70 mmol/L), and 1.0 mL of ethylene diamine into an empty 10-mL vial and sonicate for 5 min.

3.3. Add the $PbOAc$ solution to the sonicated $HVaTT$ mixture. Then bubble the reaction mixture with N_2 for 1 min, and put on the screw cap to seal the vial.

3.4. Heat the vial at 90 °C in an oven for 48 h, followed by natural cooling to room temperature, during which yellow-orange, octahedral single crystals suitable for single-crystal X-ray diffraction studies were formed (yield: 45%).

3.5. Suction filtration off the crystals and quickly wash with MeOH. Transfer the crystals with a glass dropper into a vial containing airless MeOH (5 mL) for storage at room temperature.

4. Interaction of Paraquat Diiodide with HTT-Pb Crystals

4.1. Use a glass Pasteur pipet to withdraw a few grains of the HTT-Pb single crystal from the MeOH stock and drop it onto a Petri dish (diameter 35 mm and depth 10 mm). Soak up the methanol liquid by tissue or filter paper (or let the MeOH dry up naturally), and then drop onto the crystals a few drops of an aqueous solution of paraquat diiodide (0.1%, w/w).

4.2. Observe the color change of the crystals by eye or under a microscope.

REPRESENTATIVE RESULTS:

The IR spectrum of the HVaTT molecule (collected by the KBr pellet method) features its strongest absorption at $1,700\text{ cm}^{-1}$, in accordance with the carbonyl stretching of the thioester functional group. The ^1H -NMR spectrum of HVaTT (400 MHz, CDCl_3) reveals a singlet at δ 8.47 from the aromatic hydrogens, together with 4 multiplets from the aliphatic protons: δ 8.47 (s, 6H, CHAr), 2.75-2.72 (t, $J = 7.4$, 12H, CH_2), 1.81-1.77 (m, 12H, CH_2), 1.50-1.45 (dd, $J = 7.4$, 12H, CH_2), 1.00-0.97 (t, $J = 7.3$, 18H, CH_3). The ^{13}C -NMR spectrum of HVaTT (100 MHz, CDCl_3) features a peak at δ 196.52 from the carbonyl, three peaks (δ 132.71, 132.35, 130.02) from the triphenylene part, and 4 peaks in correspondence with the aliphatic chains: δ 196.52, 132.71, 132.35, 130.02, 77.35, 77.04, 76.72, 43.56, 27.66, 22.27, and 13.83.

The IR spectrum of the HTT-Pb crystalline product (collected by the KBr pellet method) indicates the absence of carbonyl stretching (around $1,700\text{ cm}^{-1}$) and the aliphatic C-H ($2,800\text{-}3,000\text{ cm}^{-1}$) stretching as seen in the HVaTT reactant. The powder X-ray diffraction (PXRD) pattern of the crystalline HTT-Pb sample thus obtained is consistent with the single crystal structure reported²⁹, indicating the crystalline phase purity of the HTT-Pb product. The single crystals of HTT-Pb are also shown to be highly responsive to the paraquat diiodide in water. Namely, upon contact with a paraquat diiodide solution (*e.g.*, 0.1% w/w), the crystals turned black within one or two minutes, pointing to strong charge transfer interactions between the electron-rich HTT-Pb framework and the highly electron-deficient paraquat guest.

FIGURE AND TABLE LEGENDS:

Figure 1: Synthesis of the HVaTT molecule. Synthesis starts from the hexabromotriphenylene HBT and sodium thiomethoxide, which generates the HTT hexaanion that is consequently reacted with valeroyl chloride to form the thioester product, HVaTT.

Figure 2: The IR spectra of the thioester precursor molecule of HVaTT (a) and an as-made sample of HTT-Pb crystals. Reproduced from reference 29 with permission from The Royal Society of Chemistry.

Figure 3: ^1H -NMR spectrum of HVaTT. 400 MHz, using CDCl_3 as the solvent.

Figure 4: ^{13}C -NMR spectrum of HVaTT. 100 MHz, using CDCl_3 as the solvent.

Figure 5: X-ray diffraction patterns (Cu $\text{K}\alpha$, $\lambda = 1.5418\text{ \AA}$) of HTT-Pb: (a) calculated from the single-crystal structure; (b) freshly prepared bulk sample of crystals. Adapted from reference 29 with permission from The Royal Society of Chemistry.

Figure 6. Panel (a): an octahedral single crystal of HTT-Pb before and after treatment with a paraquat diiodide solution (PDI, 0.1% w/w). The edge of the octahedron is about 0.4 mm. Panel (b): an overview of the bulk sample of the PDI-treated HTT-Pb crystals.

DISCUSSION:

The reaction between the bromo group and the thiomethoxide anion apparently first produced the methyl thioether, which was then demethylated by the excess thiomethoxide to provide the thiolate anion product. To ensure complete conversion to the desired thiolate anion (especially for a polybromide substrate like HBT), the vigorous conditions of prolonged heating (*e.g.*, 240 °C over 48 h) with a large excess of sodium thiomethoxide (*e.g.*, over three times the moles of the bromo groups) are essential. Nitrogen protection is also needed for preventing the oxidation of the thiolate species of the reactants and products. The acylation step (*e.g.*, injecting valeryl chloride into the reaction mixture cooled by an ice bath) not only provides the thioester as a stable and easily isolatable product, but also offers convenience in monitoring the progress of the reaction. For example, a small aliquot of the reaction mixture can be withdrawn (under N₂ protection) and immediately injected into a valeryl chloride solution, which can then be used for TLC monitoring of the progress of the reaction.

Notice that the quality of the sodium thiomethoxide reagent (NaSMe) is also crucial for the making of the HVaTT molecule in the above procedure. Even though the commercial NaSMe reagent has repeatedly proven reliable, highly efficacious NaSMe samples can also be economically prepared in-house on a gram scale (as described in the protocol).

In the solvothermal reaction for preparing single crystals of the HTT-Pb network, which features an anionic framework of the formula [Pb₃OH_{0.5}(HTT)]^{1.5-}, it is crucial to use the ester form, *i.e.*, 2,3,6,7,10,11-hexakis(pentanoylthio)triphenylene (HVaTT), as a starting material. For example, if the free thiol of HTT and the Pb(OAc)₂ solution was directly mixed together, an amorphous powder was observed to precipitate immediately, with no distinct enhancement of crystallinity effected even with prolonged heating treatment of the reaction mixture. Under the reaction conditions, the HVaTT reactant underwent *in situ* hydrolysis to generate the HTT thiol species, and thus functioned as a masked version of the highly reactive thiol building block of HTT. As a result, HVaTT effectively serves to mitigate the network formation process, *i.e.*, slowing down the reaction between the sulfur units and the Pb²⁺ ions, and allowing for more ordered crystalline product to be accessed. The formation of large single crystals (yellow-orange octahedral, about 0.3 mm) of HTT-Pb is also brought about by its structural features. Namely, the individual Pb(II)-dithiolene units in HTT-Pb are integrated through a μ₃-oxo atom; thus, the labile Pb₃O hinge (as compared with the more intractable Pb-S bonds) as the weakest link in the 3D net offers more reversibility for achieving the highly ordered single crystalline state. Nevertheless, we expect that the crystallinity of other metal-thiolate nets in general should also benefit from the use of protected thiols (like the thioester HVaTT) for *in situ* supply of the thiol linker.

Besides the benefits of the safe and low-cost reagents (*e.g.*, compared with sodium metal in liquid ammonia), this protocol offers more compatibility with other functional groups crucial for

framework construction. For example, our ongoing exploration demonstrates that carbonitrile and pyridinyl groups are generally tolerant of the reaction conditions, and thioester-equipped carbonitrile and N-heterocycles can be efficiently prepared by a similar protocol. Under alkaline conditions, both the carbonitrile and thioester groups can be readily hydrolysed into carboxyl and thiol groups, respectively, thereby generating thiol-equipped carboxylic linkers that have been proven to be important for MOF construction^{10,30-34}. The thiol-equipped N-heterocycle molecules, on the other hand, can be directly used for coordinating with metal ions for network construction, a research area that also features a noted literature record as well as ongoing intense studies^{2,4}.

The compatibility with ester and carboxylate groups, however, remains problematic at times. For example, ester groups are generally turned into carboxylates under these vigorously nucleophilic conditions (*e.g.*, via dealkylation of the ester group). The carboxylate group, with its negative charge, tends to hinder the thiomethoxide anion in its attack on the methylthio ether; moreover, decarboxylation is often observed under the condition of prolonged heating used in the protocol. Research efforts to ameliorate this situation are therefore truly warranted.

ACKNOWLEDGMENTS:

This work was supported by the National Natural Science Foundation of China (21471037), Guangdong Natural Science Funds for Distinguished Young Scholars (15ZK0307), Science and Technology Planning Project of Guangdong Province (2017A050506051), and the Research Grants Council of HKSAR [GRF 11303414].

DISCLOSURES:

The authors have nothing to disclose.

REFERENCES:

- 1 Zhao, Y. *et al.* A paramagnetic lamellar polymer with a high semiconductivity. *Chem Commun.* **0** (11), 1020-1021, doi: 10.1039/b101422f (2001).
- 2 Su, W., Hong, M., Weng, J., Cao, R., Lu, S. A semiconducting lamella polymer [{Ag(C₅H₄NS)}]_n with a graphite-like array of silver(I) ions and its analogue with a layered structure. *Angew Chem Int Ed.* **39** (16), 2911-2914, doi: 10.1002/1521-3773 (2000).
- 3 Tang, X.-Y., Li, H.-X., Chen, J.-X., Ren, Z.-G., Lang, J.-P. Synthetic and structural chemistry of groups 11 and 12 metal complexes of the zwitterionic ammonium thiolate ligands. *Coord Chem Rev.* **252** (18-20), 2026-2049, doi: 10.1016/j.ccr.2007.11.001 (2008).
- 4 Takaishi, S. *et al.* Electroconductive porous coordination polymer Cu[Cu(pdt)₂] composed of donor and acceptor building units. *Inorg Chem.* **48** (19), 9048-9050, doi: 10.1021/ic802117q (2009).
- 5 Kobayashi, Y., Jacobs, B., Allendorf, M. D., Long, J. R. Conductivity, Doping, and Redox Chemistry of a Microporous Dithiolene-Based Metal-Organic Framework. *Chem Mater.* **22** (14), 4120-4122, doi: 10.1021/cm101238m (2010).
- 6 Low, K.-H., Roy, V. A. L., Chui, S. S.-Y., Chan, S. L.-F., Che, C.-M. Highly conducting two-dimensional copper(I) 4-hydroxythiophenolate network. *Chem Commun.* **46** (39), 7328-7330, doi: 10.1039/c0cc02348e (2010).

350 7 Kambe, T. *et al.* π -Conjugated Nickel Bis(dithiolene) Complex Nanosheet. *J Am Chem Soc.* **135**
351 (7), 2462-2465, dio: 10.1021/ja312380b (2013).

352 8 Mensforth, E. J., Hill, M. R., Batten, S. R. Coordination polymers of sulphur-donor ligands. *Inorg*
353 *Chim Acta.* **403** 9-24, dio: 10.1016/j.ica.2013.02.019 (2013).

354 9 Cui, J., Xu, Z. An electroactive porous network from covalent metal-dithiolene links. *Chem*
355 *Commun.* **50** (30), 3986-3988, dio: 10.1039/c4cc00408f (2014).

356 10 Sun, L., Miyakai, T., Seki, S., Dincă, M. Mn-2(2,5-disulfhydrylbenzene-1,4-dicarboxylate): A
357 Microporous Metal-Organic Framework with Infinite (-Mn-S-) ∞ Chains and High Intrinsic Charge
358 Mobility. *J Am Chem Soc.* **135** (22), 8185-8188, dio: 10.1021/ja4037516 (2013).

359 11 Dong, R. *et al.* Large-Area, Free-Standing, Two-Dimensional Supramolecular Polymer Single-
360 Layer Sheets for Highly Efficient Electrocatalytic Hydrogen Evolution. *Angew Chem Int Ed.* **54** (41),
361 12058-12063, dio: 10.1002/anie.201506048 (2015).

362 12 Clough, A. J., Yoo, J. W., Mecklenburg, M. H., Marinescu, S. C. Two-Dimensional Metal-Organic
363 Surfaces for Efficient Hydrogen Evolution from Water. *J Am Chem Soc.* **137** (1), 118-121,
364 dio: 10.1021/ja5116937 (2015).

365 13 Xu, Z., Li, K., Fettingner, J. C., Li, J., King, M. M. A Semiconductive Coordination Network Based
366 on 2,3,6,7,10,11-Hexakis(methylthio)triphenylene and BiCl₃. *Cryst Growth Des.* **5** (2), 423-425,
367 dio: 10.1021/cg049817k (2005).

368 14 Sheberla, D. *et al.* High Electrical Conductivity in Ni₃(2,3,6,7,10,11-hexaiminotriphenylene)₂,
369 a Semiconducting Metal-Organic Graphene Analogue. *J Am Chem Soc.* **136** (25), 8859-8862, dio:
370 10.1021/ja502765n (2014).

371 15 Dirk, C. W. *et al.* Metal poly(benzodithiolenes). *Macromolecules.* **19** (2), 266-269,
372 dio: 10.1021/ma00156a003 (1986).

373 16 Edwards, J. D., Pianka, M. 1346. Isomerisation of 2-butyl-4,6-dinitrophenyl thiocarbamates. *J.*
374 *Chem. Soc.* (0), 7338, dio: 10.1039/JR9650007338 (1965).

375 17 Kwart, H., Evans, E. R. The Vapor Phase Rearrangement of Thioncarbonates and
376 Thioncarbarnates. *J Org Chem.* **31** (2), 410-413, dio: 10.1021/jo01340a015 (1966).

377 18 Newman, M. S., Karnes, H. A. The Conversion of Phenols to Thiophenols via
378 Dialkylthiocarbarnates1. *J Org Chem.* **31** (12), 3980-3984, dio: 10.1021/jo01350a023 (1966).

379 19 Wolman, Y. in *The Thiol Group (1974)*. 669-684, dio: 10.1002/9780470771327 (John Wiley &
380 Sons, Ltd., 2010).

381 20 Harnisch, J. A., Angelici, R. J. Gold and platinum benzenehexathiolate complexes as large
382 templates for the synthesis of 12-coordinate polyphosphine macrocycles. *Inorg Chim Acta.* **300**
383 273-279, dio: 10.1016/S0020-1693(99)00552-6 (2000).

384 21 Yip, H. K., Schier, A., Riede, J., Schmidbaur, H. Benzenehexathiol as a template rim for a golden
385 wheel: synthesis and structure of [CSAu(PPh₃)]₆. *J Chem Soc Dalton Trans.* (15), 2333-2334, dio:
386 10.1039/dt9940002333 (1994).

387 22 Sakamoto, R. *et al.* π -Conjugated Trinuclear Group-9 Metalladithiolenes with a Triphenylene
388 Backbone. *Inorg Chem.* **52** (13), 7411-7416, dio: 10.1021/ic400110z (2013).

389 23 Testaferri, L., Tiecco, M., Tingoli, M., Chianelli, D., Montanucci, M. Simple Syntheses of Aryl
390 Alkyl Thioethers and of Aromatic Thiols from Unactivated Aryl Halides and Efficient Methods for
391 Selective Dealkylation of Aryl Alkyl Ethers and Thioethers. *Synthesis.* (9), 751-755, dio: 10.1055/s-
392 1983-30501 (1983).

393 24 Testaferri, L., Tingoli, M., Tiecco, M. Reactions of polychlorobenzenes with alkanethiol anions

in HMPA. A simple, high-yield synthesis of poly(alkylthio)benzenes. *J Org Chem.* **45** (22), 4376-4380, dio: 10.1021/jo01310a022 (1980).

25 Tiecco, M. Selective dealkylations of aryl alkyl ethers, thioethers, and selenoethers. *Synthesis.* (10), 749-759, dio: 10.1055/s-1988-27699 (1988).

26 Tiecco, M., Tingoli, M., Testaferri, L., Chianelli, D., Maiolo, F. Selective dealkylation of bis[alkylthio]benzenes: elimination-substitution competition with methoxide and methanethiolate ions in hexamethylphosphoric triamide. *Synthesis.* (6), 478-480, dio: 10.1055/s-1982-29844 (1982).

27 Wark, T. A., Stephan, D. W. Early metal thiolato species as metalloligands in the formation of early/late heterobimetallic complexes: syntheses and molecular structures of $\text{Cp}_2\text{Ti}(\text{SMe})_2$, $\text{Cp}_2\text{V}(\text{SMe})_2$, $(\text{Cp}_2\text{Ti}(\mu\text{-SMe})_2)_2\text{Ni}$ and $(\text{Ni}(\mu\text{-SMe})_2)_6$. *Organometallics.* **8** (12), 2836-2843, dio: 10.1021/om00114a017 (1989).

28 Chakraborty, P. Sodium methanethiolate. *e-EROS Encycl Reagents Org Synth.* 1-5, dio: 10.1002/047084289X.rn01716 (2014).

29 Huang, J. *et al.* A semiconducting gyroidal metal-sulfur framework for chemiresistive sensing. *J Mater Chem A.* **5** (31), 16139-16143, dio: 10.1039/c7ta02069d (2017).


30 He, J. *et al.* Building thiol and metal-thiolate functions into coordination nets: Clues from a simple molecule. *J Solid State Chem.* **182** (7), 1821-1826, dio: 10.1016/j.jssc.2009.04.024 (2009).


31 Yee, K.-K. *et al.* Effective Mercury Sorption by Thiol-Laced Metal-Organic Frameworks: in Strong Acid and the Vapor Phase. *J Am Chem Soc.* **135** (21), 7795-7798, dio: 10.1021/ja400212k (2013).


32 Yee, K.-K. *et al.* Room-temperature acetylene hydration by a $\text{Hg}(\text{II})$ -laced metal-organic framework. *Chem Commun.* **51** (54), 10941-10944, dio: 10.1039/c5cc03943f (2015).


33 Gui, B. *et al.* Tackling poison and leach: catalysis by dangling thiol-palladium functions within a porous metal-organic solid. *Chem Commun.* **51** (32), 6917-6920, dio: 10.1039/c5cc90141d (2015).


34 He, J., Zeller, M., Hunter, A. D., Xu, Z. Functional shakeup of metal-organic frameworks: the rise of the sidekick. *CrystEngComm.* **17** (48), 9254-9263, dio: 10.1039/c5ce01790d (2015).


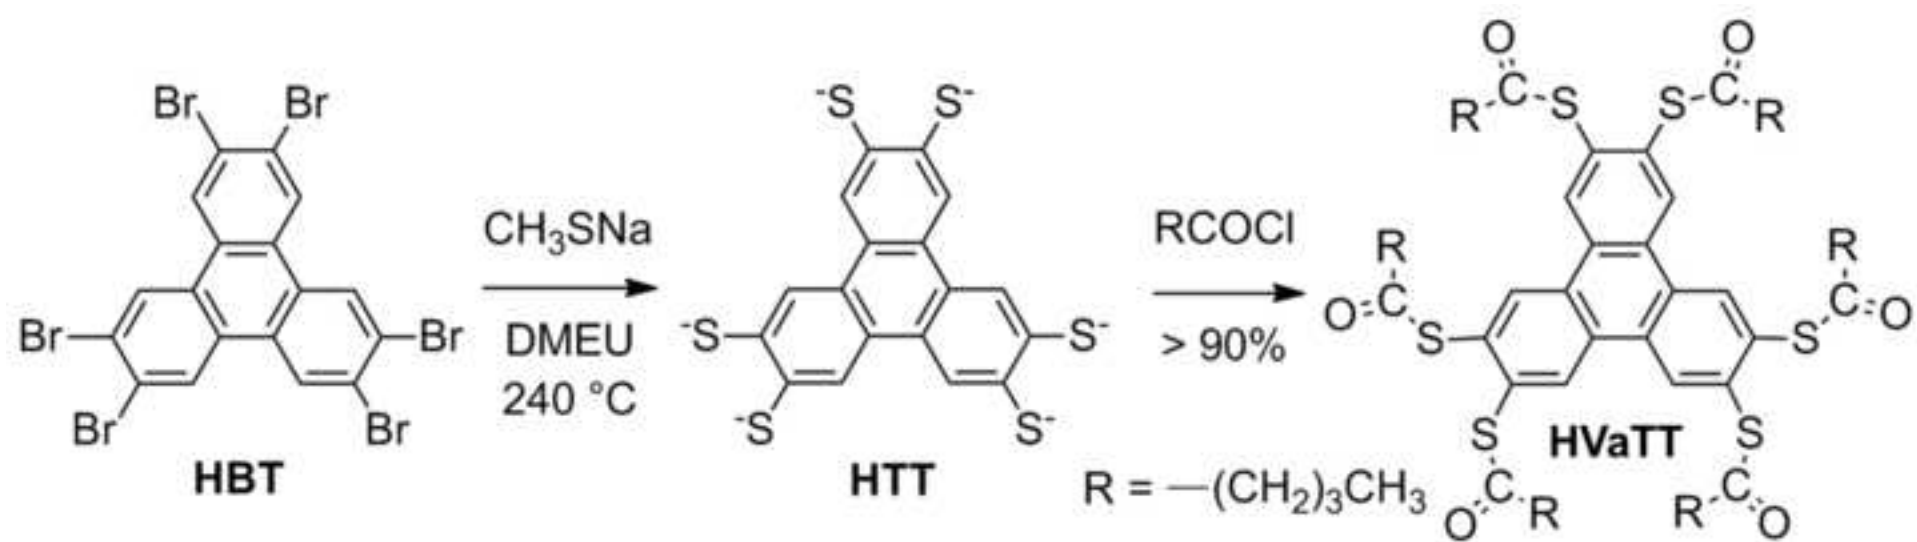


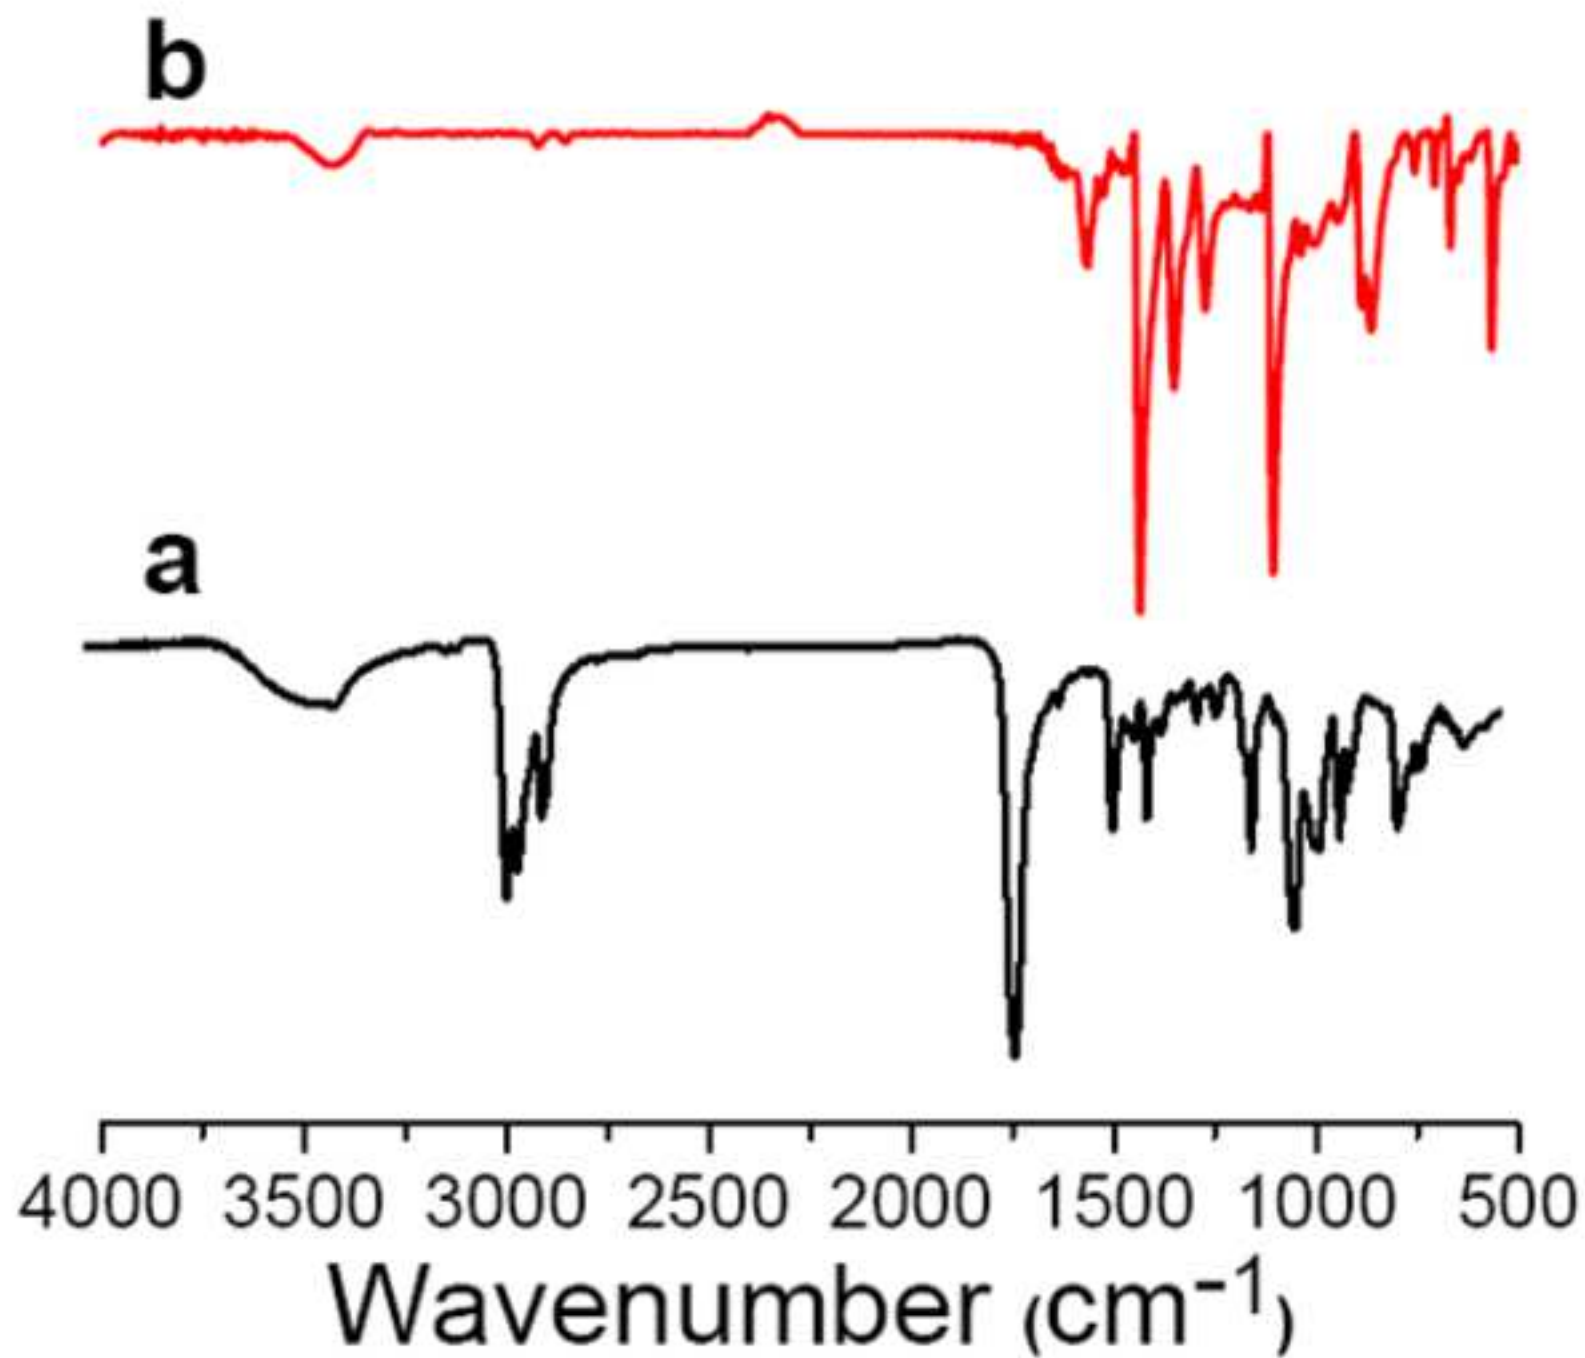

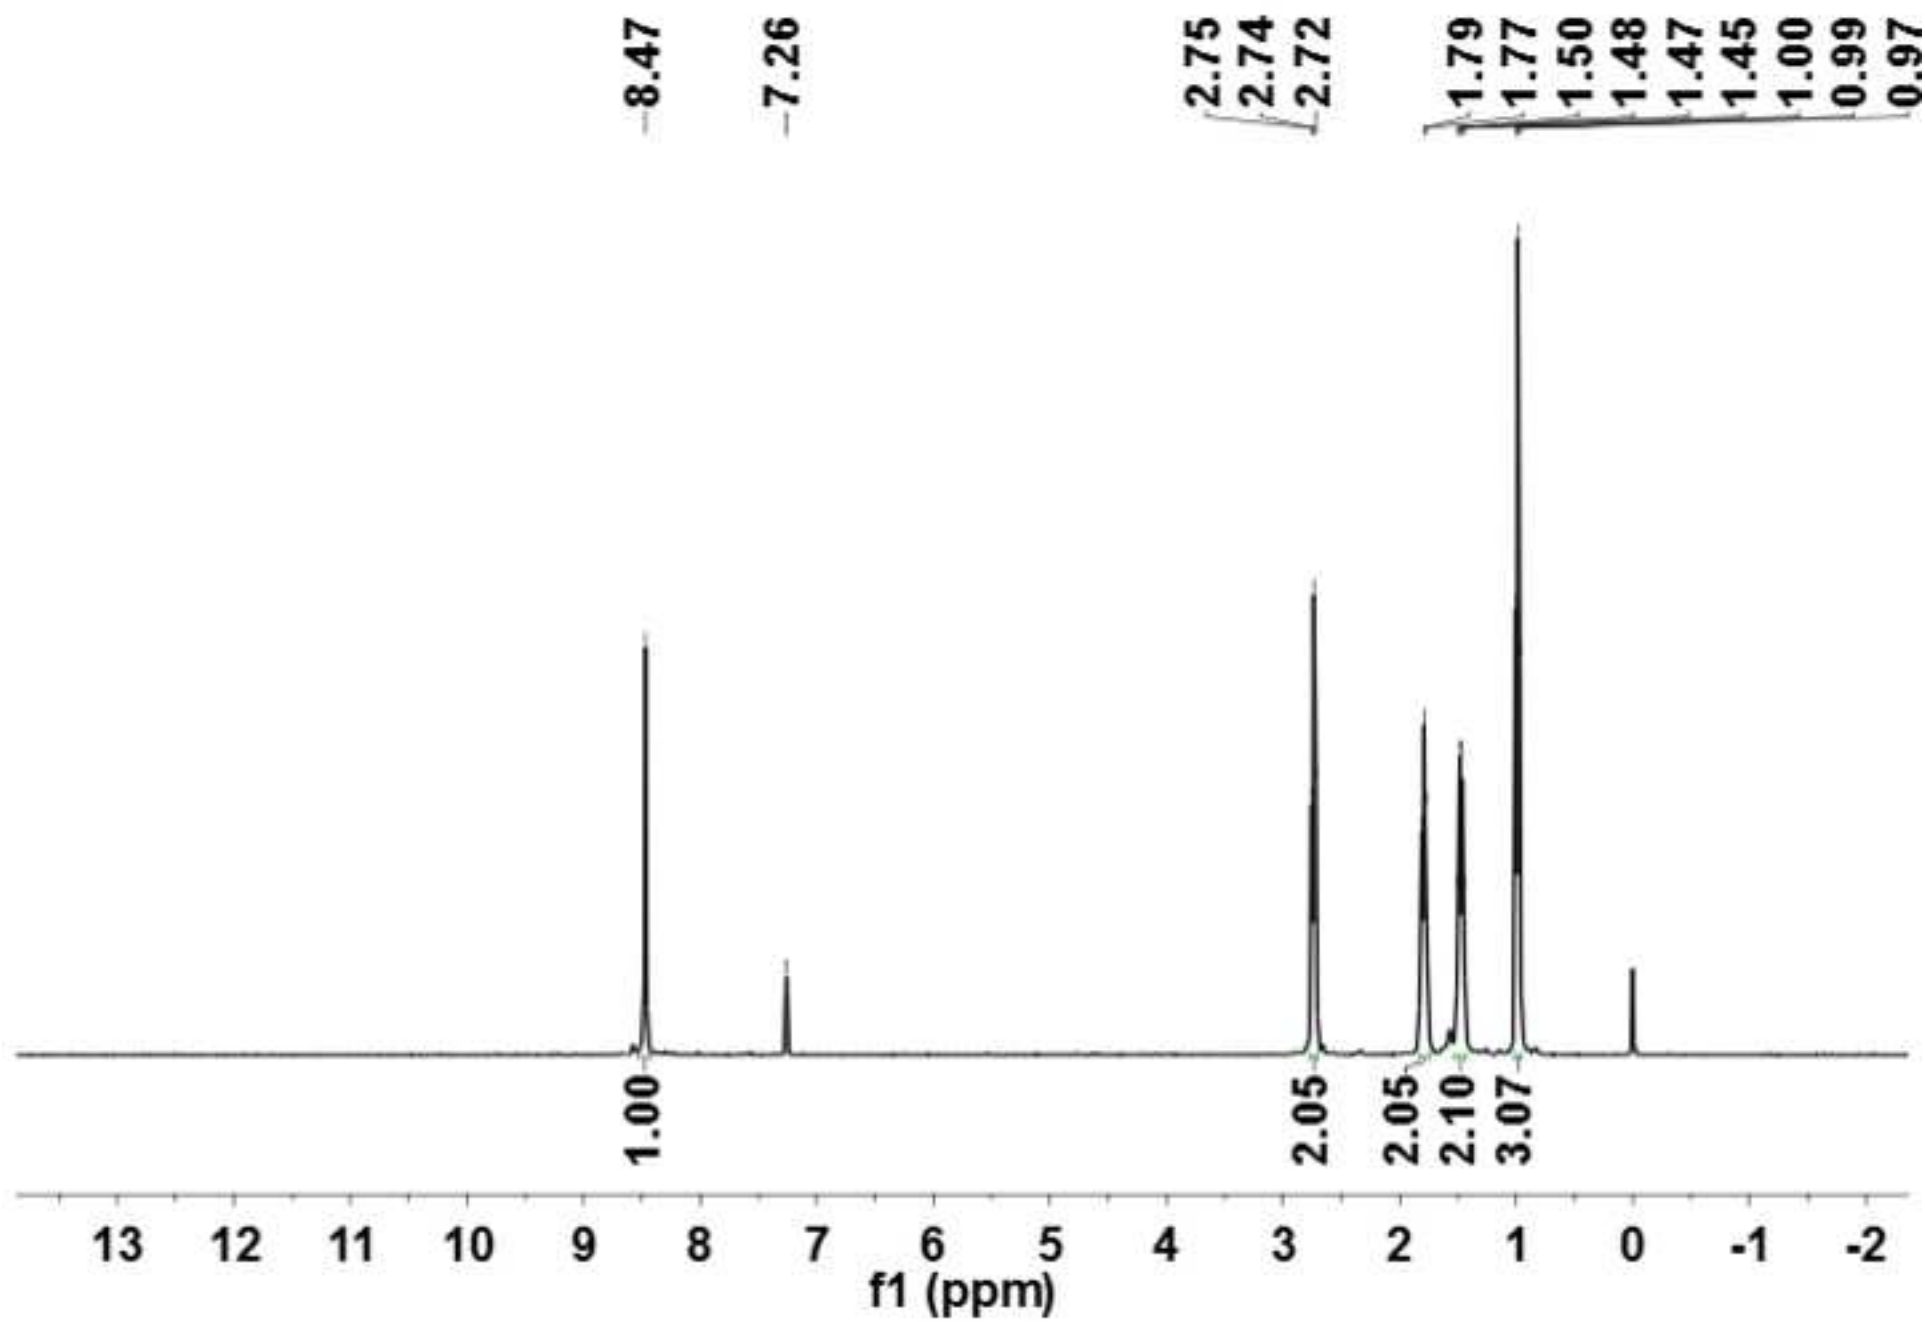

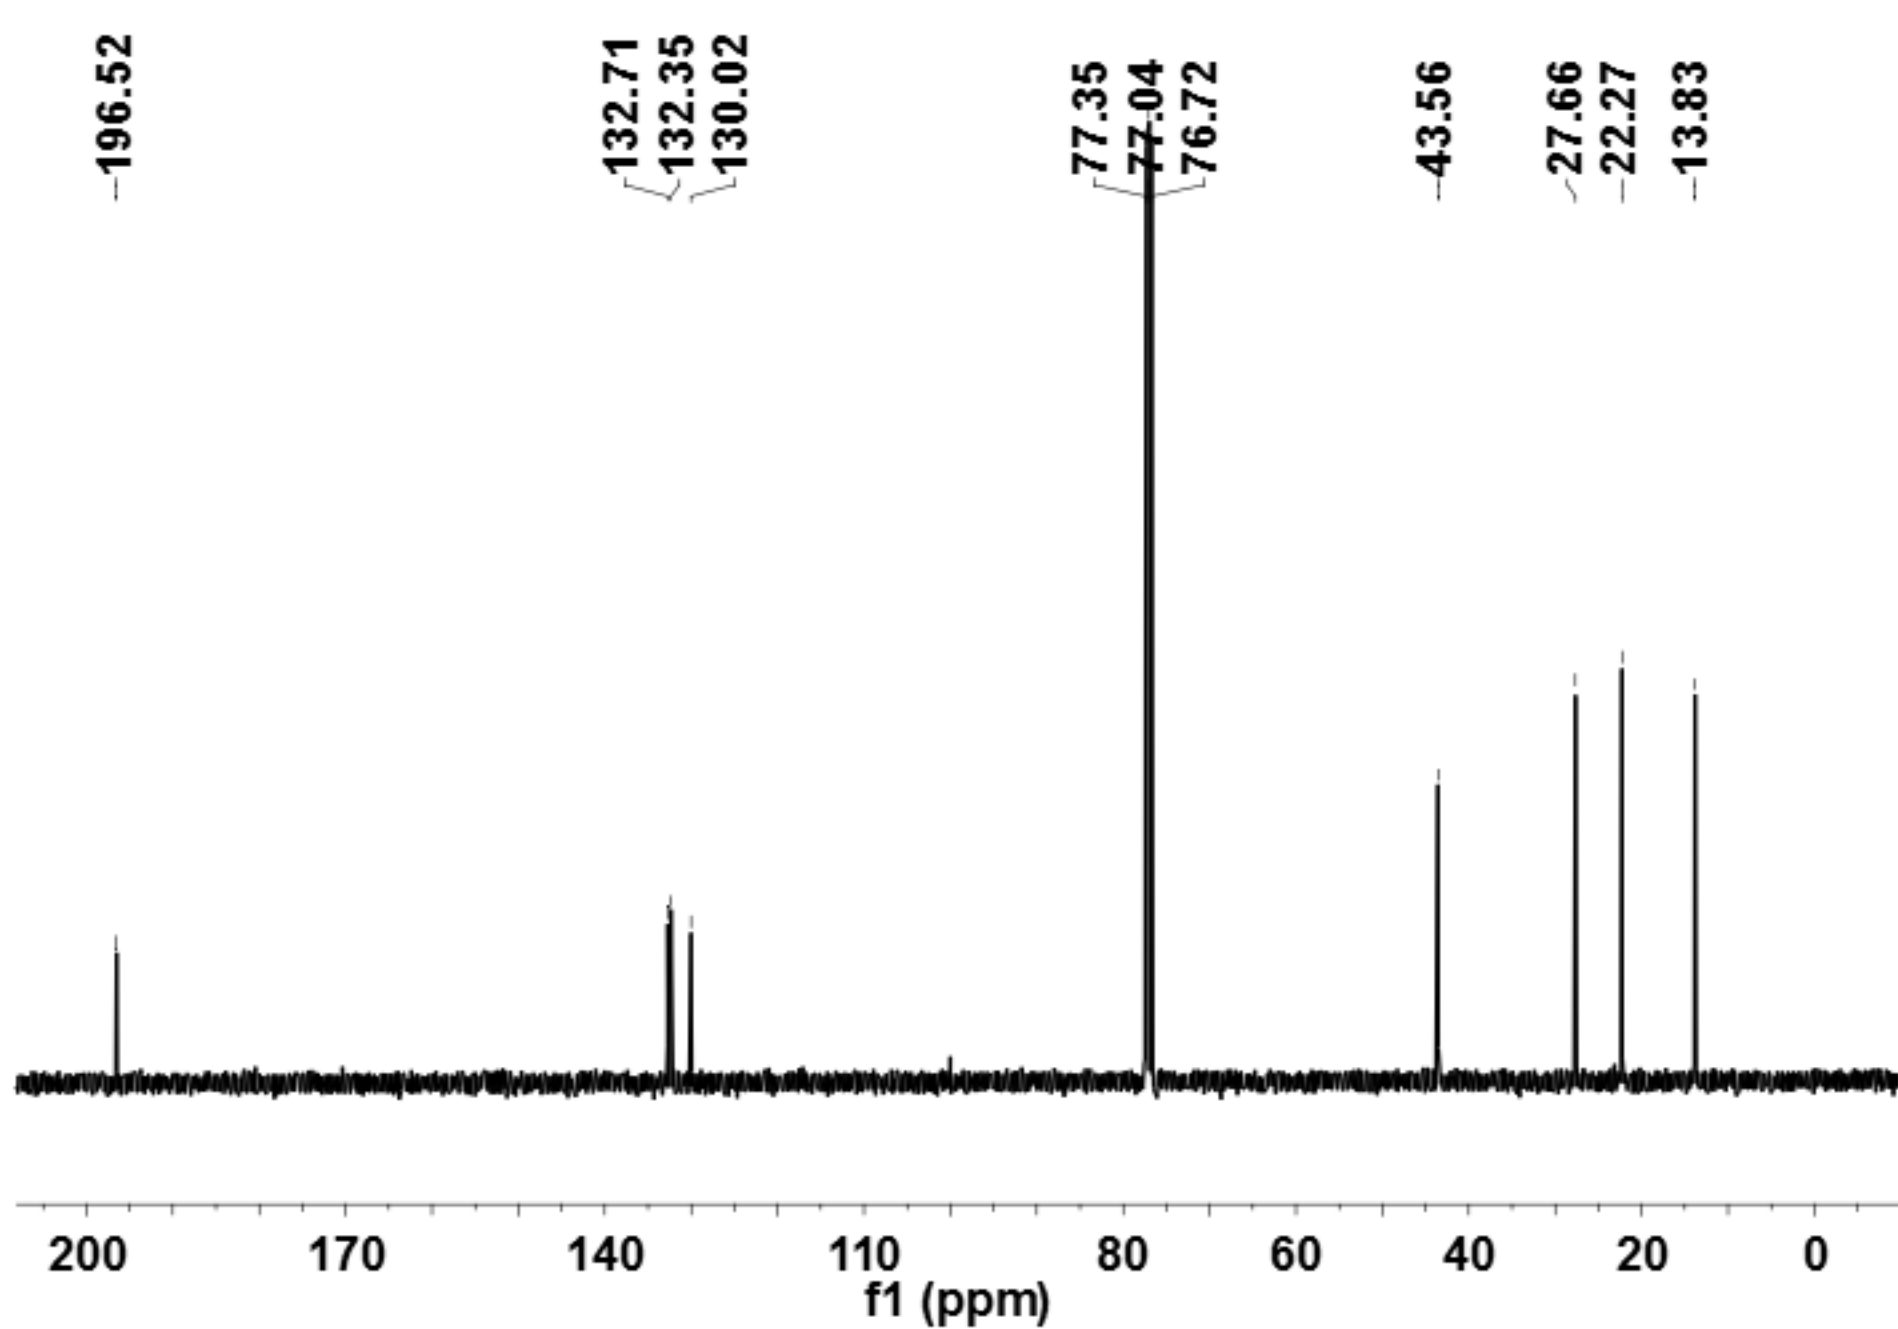

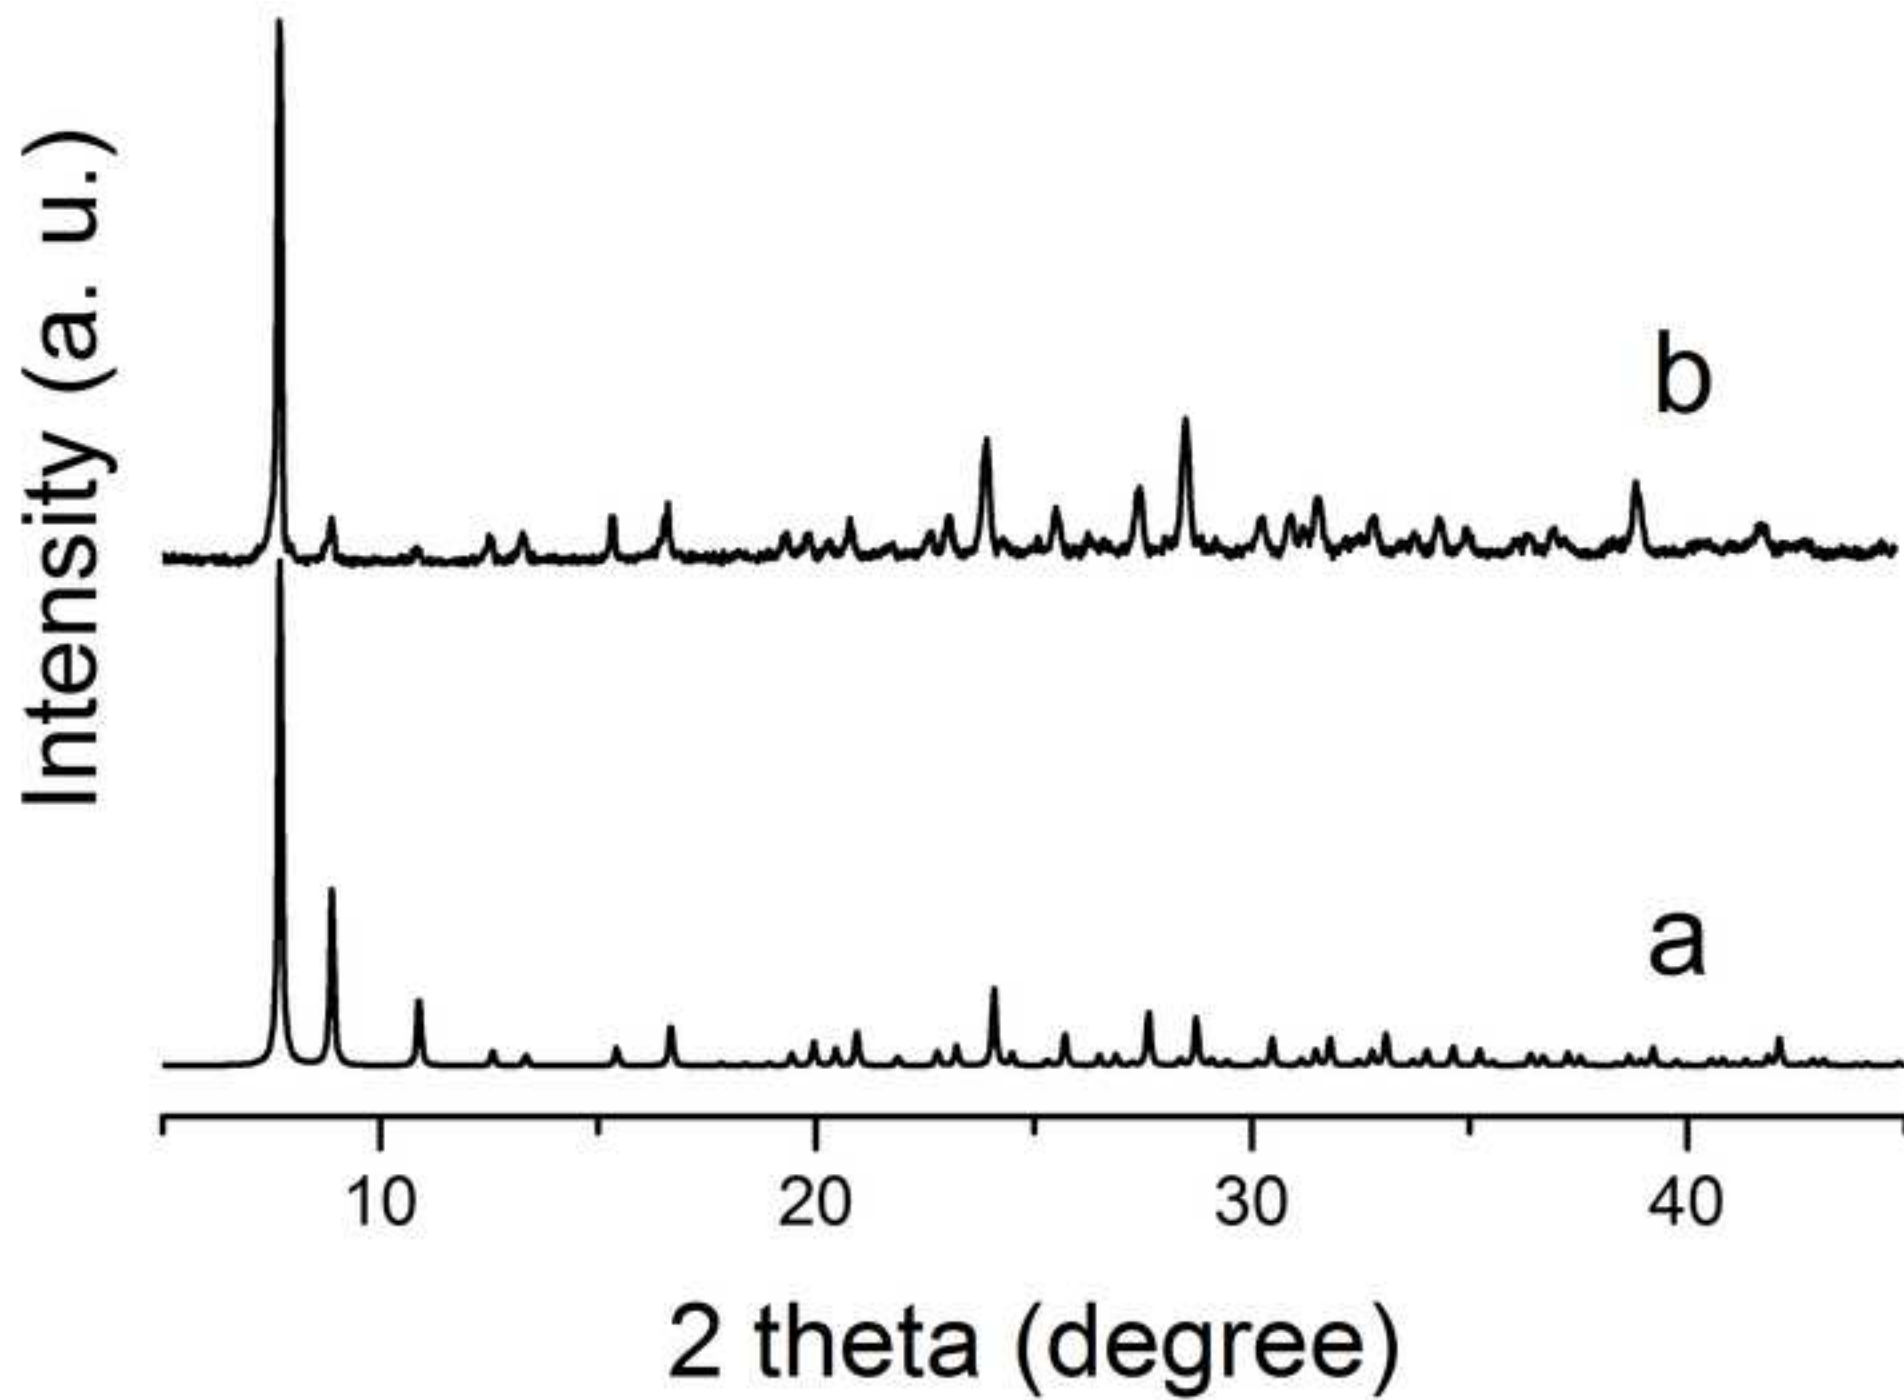

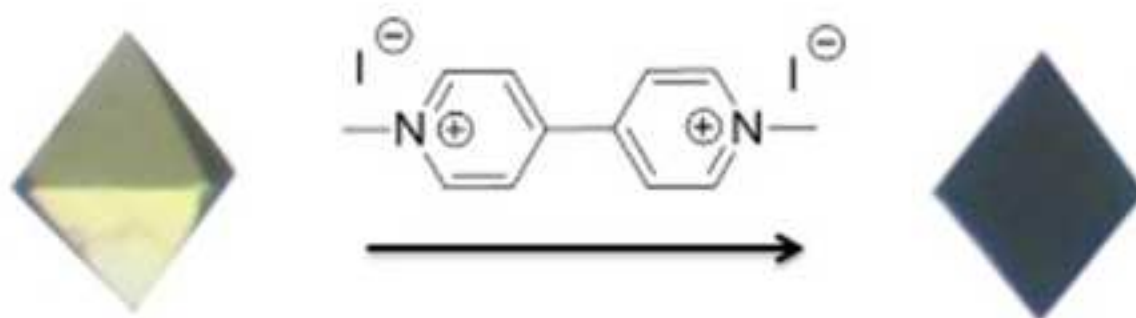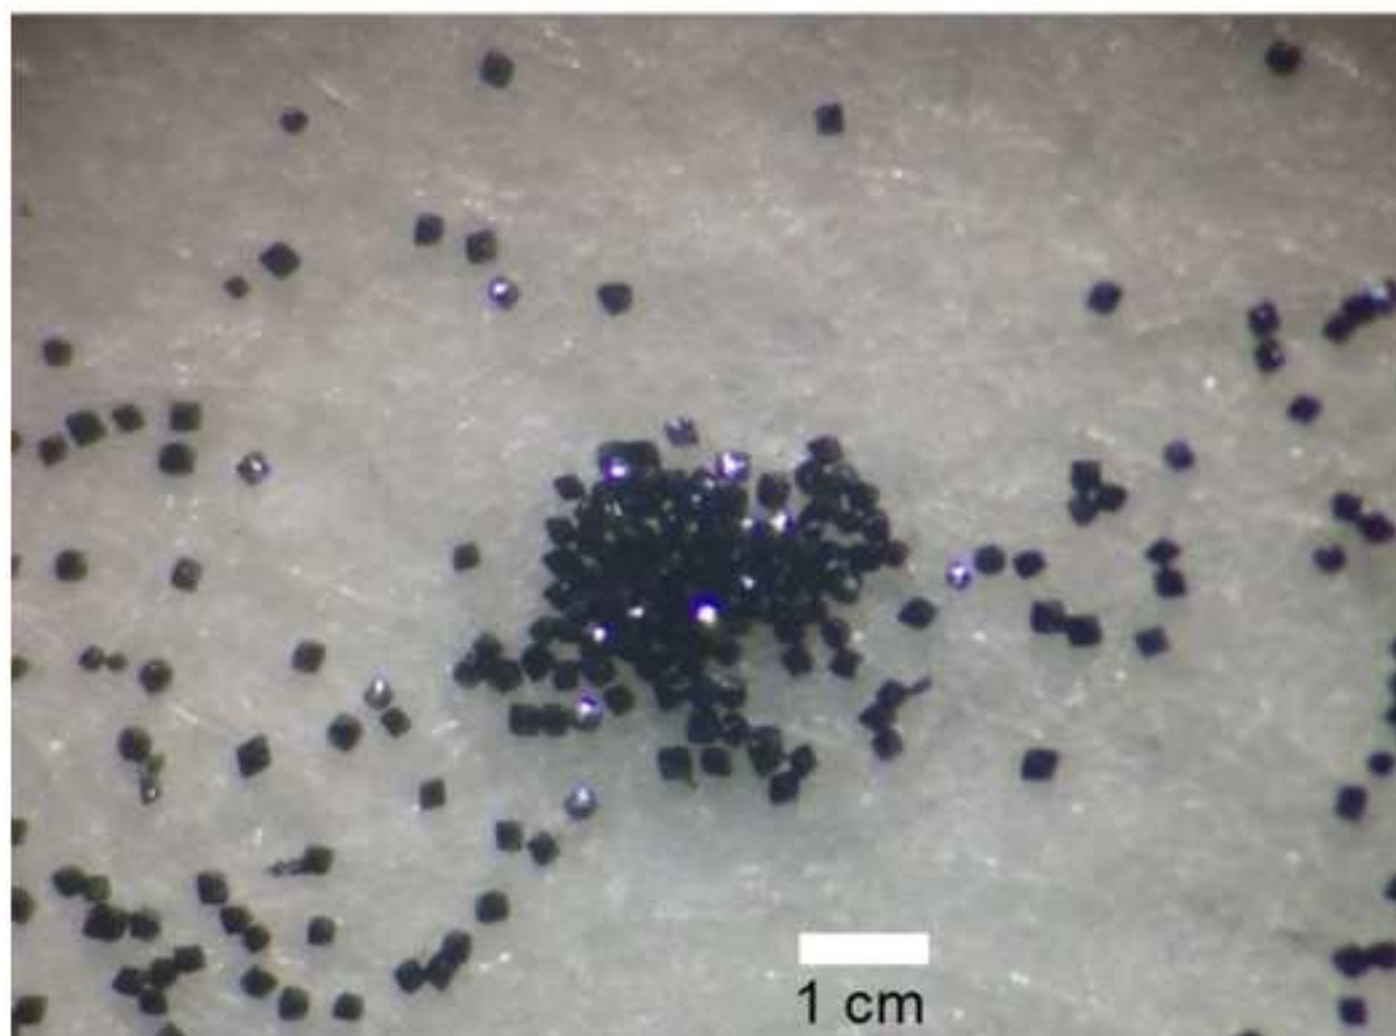a**b**

Name of Material/ Equipment	Company	Catalog Number	Comments/Description
Bromine	DAMAO CHEMICAL REAGENT FACTORY	7726-95-6	Highly toxic
Triphenylene	HWRK Chem	HWG45510	
Iron powder	Sigma-Aldrich	12310	
Nitrobenzene	DAMAO CHEMICAL REAGENT FACTORY	2934	
Diethyl ether	DAMAO CHEMICAL REAGENT FACTORY	48	
Dichloromethane	DAMAO CHEMICAL REAGENT FACTORY	3067	
Sodium metal	J&K	WM-NMS-54-25X-50G	Air sensitive
Tetrahydrofuran	J&K	315353	
Dimethyl disulfide	INTERNATIONAL LABORATORY USA	726415	
1,3-Dimethyl-2-imadazolidinone	J&K	50483	Dried over 4Å sieves
Valeryl chloride	J&K	99590	
Methanol	Guangzhou Chemical Reagent Factory	2334	
Sodium hydroxide	Guangzhou Chemical Reagent Factory	1588	
Ethylene diamine	Riedel-de Haën	15070	
Lead acetate trihydrate	PEKING CHEMICAL WORKE	861218	



1 Alewife Center #200
Cambridge, MA 02140
tel. 617.945.9051
www.jove.com

ARTICLE AND VIDEO LICENSE AGREEMENT

Title of Article: Synthesis of a Thiol Building Block for the Crystallization of a Semiconducting Gyroidal Metal-Sulfur Framework

Author(s): Yonghe He, Jiahong Huang, Jun He, Zhengtao Xu

Item 1 (check one box): The Author elects to have the Materials be made available (as described at <http://www.jove.com/author>) via: ☒ Standard Access ☐ Open Access

Item 2 (check one box):

- ☒ The Author is NOT a United States government employee.
- ☐ The Author is a United States government employee and the Materials were prepared in the course of his or her duties as a United States government employee.
- ☐ The Author is a United States government employee but the Materials were NOT prepared in the course of his or her duties as a United States government employee.

ARTICLE AND VIDEO LICENSE AGREEMENT

1. **Defined Terms.** As used in this Article and Video License Agreement, the following terms shall have the following meanings: "**Agreement**" means this Article and Video License Agreement; "**Article**" means the article specified on the last page of this Agreement, including any associated materials such as texts, figures, tables, artwork, abstracts, or summaries contained therein; "**Author**" means the author who is a signatory to this Agreement; "**Collective Work**" means a work, such as a periodical issue, anthology or encyclopedia, in which the Materials in their entirety in unmodified form, along with a number of other contributions, constituting separate and independent works in themselves, are assembled into a collective whole; "**CRC License**" means the Creative Commons Attribution-Non Commercial-No Derivs 3.0 Unported Agreement, the terms and conditions of which can be found at: <http://creativecommons.org/licenses/by-nc-nd/3.0/legalcode>; "**Derivative Work**" means a work based upon the Materials or upon the Materials and other pre-existing works, such as a translation, musical arrangement, dramatization, fictionalization, motion picture version, sound recording, art reproduction, abridgment, condensation, or any other form in which the Materials may be recast, transformed, or adapted; "**Institution**" means the institution, listed on the last page of this Agreement, by which the Author was employed at the time of the creation of the Materials; "**JoVE**" means MyJoVE Corporation, a Massachusetts corporation and the publisher of *The Journal of Visualized Experiments*; "**Materials**" means the Article and / or the Video; "**Parties**" means the Author and JoVE; "**Video**" means any video(s) made by the Author, alone or in conjunction with any other parties, or by JoVE or its affiliates or agents, individually or in collaboration with the Author or any other parties, incorporating all or any portion of the Article, and in which the Author may or may not appear.

2. **Background.** The Author, who is the author of the Article, in order to ensure the dissemination and protection of the Article, desires to have the JoVE publish the Article and create and transmit videos based on the Article. In furtherance of such goals, the Parties desire to memorialize in this Agreement the respective rights of each Party in and to the Article and the Video.

3. **Grant of Rights in Article.** In consideration of JoVE agreeing to publish the Article, the Author hereby grants to JoVE, subject to **Sections 4 and 7** below, the exclusive, royalty-free, perpetual (for the full term of copyright in the Article, including any extensions thereto) license (a) to publish, reproduce, distribute, display and store the Article in all forms, formats and media whether now known or hereafter developed (including without limitation in print, digital and electronic form) throughout the world, (b) to translate the Article into other languages, create adaptations, summaries or extracts of the Article or other Derivative Works (including, without limitation, the Video) or Collective Works based on all or any portion of the Article and exercise all of the rights set forth in (a) above in such translations, adaptations, summaries, extracts, Derivative Works or Collective Works and (c) to license others to do any or all of the above. The foregoing rights may be exercised in all media and formats, whether now known or hereafter devised, and include the right to make such modifications as are technically necessary to exercise the rights in other media and formats. If the "Open Access" box has been checked in **Item 1** above, JoVE and the Author hereby grant to the public all such rights in the Article as provided in, but subject to all limitations and requirements set forth in, the CRC License.

ARTICLE AND VIDEO LICENSE AGREEMENT

4. Retention of Rights in Article. Notwithstanding the exclusive license granted to JoVE in **Section 3** above, the Author shall, with respect to the Article, retain the non-exclusive right to use all or part of the Article for the non-commercial purpose of giving lectures, presentations or teaching classes, and to post a copy of the Article on the Institution's website or the Author's personal website, in each case provided that a link to the Article on the JoVE website is provided and notice of JoVE's copyright in the Article is included. All non-copyright intellectual property rights in and to the Article, such as patent rights, shall remain with the Author.

5. Grant of Rights in Video – Standard Access. This **Section 5** applies if the "Standard Access" box has been checked in **Item 1** above or if no box has been checked in **Item 1** above. In consideration of JoVE agreeing to produce, display or otherwise assist with the Video, the Author hereby acknowledges and agrees that, Subject to **Section 7** below, JoVE is and shall be the sole and exclusive owner of all rights of any nature, including, without limitation, all copyrights, in and to the Video. To the extent that, by law, the Author is deemed, now or at any time in the future, to have any rights of any nature in or to the Video, the Author hereby disclaims all such rights and transfers all such rights to JoVE.

6. Grant of Rights in Video – Open Access. This **Section 6** applies only if the "Open Access" box has been checked in **Item 1** above. In consideration of JoVE agreeing to produce, display or otherwise assist with the Video, the Author hereby grants to JoVE, subject to **Section 7** below, the exclusive, royalty-free, perpetual (for the full term of copyright in the Article, including any extensions thereto) license (a) to publish, reproduce, distribute, display and store the Video in all forms, formats and media whether now known or hereafter developed (including without limitation in print, digital and electronic form) throughout the world, (b) to translate the Video into other languages, create adaptations, summaries or extracts of the Video or other Derivative Works or Collective Works based on all or any portion of the Video and exercise all of the rights set forth in (a) above in such translations, adaptations, summaries, extracts, Derivative Works or Collective Works and (c) to license others to do any or all of the above. The foregoing rights may be exercised in all media and formats, whether now known or hereafter devised, and include the right to make such modifications as are technically necessary to exercise the rights in other media and formats. For any Video to which this Section 6 is applicable, JoVE and the Author hereby grant to the public all such rights in the Video as provided in, but subject to all limitations and requirements set forth in, the CRC License.

7. Government Employees. If the Author is a United States government employee and the Article was prepared in the course of his or her duties as a United States government employee, as indicated in **Item 2** above, and any of the licenses or grants granted by the Author hereunder exceed the scope of the 17 U.S.C. 403, then the rights granted hereunder shall be limited to the maximum rights permitted under such

statute. In such case, all provisions contained herein that are not in conflict with such statute shall remain in full force and effect, and all provisions contained herein that do so conflict shall be deemed to be amended so as to provide to JoVE the maximum rights permissible within such statute.

8. Likeness, Privacy, Personality. The Author hereby grants JoVE the right to use the Author's name, voice, likeness, picture, photograph, image, biography and performance in any way, commercial or otherwise, in connection with the Materials and the sale, promotion and distribution thereof. The Author hereby waives any and all rights he or she may have, relating to his or her appearance in the Video or otherwise relating to the Materials, under all applicable privacy, likeness, personality or similar laws.

9. Author Warranties. The Author represents and warrants that the Article is original, that it has not been published, that the copyright interest is owned by the Author (or, if more than one author is listed at the beginning of this Agreement, by such authors collectively) and has not been assigned, licensed, or otherwise transferred to any other party. The Author represents and warrants that the author(s) listed at the top of this Agreement are the only authors of the Materials. If more than one author is listed at the top of this Agreement and if any such author has not entered into a separate Article and Video License Agreement with JoVE relating to the Materials, the Author represents and warrants that the Author has been authorized by each of the other such authors to execute this Agreement on his or her behalf and to bind him or her with respect to the terms of this Agreement as if each of them had been a party hereto as an Author. The Author warrants that the use, reproduction, distribution, public or private performance or display, and/or modification of all or any portion of the Materials does not and will not violate, infringe and/or misappropriate the patent, trademark, intellectual property or other rights of any third party. The Author represents and warrants that it has and will continue to comply with all government, institutional and other regulations, including, without limitation all institutional, laboratory, hospital, ethical, human and animal treatment, privacy, and all other rules, regulations, laws, procedures or guidelines, applicable to the Materials, and that all research involving human and animal subjects has been approved by the Author's relevant institutional review board.

10. JoVE Discretion. If the Author requests the assistance of JoVE in producing the Video in the Author's facility, the Author shall ensure that the presence of JoVE employees, agents or independent contractors is in accordance with the relevant regulations of the Author's institution. If more than one author is listed at the beginning of this Agreement, JoVE may, in its sole discretion, elect not take any action with respect to the Article until such time as it has received complete, executed Article and Video License Agreements from each such author. JoVE reserves the right, in its absolute and sole discretion and without giving any reason therefore, to accept or decline any work submitted to JoVE. JoVE and its employees, agents and independent contractors shall have

ARTICLE AND VIDEO LICENSE AGREEMENT

full, unfettered access to the facilities of the Author or of the Author's institution as necessary to make the Video, whether actually published or not. JoVE has sole discretion as to the method of making and publishing the Materials, including, without limitation, to all decisions regarding editing, lighting, filming, timing of publication, if any, length, quality, content and the like.

11. Indemnification. The Author agrees to indemnify JoVE and/or its successors and assigns from and against any and all claims, costs, and expenses, including attorney's fees, arising out of any breach of any warranty or other representations contained herein. The Author further agrees to indemnify and hold harmless JoVE from and against any and all claims, costs, and expenses, including attorney's fees, resulting from the breach by the Author of any representation or warranty contained herein or from allegations or instances of violation of intellectual property rights, damage to the Author's or the Author's institution's facilities, fraud, libel, defamation, research, equipment, experiments, property damage, personal injury, violations of institutional, laboratory, hospital, ethical, human and animal treatment, privacy or other rules, regulations, laws, procedures or guidelines, liabilities and other losses or damages related in any way to the submission of work to JoVE, making of videos by JoVE, or publication in JoVE or elsewhere by JoVE. The Author shall be responsible for, and shall hold JoVE harmless from, damages caused by lack of sterilization, lack of cleanliness or by contamination due to the making of a video by JoVE its employees, agents or independent contractors. All sterilization, cleanliness or decontamination procedures shall be solely the responsibility of the Author and shall be undertaken at the Author's

expense. All indemnifications provided herein shall include JoVE's attorney's fees and costs related to said losses or damages. Such indemnification and holding harmless shall include such losses or damages incurred by, or in connection with, acts or omissions of JoVE, its employees, agents or independent contractors.

12. Fees. To cover the cost incurred for publication, JoVE must receive payment before production and publication the Materials. Payment is due in 21 days of invoice. Should the Materials not be published due to an editorial or production decision, these funds will be returned to the Author. Withdrawal by the Author of any submitted Materials after final peer review approval will result in a US\$1,200 fee to cover pre-production expenses incurred by JoVE. If payment is not received by the completion of filming, production and publication of the Materials will be suspended until payment is received.

13. Transfer, Governing Law. This Agreement may be assigned by JoVE and shall inure to the benefits of any of JoVE's successors and assignees. This Agreement shall be governed and construed by the internal laws of the Commonwealth of Massachusetts without giving effect to any conflict of law provision thereunder. This Agreement may be executed in counterparts, each of which shall be deemed an original, but all of which together shall be deemed to be one and the same agreement. A signed copy of this Agreement delivered by facsimile, e-mail or other means of electronic transmission shall be deemed to have the same legal effect as delivery of an original signed copy of this Agreement.

A signed copy of this document must be sent with all new submissions. Only one Agreement required per submission.

CORRESPONDING AUTHOR:

Name:	Zhengtao Xu		
Department:	Department of Chemistry		
Institution:	City University of Hong Kong		
Article Title:	Synthesis of a Thiol Building Block for the Crystallization of a Semiconducting Gyroidal Metal-Sulfur Framework		
Signature:		Date:	Oct 11, 2017

Please submit a signed and dated copy of this license by one of the following three methods:

- 1) Upload a scanned copy of the document as a pdf on the JoVE submission site;
- 2) Fax the document to +1.866.381.2236;
- 3) Mail the document to JoVE / Attn: JoVE Editorial / 1 Alewife Center #200 / Cambridge, MA 02139

For questions, please email submissions@jove.com or call +1.617.945.9051

Dear Editors, please see below the responses in connection with the manuscript revision.

Thank you,

Zhengtao Xu

Editorial comments:

The manuscript has been modified and the updated manuscript, **57455_R0.docx**, is attached and located in your Editorial Manager account. **Please use the updated version to make your revisions.**

1. Please take this opportunity to thoroughly proofread the manuscript to ensure that there are no spelling or grammar issues.

Checked.

2. Unfortunately, there are a few sections of the manuscript that show significant overlap with previously published work. Though there may be a limited number of ways to describe a technique, please use original language throughout the manuscript. Please check the iThenticateReport attached to this email.

The text has been revised to resolve the issue mentioned.

3. Please define all abbreviations before use.

Done!

4. Please revise the table of materials. The table should be uploaded to your Editorial Manager account in the form of an .xls or .xlsx file.

Done!

5. Please ensure that the references appear as the following:

Lastname, F.I., LastName, F.I., LastName, F.I. Article Title. *Source*. **Volume** (Issue), FirstPage – LastPage, doi: DOI (YEAR).

For more than 6 authors, list only the first author then et al.

Done!

6. Please use standard SI unit symbols and prefixes such as μL , mL, L, g, m, etc., and h, min, s for time units.

Done!

7. Please obtain explicit copyright permission to reuse any figures from a previous publication. Explicit permission can be expressed in the form of a letter from the editor or a link to the editorial policy that allows re-prints. Please upload this information as a .doc or .docx file to your Editorial Manager account. The Figure must be cited appropriately in the Figure Legend, i.e. "This figure has been modified from [citation]."

Upload the copyright permission.

8. Please provide a short description in addition to the title for each figure.
9. A schematic or a picture of the vacuum gas manifold would be helpful for the readers.
A vacuum gas manifold is well known.
10. Protocol step 1.3: Is THF and DMSO used directly after purchased? If not, please specify the drying procedure in a note.
Exactly, THF and DMSO is used directly after purchased.
11. 1.5: What's the flow rate of dinitrogen gas? Please specify how much solvent is left in the step.
Use a stream of N₂ (0.2 L/min) to blow off, until a dry solid appears.
12. 1.6: Please specify how to store the solid product in a nitrogen atmosphere.
13. 2.2: What is HBT?
2,3,6,7,10,11-hexabromotriphenylene
14. 2.3: What is DMEU?
1,3-Dimethyl-2-imidazolidinone
15. 2.4: Please split this step into three or more steps. What is used to withdraw a small aliquot from the reaction mixture?
Have divided into three steps (2.4~2.6). Use a glass dropper to withdraw a small aliquot of the reaction mixture.
16. 2.8: Please specify if a TLC is used. If yes, please specify R_f value.
Use 1:4 ethyl acetate/petroleum ether to develop the TLC plate, R_f = 0.4.
17. 3.2: What is HVaTT?
2,3,6,7,10,11-hexakis(pentanoylthio)triphenylene
18. 3.4: Is it appropriate to use a vial? Is it safer to use a pressure tube in this step?
Vial is ok, but, for the safety, we can use a Schlenk flask instead.
19. 3.5: How are the crystals transferred to a vial?
The crystals with a little mother liquid were sucked out from the reaction mixture by a glass dropper, and then immediately transferred into a glass vial containing 5 mL airless MeOH. The liquid was decanted and a new portion of airless methanol was injected into the vial as soon as possible.
20. 4.1: What's the size of the Petri dish?
diameter 35 mm and depth 10 mm

21. Scheme 1: Please make this as a figure.
Done!