

# Journal of Visualized Experiments

## RF magnetron sputtering of GdBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub>/ La<sub>0.67</sub>Sr<sub>0.33</sub>MnO<sub>3</sub> Quasi-bilayer films on SrTiO<sub>3</sub> (STO) single-crystal substrates --Manuscript Draft--

Article Type:	Invited Methods Article - JoVE Produced Video
Manuscript Number:	JoVE58069R2
Full Title:	RF magnetron sputtering of GdBa <sub>2</sub> Cu <sub>3</sub> O <sub>7-δ</sub> / La <sub>0.67</sub> Sr <sub>0.33</sub> MnO <sub>3</sub> Quasi-bilayer films on SrTiO <sub>3</sub> (STO) single-crystal substrates
Keywords:	LSMO; (Gd) BCO; sputtering; superconductivity; ferromagnetic particles
Corresponding Author:	Ying Wang CHINA
Corresponding Author's Institution:	
Corresponding Author E-Mail:	2006000081@shiep.edu.cn
Order of Authors:	Ying Wang Yijie Li Linfei Liu XiaoJing Luo
Additional Information:	
Question	Response
Please indicate whether this article will be Standard Access or Open Access.	Standard Access (US\$2,400)
Please indicate the city, state/province, and country where this article will be filmed. Please do not use abbreviations.	28# Xue Hai Road, Shanghai 201300 P.R. China

**TITLE:**

**Radio Frequency Magnetron Sputtering of  $\text{GdBa}_2\text{Cu}_3\text{O}_{7-\delta}$ /  $\text{La}_{0.67}\text{Sr}_{0.33}\text{MnO}_3$  Quasi-bilayer Films on  $\text{SrTiO}_3$  (STO) Single-crystal Substrates**

**AUTHORS & AFFILIATIONS:**

Ying Wang<sup>1, 2</sup>, Yijie Li<sup>2</sup>, Linfei Liu<sup>2</sup>, Da Xu<sup>2</sup>, Xiaojing Luo<sup>1</sup>, Tian Gao<sup>1, 3</sup>, Yanyan Zhu<sup>1, 3</sup>

<sup>1</sup>Department of Physics, Mathematics, Shanghai Key Laboratory of Materials Protection and Advanced Materials in Electric Power, Shanghai University of Electric Power, Shanghai, P.R. China

<sup>2</sup>Key Laboratory of Artificial Structure and Quantum Control, Ministry of Education, Department of Physics, Shanghai Jiao Tong University, Shanghai, P.R. China

<sup>3</sup>Shanghai Key Laboratory of High Temperature Superconductors, Shanghai University, Shanghai, P.R. China

**Corresponding author:**

Ying Wang (2006000081@sjtu.edu.cn)

Phone: +86-21-68020533; Fax: +86-21-68020533

**Email Addresses of Co-authors:**

Yijie Li (yjli@sjtu.edu.cn)

Linfei Liu (linfeiliu@sjtu.edu.cn)

Da Xu (daxu@sjtu.edu.cn)

Xiaojing Luo (xiaojingluo@sjtu.edu.cn)

**KEYWORDS:**

LSMO/ (Gd) BCO films, RF-sputtering, superconductivity, ferromagnetic, nanoparticles, quasi-bilayer film structure

**SHORT ABSTRACT:**

Here, we present a protocol to grow LSMO nanoparticles and (Gd) BCO films on (001)  $\text{SrTiO}_3$  (STO) single-crystal substrates by radio frequency (RF)-sputtering.

**LONG ABSTRACT:**

Here, we demonstrate a method of coating ferromagnetic  $\text{La}_{0.67}\text{Sr}_{0.33}\text{MnO}_3$  (LSMO) nanoparticles on (001)  $\text{SrTiO}_3$  (STO) single-crystal substrates by radio frequency (RF) magnetron sputtering. LSMO nanoparticles were deposited with diameters from 10 to 20 nm and heights between 20 and 50 nm. At the same time, (Gd)  $\text{Ba}_2\text{Cu}_3\text{O}_{7-\delta}$  ((Gd) BCO) films were fabricated on both undecorated and LSMO nanoparticle decorated STO substrates using RF magnetron sputtering. This report also describes the properties of  $\text{GdBa}_2\text{Cu}_3\text{O}_{7-\delta}$ /  $\text{La}_{0.67}\text{Sr}_{0.33}\text{MnO}_3$  quasi-bilayer films structures (*e.g.*, crystalline phase, morphology, chemical composition); magnetization, magneto-transport, and superconducting transport properties were also evaluated.

## INTRODUCTION:

The hole-doped manganite  $\text{La}_{0.67}\text{Sr}_{0.33}\text{MnO}_3$  (LSMO) have unique properties such as wide-band gaps, half-metallic ferromagnetism, and entangled electronic states, which provide extraordinary opportunities for potential spintronic applications<sup>1-4</sup>. Currently, many researchers are endeavoring to take advantage of the unique properties of LSMO to inhabit the vortex movement for high temperature superconducting (HTS) films, such as (RE)  $\text{Ba}_2\text{Cu}_3\text{O}_{7-\delta}$  films (REBCO, RE= rare-earth element)<sup>5-12</sup>. Nanoscale decoration of the substrate surfaces with ferromagnetic nanoparticles will provide well-defined sites for inducing magnetic pinning centers of expected density<sup>13,14</sup>. However, the ability to control the density and geometry of the nanoparticles on highly textured surfaces, such as on single-crystal substrates and highly textured metal substrates is very difficult. Most commonly, nanoparticles are synthesized and coated on surfaces using metal organic decomposition methods<sup>15</sup>, and pulsed laser deposition methods<sup>16,17</sup>. Although pulse laser deposition methods can provide nanoparticles coated on various substrates, it is difficult to realize large area homogeneous nanoparticles deposition. As for metal organic decomposition methods, they are proper for large area deposition of nanoparticles. However, the nanoparticles are often non-uniform and easily damaged by small physical stresses.

Among these techniques, RF-magnetron sputtering has many advantages. Sputtering has a high deposition rate, low cost, and a lack of toxic gas emission. Also, it is easy to expand to large scale area substrates<sup>18,19</sup>. This method provides single-step formation of  $\text{La}_{0.67}\text{Sr}_{0.33}\text{MnO}_3$  (LSMO) nanoparticles, and the nanoparticles are easy to be deposited on single-crystal substrates. RF magnetron sputtering can create large area nanoparticles uniformly on a diverse range of substrates, irrespective of surface texture, and surface roughness<sup>20</sup>. The particle control can be achieved by adjust sputtering time. Homogeneity can be achieved by adjust target-substrate distance. The disadvantage of RF-magnetron sputtering is its lower growth rate for some oxides<sup>21</sup>. In this approach, target atoms (or molecules) are sputtered out of the target by argon ion, and then nanoparticles are deposited on substrates in the vapor phase<sup>22</sup>. Nanoparticles formation occurs on the substrate in a single step<sup>23</sup>. This method is theoretically applicable to any materials including superconducting thin film, resistance film, semiconductor film, ferromagnetic thin film *etc.* However, to date, reports about protocols for depositing ferromagnetic nanoparticles are very scarce.

Here, we demonstrate the deposition of  $\text{GdBa}_2\text{Cu}_3\text{O}_{7-\delta}/\text{La}_{0.67}\text{Sr}_{0.33}\text{MnO}_3$  quasi-bilayer films on  $\text{SrTiO}_3$  (STO) single-crystal substrates by RF magnetron sputtering method. Two kinds of target materials,  $\text{GdBa}_2\text{Cu}_3\text{O}_{7-\delta}$  and  $\text{La}_{0.67}\text{Sr}_{0.33}\text{MnO}_3$  target are used in the process.  $\text{SrTiO}_3$  (STO) single-crystal substrates were coated with  $\text{GdBa}_2\text{Cu}_3\text{O}_{7-\delta}$  films and  $\text{GdBa}_2\text{Cu}_3\text{O}_{7-\delta}/\text{La}_{0.67}\text{Sr}_{0.33}\text{MnO}_3$  quasi-bilayer films.

In this protocol,  $\text{GdBa}_2\text{Cu}_3\text{O}_{7-\delta}/\text{La}_{0.67}\text{Sr}_{0.33}\text{MnO}_3$  Quasi-bilayer films are deposited with RF magnetron sputtering on STO (001) substrates. The target diameter is 60 mm and the distance between the target and substrates is about 10 cm. The heaters are bulbs positioned 1 cm above the substrates. The maximum temperature is 850°C in this system. There are 5 different

substrates in this system. RF magnetron sputtering  $\text{GdBa}_2\text{Cu}_3\text{O}_{7-\delta}/\text{La}_{0.67}\text{Sr}_{0.33}\text{MnO}_3$  quasi-bilayer films consists of two steps, which are the preparation of substrates and the RF magnetron sputtering process. A picture of the sputtering system is shown in **Figure S1**.

## **PROTOCOL:**

### **1. Substrate and Target Preparation**

Note: This section describes the preparation of the sputter deposition chamber and the single crystal  $\text{SrTiO}_3$  (STO) substrates.

1.1. Use 10 mm x 10 mm  $\text{SrTiO}_3$  (STO) single-crystal substrates during the RF magnetron sputtering process.

1.2. Sequentially clean the substrates in isopropanol and deionized water for 10 min each at room temperature in ultrasonic bath. Then dry the substrates with nitrogen, which is for uniform covering of the substrate and good film adherence.

1.3. Mount the (001) STO substrates in the substrate holders with silver powder conductive glue. Load these into the vacuum chamber.

1.4. Mount the LSMO target in the magnetron injection gun, and then reassemble the gun. Test the resistance with an ohmmeter, to avoid a short circuit between the magnetron and the surrounding shield. Close the vacuum chamber is closed and pump down.

1.5. Once the vacuum is lower than  $1 \times 10^{-4}$  Pa, heat the substrates to 850 °C using a heating rate of 15 °C/min. set the target-substrate distance to 8 cm.

1.6. Set the mass flow controller to 10 sccm of O and 5 sccm of Ar as working gas flow. Use Ar/ O mixed gas to keep O cationic ratio (3) for  $\text{La}_{0.67}\text{Sr}_{0.33}\text{MnO}_3$  material during growth.

1.7. Before the deposition, pre-sputter the LSMO target for 20 min at 30 W. High power will lead to cracks in the target and using low power will lead to more time for a clean surface, so we choose 20 min for 30 W.

### **2. LSMO Nanoparticle Deposition**

Note: This section describes the deposition of the LSMO nanoparticles by RF-magnetron sputtering.

2.1. To obtain a chamber pressure of 25 Pa, adjust the molecular pump splint valve. If the instant value is becoming larger than 25 Pa, rotate it counter-clockwise; if it is becoming smaller than 25Pa, rotate it clockwise. Continue until the pressure has settled to a stable value.

2.2. Check that the substrate temperature remains at 850 °C and is stable.

2.3. Increase the power of magnetron from 30 to 80 W. Wait for 10 min, until the plasma is stabilized.

2.4. Open the shutter and deposit LSMO on the heated substrate.

Note: We used sputtering times of 5, 10, 30, and 60 s for four samples.

2.5. Close the shutter. Shut off power to the magnetron. Close the gas valve and shut off heater power.

2.8. Cool the samples to room temperature. Unusually, this takes at least two hours in this system. Vent the chamber with dry nitrogen, open it, and remove the samples.

### 3. $\text{GdBa}_2\text{Cu}_3\text{O}_{7-\delta}$ Film Deposition

3.1. Mount the  $\text{GdBa}_2\text{Cu}_3\text{O}_{7-\delta}$  target in the magnetron gun, then reassemble the gun. Deposit any (Gd) BCO films, using steps similar to steps 1.4-2.8. Use similar deposition conditions for (Gd) BCO films as for the LSMO nanoparticles, except for the sputtering time which should be 30 min. After this, the growth will be over, and next step is the post-annealing.

3.2. Decrease the sample temperature to 500°C. Then, open the gas valve for oxygen to give a chamber pressure of 75,000 Pa. Hold the samples at this temperature for one hour.

Note: The temperature for 500 °C and a chamber pressure of 75, 000 Pa are for uniformly achieving LSMO nanoparticles.

3.3. Cool the samples to room temperature. Vent the chamber with dry nitrogen, open it, and remove the samples.

### REPRESENTATIVE RESULTS:

The thickness of (Gd) BCO films on both bare and LSMO decorated STO substrate was 500nm, which was measured by a surface profilometer. The film thickness was controlled by sputtering time. **Figure 1a,b** shows the AFM image of LSMO nanoparticle (sputtering time of 10 s) on 1.0 cm x 1.0 cm single-crystal STO substrates to prove that the LSMO nanoparticles grown on STO substrates uniformly. The surface and to measure the roughness of the films was characterized by atomic force microscopy (AFM) working in tapping Mode. The diameter of these LSMO nanoparticles ranged from 10 to 20 nm. Their height ranged from 20 to 50 nm. With an appropriate adjustment of deposited parameters, such as growth temperatures and target-substrate distance, different surface topography could be achieved, as shown in **Figure 1c,d**. At a low temperature (650 °C), particle and line mixed topography was obtained, as seen in **Figure 1c**. Furthermore, a small target-substrate distance (6 cm) can lead to a high density of LSMO

particles with small size (**Figure 1d**). The structure of the LSMO nanoparticles (sputtering time of 10 s) and (Gd) BCO films (**Figure 2**) was measured by X-ray diffractometer (XRD) measurement with Cu Ka radiation operated at 40 kV and 20 mA. In **Figure 3**, results are shown for two representative (Gd) BCO samples as described above: (Gd) BCO films on undecorated and LSMO decorated substrates. The superconducting transition temperature ( $T_c$ ) was close to 90.5 K for pure GBCO film and 90.3 K for LSMO/GBCO films. This nearly equal  $T_c$  value indicates LSMO nanoparticles don't harm the superconducting property ( $T_c$ ) for (Gd) BCO films. The higher slope indicate smaller  $T_c$  width for pure GBCO film compared with LSMO/GBCO films. The magnetization hysteresis loops for these two samples are plotted in **Figure 4**. By comparison, the M-H loop area is much bigger from 0 to 6 T at 30K for (Gd) BCO films fabricated on LSMO decorated substrate. The same trend is found at 50 and 77 K.

Representative J-H distributions are also shown for each sample in **Figure 5**. For a given magnetic field, these distributions are calculated as

$$J_c = 2\Delta M \times \left[ a \left( 1 - \frac{a}{3b} \right) \right]^{-1}$$

where a and b are the length and width of the tested sample. A magnetic field, which is perpendicular to the sample plane,  $a < b$ , is applied during testing process. In our case, a and b are 3 mm and 4 mm, respectively. The  $\Delta M$  symbols in the formula is the difference between upper and lower values of a magnetic hysteresis loop at the same H, as shown in **Figure 4**. The critical current density and its dependences of field help will give more information for the effect of LSMO nanoparticles on flux pinning properties. These data in **Figure 5a** suggest that the (Gd) BCO film deposited on LSMO decorated substrate possess a higher  $J_c$  value from 1.3 to 6 T at 30 K. Furthermore, as shown in **Figure 5b**, the (Gd) BCO film fabricated on LSMO decorated substrate shows a higher  $J_c$  value from 0 to 6 T at 77 K. The two phenomena in **Figure 5** suggests that an additional pinning mechanism exist in (Gd) BCO films on LSMO decorated substrates. We named it as magnetic pinning, which is due to LSMO nanoparticles deposited on the substrate.

The pinning force density was calculated by  $F_p = J_c \times B$ . The calculated result is shown in **Figure 6a,b**. There is a crossing point at 1.3T for  $F_p$  (max) value at 30K (**Figure 6a**), above which, the decorated sample has larger  $F_p$  value. The  $F_p$  (max) value at 77K moved to a higher H value (from 0.6 T to 2.5 T) for sample with decoration, which is shown in **Figure 6b**. This difference also indicates there are different pinning mechanisms for (Gd) BCO film with and without LSMO decoration.

We measured the critical current density dependence on magnetic field orientation for obtaining further interesting information on the vortex pinning properties. **Figure 7** shows the angular dependence of  $J_c$  at 0.3T and 77 K for (Gd) BCO film with and without LSMO decoration. It is found that the most prominent increase of  $J_c$  is along the c-axis. This suggests that it is more effective at a field orientation of  $H//c$  for LSMO decorated (Gd) BCO film. For explaining the phenomenon, we show a schematic in the inset of **Figure 7**, which shows threading dislocations generated at  $H//c$  direction. We believe that the threading dislocations along the c-axis in a (Gd) BCO film with LSMO decoration is responsible for this phenomenon.

## FIGURE LEGENDS:

**Figure 1: Atomic Force Microscopic image of LSMO nanoparticle decorated STO substrates. (a) 2D image, (b) 3D image, (c) 3D image of sample grown at a low temperature (650 °C), and (d) 3D image of sample grown at a small target-substrate distance (6 cm).** Reprinted with permission from previous work<sup>12</sup>. Copyright 2018 Elsevier.

**Figure 2: XRD pattern of (Gd) BCO thin films fabricated on undecorated and LSMO nanoparticle decorated STO substrates.** Reprinted with permission from previous work<sup>12</sup>. Copyright 2018 Elsevier.

**Figure 3: DC magnetization measurements of the superconducting transition  $T_c$  for (Gd) BCO thin films fabricated on undecorated and LSMO nanoparticle decorated STO substrates.** Reprinted with permission from previous work<sup>12</sup>. Copyright 2018 Elsevier.

**Figure 4: Magnetization hysteresis loops for (Gd) BCO thin films on the undecorated and LSMO nanoparticle decorated STO substrates at three different temperatures. (a) 30 K, (b) 50 K, and (c) 77 K.** Reprinted with permission from previous work<sup>12</sup>. Copyright 2018 Elsevier.

**Figure 5: Field dependence of  $J_c$  (the critical current density) for (Gd) BCO thin films on undecorated and LSMO decorated STO substrates at (a) 30 K and (b) 77 K.** Reprinted with permission from previous work<sup>12</sup>. Copyright 2018 Elsevier.

**Figure 6: Variation of  $F_p$  as a function of the applied magnetic field for (Gd)BCO films deposited on undecorated and LSMO-nanoparticle-decorated STO substrates. (a) 30 K and (b) 77 K.** Reprinted with permission from previous work<sup>12</sup>. Copyright 2018 Elsevier.

**Figure 7: Dependence of  $J_c$  at 0.3 T and 77 K on orientation of the applied magnetic field, relative to the film's normal direction.** The inset shows the schematic diagram of threading dislocations generated along the c-axis in the LSMO decorated (Gd) BCO thin film. Reprinted with permission from previous work<sup>12</sup>. Copyright 2018 Elsevier.

**Figure S1: Picture of the RF sputtering system**

## DISCUSSION:

Here we have demonstrated that this method can be used to prepare LSMO ferromagnetic nanoparticles of uniform distribution on  $\text{SrTiO}_3$  (STO) single-crystal substrates. The (Gd) BCO films also can be deposited on both bare and LSMO decorated STO substrate. With an appropriate adjustment of deposited parameters, such as growth temperatures and target-substrate distance, this method ought to be useful for deposited different kinds of magnetic and non-magnetic particles or layers, for example,  $\text{CeO}_2$ , YSZ (yttrium-stabilized zirconia)<sup>24</sup>, and ITO (Indium tin oxide).

A critical step in the protocol is the sputtering time for deposition of LSMO particles. In the

protocol, the proper sputtering time is needed. If the sputtering time is too long, this will form continuous LSMO thin film not nanoparticles. On the other hand, if the sputtering time is too short, the density of LSMO nanoparticles is not enough and it will affect current carrying ability for top GBCO films. For GBCO films, in order to achieve epitaxy, the use of a single crystal substrate is needed. In our case, LSMO nanoparticles do not need to achieve epitaxy, but just need greater density and the proper size to enhance top GBCO superconducting properties. In this report, sputtering times are used to control the different morphology for LSMO nanoparticles.

One drawback of our deposition chamber is that because there is no *in situ* QCM (quartz crystal microbalance) sensor, we cannot monitor in real time the film thickness and deposition during the growth process. In our case, the thickness of GBCO films can be controlled by sputtering times. The deposition rate of the GBCO films presented here is about 15 nm/min. Finally, as mentioned in the introduction, the fabrication of LSMO nanoparticles has been successfully achieved by either metal organic decomposition methods (MOD) or pulsed laser deposition methods (PLD). The PLD method possesses slower deposition rates and involves a larger investment, while the MOD method results uniform particle distribution and low reproduction. Concerning the RF sputtering deposition, it can provide particles with uniform distribution and lower investment with respect to PLD method. Also, this nanoparticle deposition procedure can be scaled-up to coat larger surfaces easily.

In conclusion, we demonstrate a RF sputtering method with which to create ferromagnetic LSMO nanoparticles on STO substrate, and GBCO superconducting films on bare and LSMO decorated STO substrate. These ferromagnetic LSMO nanoparticles have never been synthesized by RF sputtering deposition before. This RF sputtering method can coat nanoparticles uniformly on SrTiO<sub>3</sub> (STO) single-crystal substrates or high textured substrates with different particle density and size<sup>17,25</sup>. This feature allows for future application of RF sputtering ferromagnetic nanoparticles in electronics devices on single-crystal substrates or flexible and highly textured substrates.

#### ACKNOWLEDGMENTS:

This work was supported by the National Natural Science Foundation of China (No. 51502168; No.11504227) and the Shanghai Municipal Natural Science Foundation (No.16ZR1413600).The authors gratefully thank the Instrumental Analysis Center of Shanghai Jiao Tong University and Ma-tek analytical lab for competent technical assistance.

#### DISCLOSURES:

The authors have nothing to disclose.

#### REFERENCES:

- 1 Gong, J., Zheng, D., Li, D., Jin, C. & Bai, H. Lattice distortion modified anisotropic magnetoresistance in epitaxial La<sub>0.67</sub>Sr<sub>0.33</sub>MnO<sub>3</sub> thin films. *Journal of Alloys and Compounds*. **735**, 1152-1157, doi:<https://doi.org/10.1016/j.jallcom.2017.11.221>, (2018).
- 2 Wang, J., Han, Z., Bai, J., Luo, B. & Chen, C. Magnetoelectric coupling in oxygen deficient



- La0.67Sr0.33MnO3- $\delta$ /BaTiO3 composite film. *Physica B: Condensed Matter*. **534**, 141-144, doi:<https://doi.org/10.1016/j.physb.2018.01.051>, (2018).
- 3 Duan, Z. *et al.* Facile fabrication of micro-patterned LSMO films with unchanged magnetic properties by photosensitive sol-gel method on LaAlO3 substrates. *Ceramics International*. **42** (12), 14100-14106, doi:<https://doi.org/10.1016/j.ceramint.2016.06.021>, (2016).
  - 4 Xu, P., Huffman, T. J., Kwak, I. H., Biswas, A. & Qazilbash, M. M. Temperature dependent infrared nano-imaging of La0.67Sr0.33MnO3 thin film. *Journal of Physics-Condensed Matter*. **30** (2), doi:10.1088/1361-648X/aa9c65, (2018).
  - 5 Bulaevskii, L. N., Chudnovsky, E. M. & Maley, M. P. Magnetic pinning in superconductor-ferromagnet multilayers. *Applied Physics Letters*. **76** (18), 2594-2596, doi:<http://dx.doi.org/10.1063/1.126419>, (2000).
  - 6 Chen, C. Z. *et al.* Flux pinning of stress-induced magnetic inhomogeneity in the bilayers of YBa2Cu3O7- $\delta$ /La0.67Sr0.33MnO3- $\delta$ . *Journal of Applied Physics*. **106** (9), 093902, doi:<http://dx.doi.org/10.1063/1.3253751>, (2009).
  - 7 Chen, C. Z. *et al.* Robust high-temperature magnetic pinning induced by proximity in YBa2Cu3O7- $\delta$ /La0.67Sr0.33MnO3 hybrids. *Journal of Applied Physics*. **109** (7), 073921, doi: <http://dx.doi.org/10.1063/1.3573491>, (2011).
  - 8 Huang, J. *et al.* Magnetic properties of (CoFe2O4)x:(CeO2)1-x vertically aligned nanocomposites and their pinning properties in YBa2Cu3O7- $\delta$  thin films. *Journal of Applied Physics*. **115** (12), 123902, doi: <http://dx.doi.org/10.1063/1.4869217>, (2014).
  - 9 Lange, M., Bael, M. J. V., Bruynseraede, Y. & Moshchalkov, V. V. Nanoengineered Magnetic-Field-Induced Superconductivity. *Physical Review Letters*. **90** (19), 197006 (2003).
  - 10 Rakshit, R. K., Budhani, R. C., Bhuvana, T., Kulkarni, V. N. & Kulkarni, G. U. Inhomogeneous vortex-state-driven enhancement of superconductivity in nanoengineered ferromagnet-superconductor heterostructures. *Physical Review B*. **77** (5), 052509 (2008).
  - 11 Guo, H. & Ward, T. Z. Fabrication of Spatially Confined Complex Oxides. *Journal of Visualized Experiments*. **77**, e50573, doi:10.3791/50573, (2013).
  - 12 Wang, Y., Li, Y., Liu, L. & Xu, D. Improvement of flux pinning in GdBa2Cu3O7- $\delta$  thin film by nanoscale ferromagnetic La0.67Sr0.33MnO3 pretreatment of substrate surface. *Ceramics International*. **44** (1), 225-230, doi:10.1016/j.ceramint.2017.09.162, (2018).
  - 13 Martín, J. I., Vélez, M., Nogués, J. & Schuller, I. K. Flux Pinning in a Superconductor by an Array of Submicrometer Magnetic Dots. *Physical Review Letters*. **79** (10), 1929-1932 (1997).
  - 14 Morgan, D. J. & Ketterson, J. B. Asymmetric Flux Pinning in a Regular Array of Magnetic Dipoles. *Physical Review Letters*. **80** (16), 3614-3617 (1998).
  - 15 Gutierrez, J. *et al.* Anisotropic c-axis pinning in interfacial self-assembled nanostructured trifluoroacetate-YBa2Cu3O7-x films. *Applied Physics Letters*. **94** (17), 172513, doi:<http://dx.doi.org/10.1063/1.3130085>, (2009).
  - 16 Tran, D. H. *et al.* Enhanced critical current density in GdBa2Cu3O7- $\delta$  thin films with substrate surface decoration using Gd2O3 nanoparticles. *Thin Solid Films*. **526** (0), 241-245, doi:<http://dx.doi.org/10.1016/j.tsf.2012.11.013>, (2012).
  - 17 Jha, A. K., Khare, N. & Pinto, R. Interface engineering using ferromagnetic nanoparticles

for enhancing pinning in YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub> thin film. *Journal of Applied Physics*. **110** (11), doi:10.1063/1.3665874, (2011).

18 Casotti, D. *et al.* Ageing effects on electrical resistivity of Nb-doped TiO<sub>2</sub> thin films deposited at a high rate by reactive DC magnetron sputtering. *Applied Surface Science*. **455**, 267-275, doi:10.1016/j.apsusc.2018.05.068, (2018).

19 Li, Y. *et al.* Preparation of single-phase Ti<sub>2</sub>AlN coating by magnetron sputtering with cost-efficient hot-pressed Ti-Al-N targets. *Ceramics International*. **44** (14), 17530-17534, doi:10.1016/j.ceramint.2018.06.055, (2018).

20 Mahdhi, H., Djessas, K. & Ben Ayadi, Z. Synthesis and characteristics of Ca-doped ZnO thin films by rf magnetron sputtering at low temperature. *Materials Letters*. **214**, 10-14, doi:<https://doi.org/10.1016/j.matlet.2017.11.108>, (2018).

21 Shen, H., Wei, B., Zhang, D., Qi, Z. & Wang, Z. Magnetron sputtered NbN thin film electrodes for supercapacitors. *Materials Letters*. **229**, 17-20, doi:10.1016/j.matlet.2018.06.052, (2018).

22 Sinnarasa, I. *et al.* Influence of thickness and microstructure on thermoelectric properties of Mg-doped CuCrO<sub>2</sub> delafossite thin films deposited by RF-magnetron sputtering. *Applied Surface Science*. **455**, 244-250, doi:10.1016/j.apsusc.2018.05.104, (2018).

23 Thi-Thuy-Nga, N., Chen, Y.-H., Chen, Z.-M., Cheng, K.-B. & He, J.-L. Microstructure, near infrared reflectance, and surface temperature of Ti-O coated polyethylene terephthalate fabrics prepared by roll-to-roll high power impulse magnetron sputtering system. *Thin Solid Films*. **663**, 1-8, doi:10.1016/j.tsf.2018.08.003, (2018).

24 Wang, Y., Xu, D., Li, Y. & Liu, L. Texture and morphology developments of Yttria-stabilized zirconia (YSZ) buffer layer for coated conductors by RF sputtering. *Surface & Coatings Technology*. **232**, 497-503, doi:10.1016/j.surfcoat.2013.06.008, (2013).

25 Petrisor, T., Jr. *et al.* Magnetic pinning effects of epitaxial La<sub>x</sub>Sr<sub>1-x</sub>MnO<sub>3</sub> nanostructured thin films on YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub> layers. *Journal of Applied Physics*. **112** (5), 053919-1-053919-7, doi:10.1063/1.4748049, (2012).

Figure 1

[Click here to access/download;Figure;Figure 1 \(revised 2\).tif.tif](#)

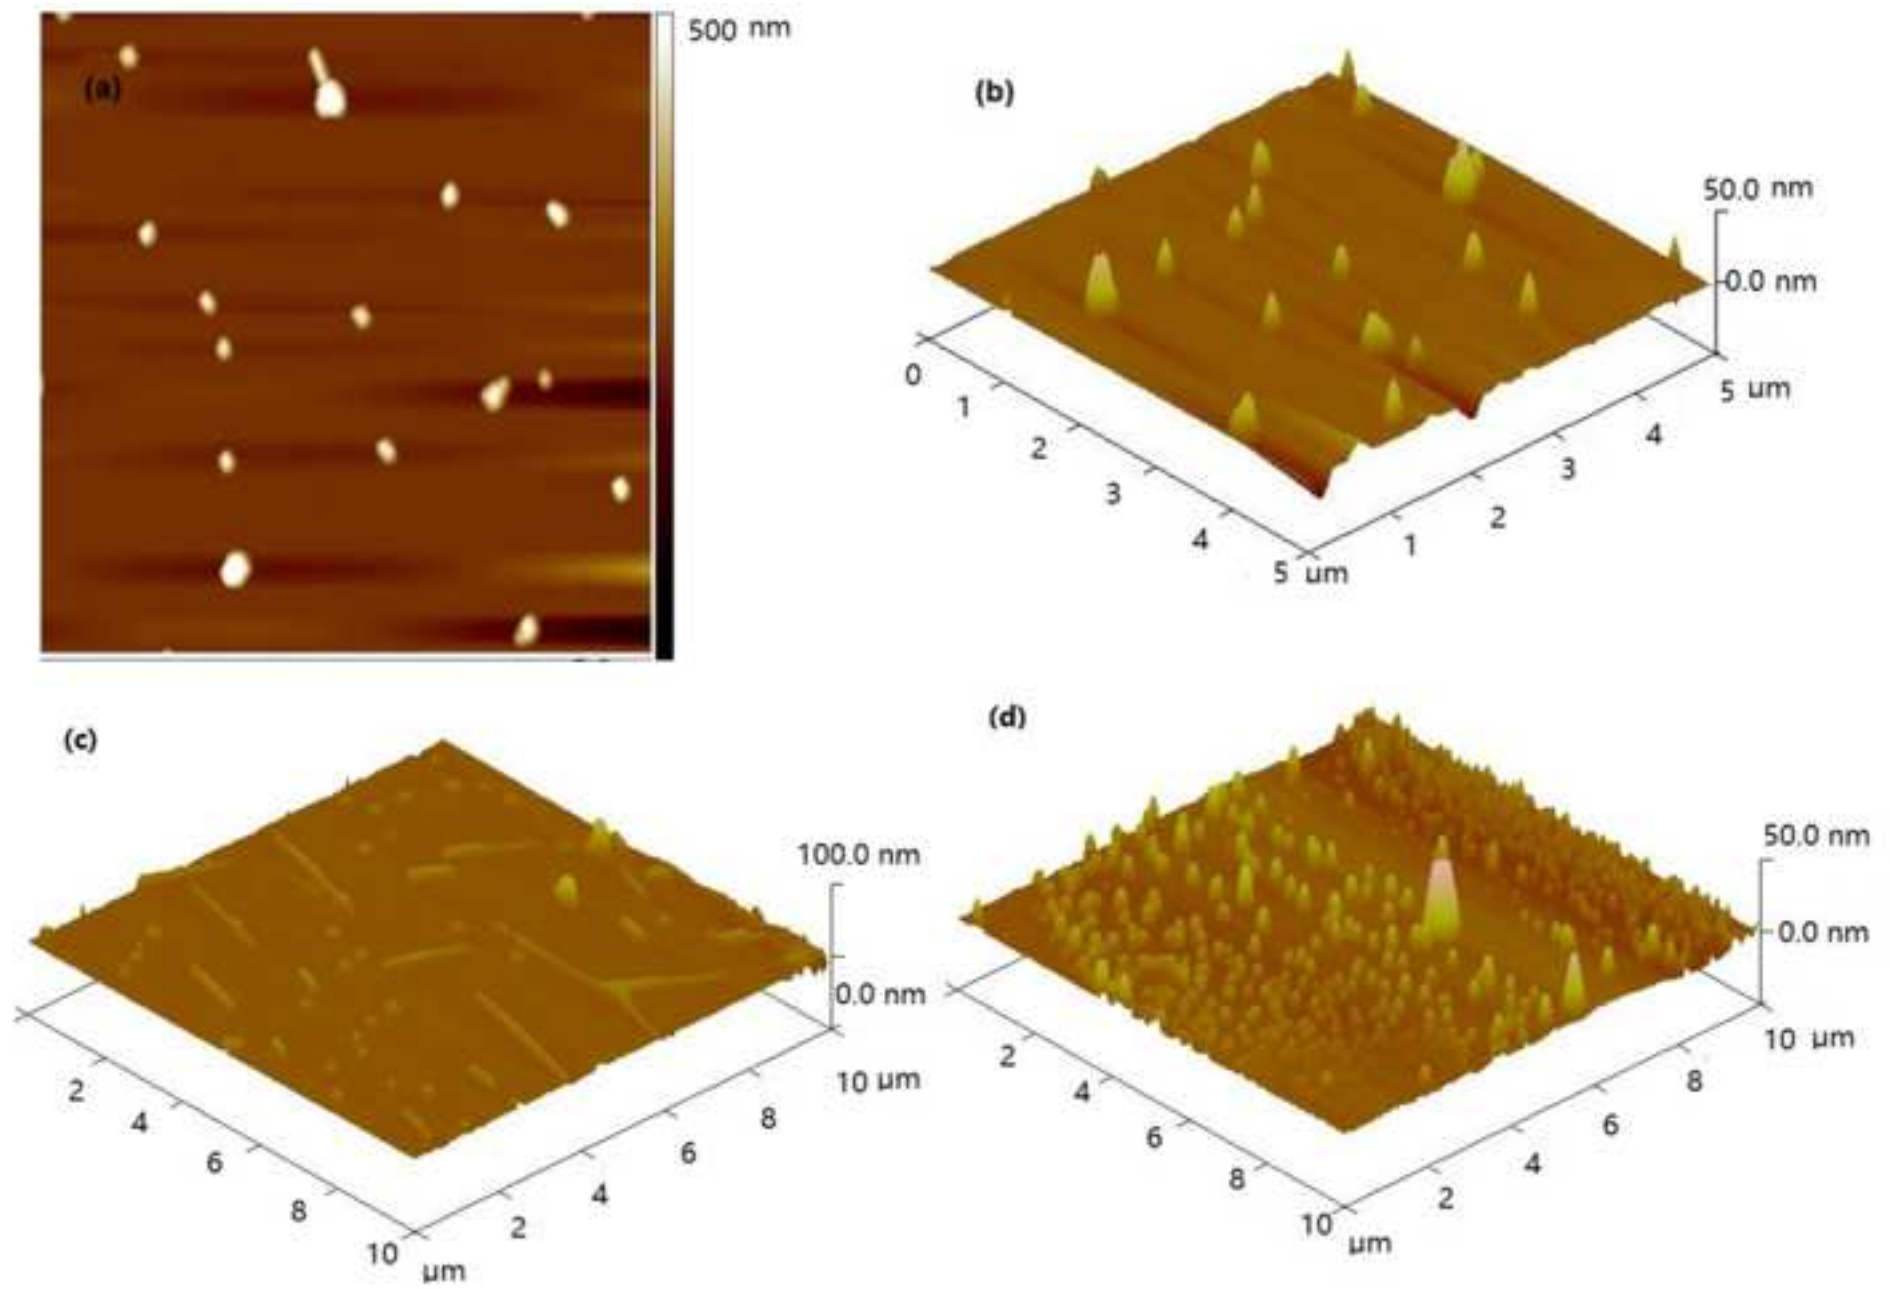


Figure 2

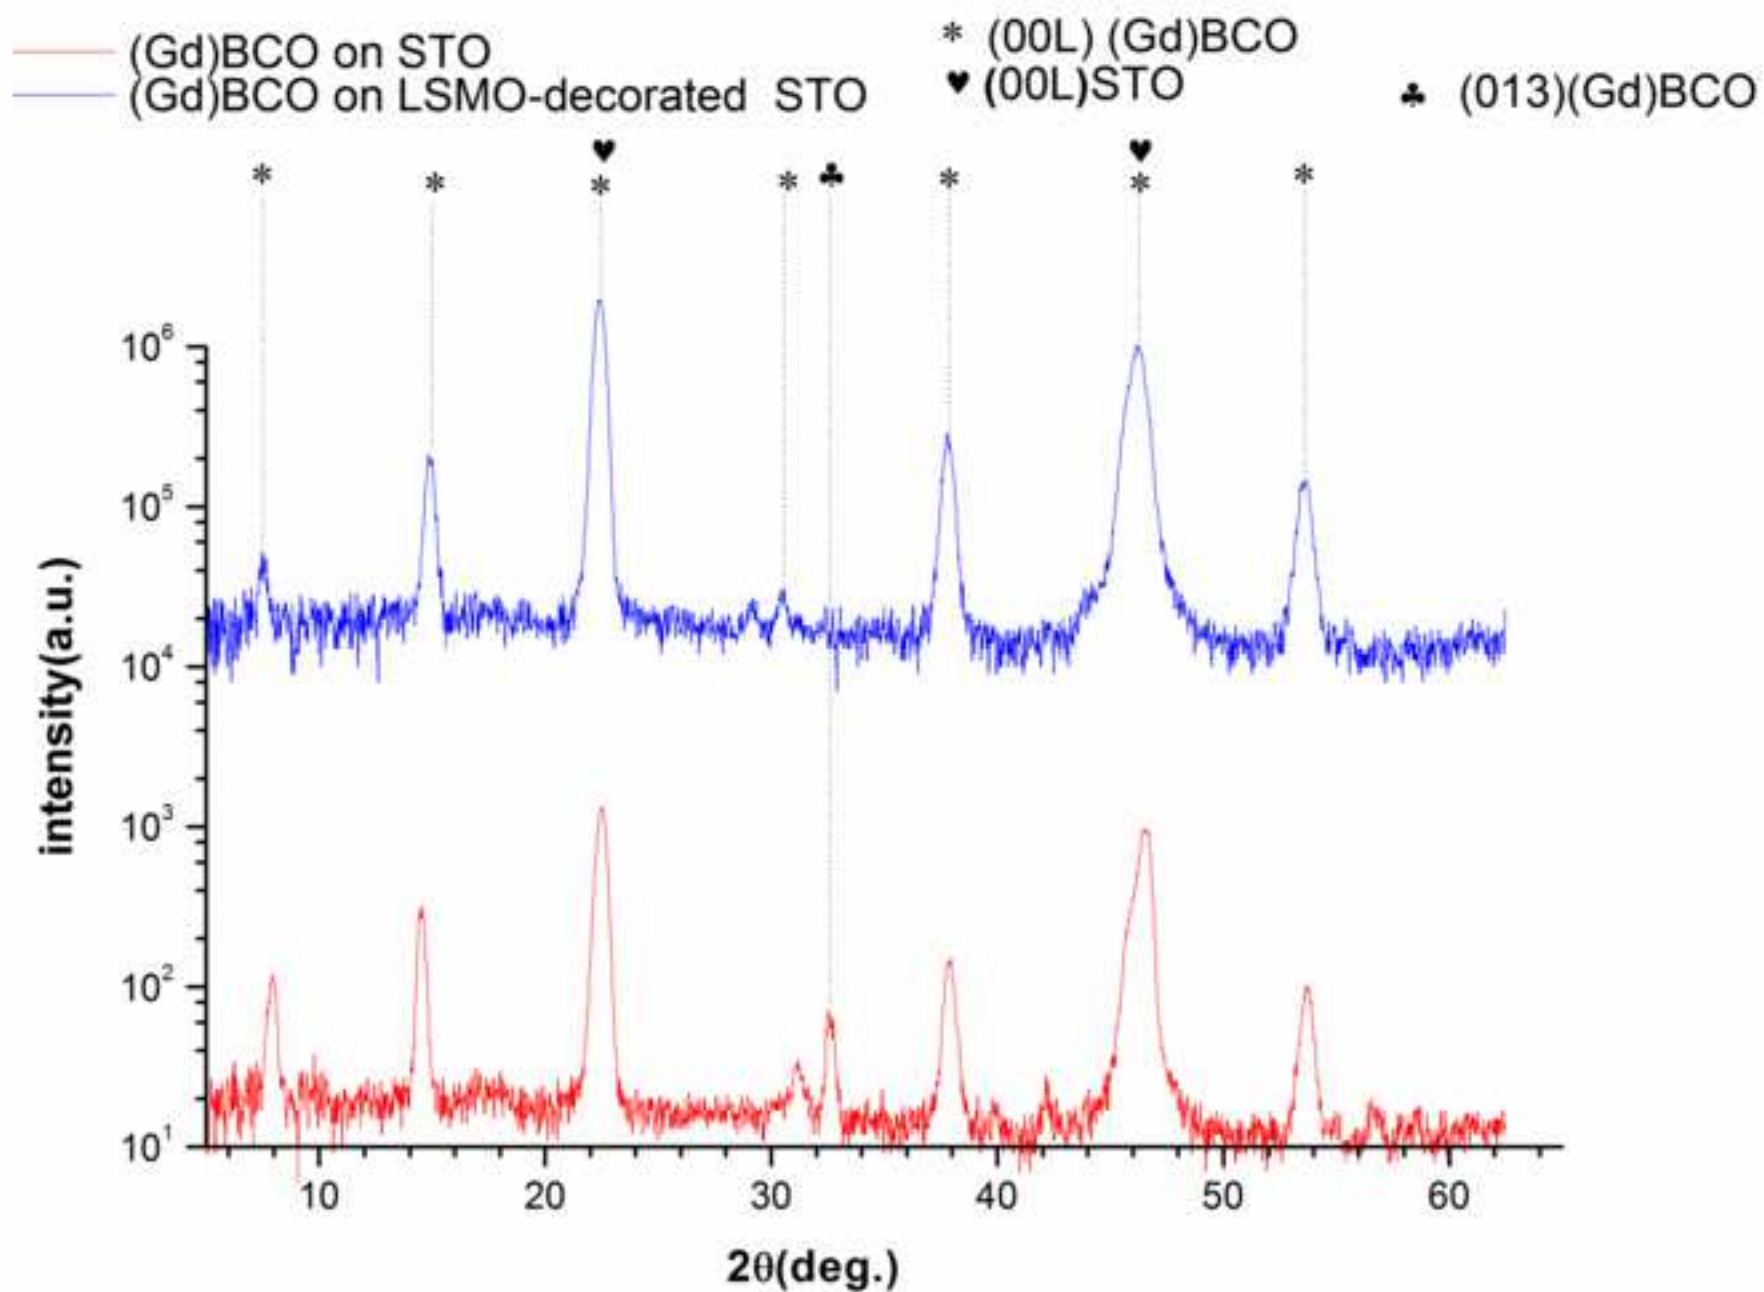


Figure 3

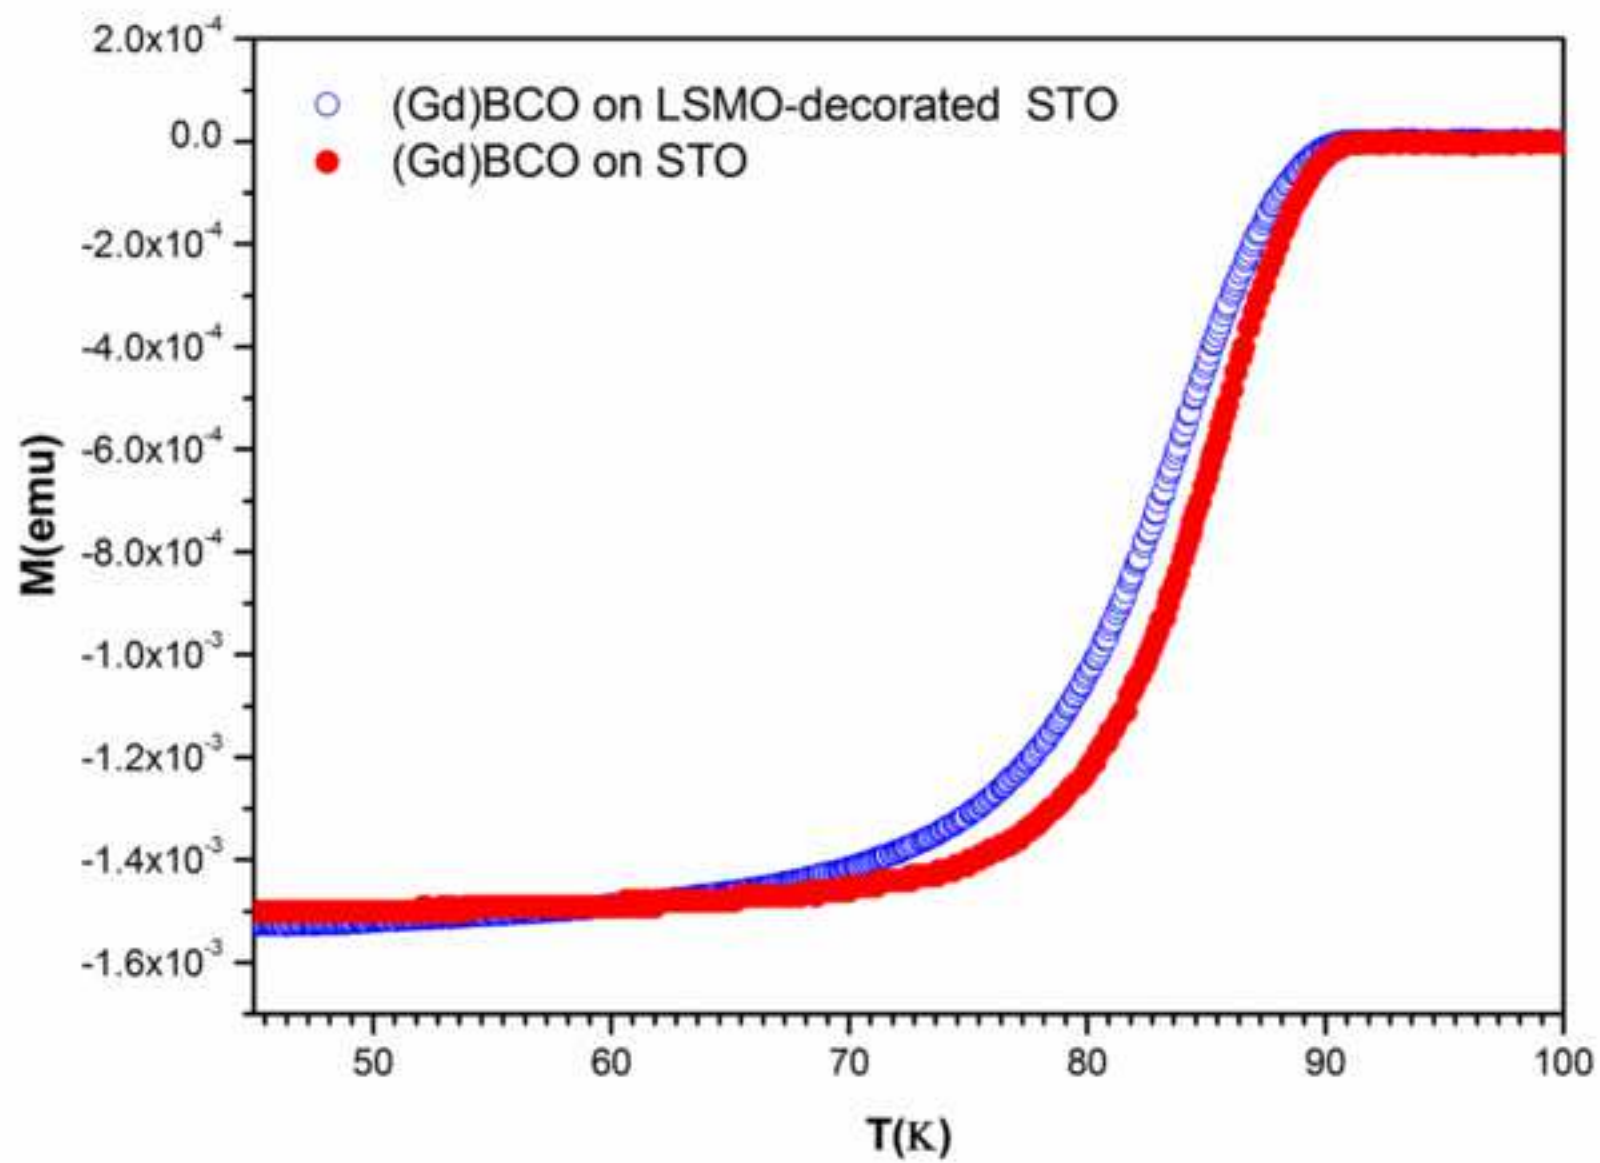


Figure 4




[Click here to access/download;Figure;Fig4 .tiff.tif](#)

Figure 5







Figure 6

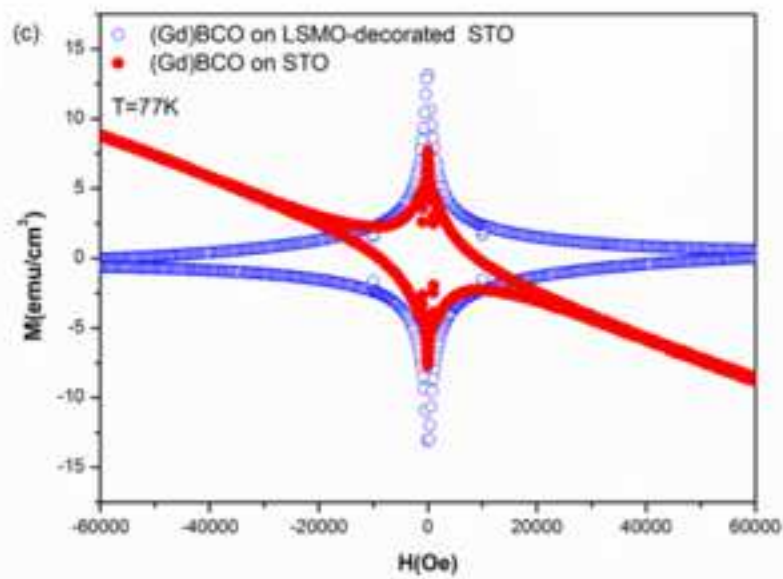
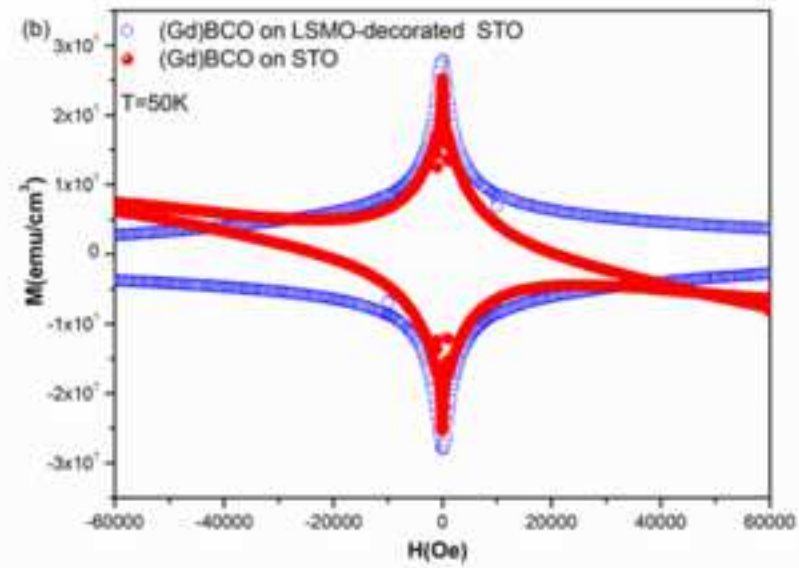
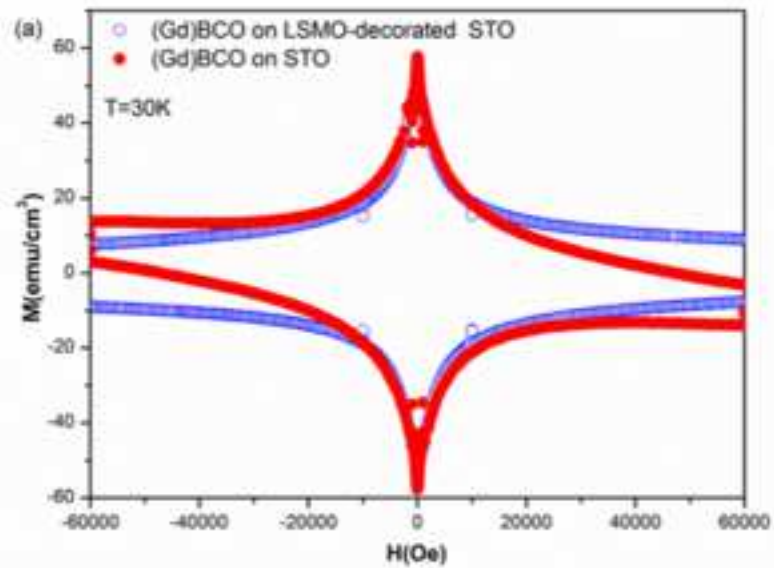


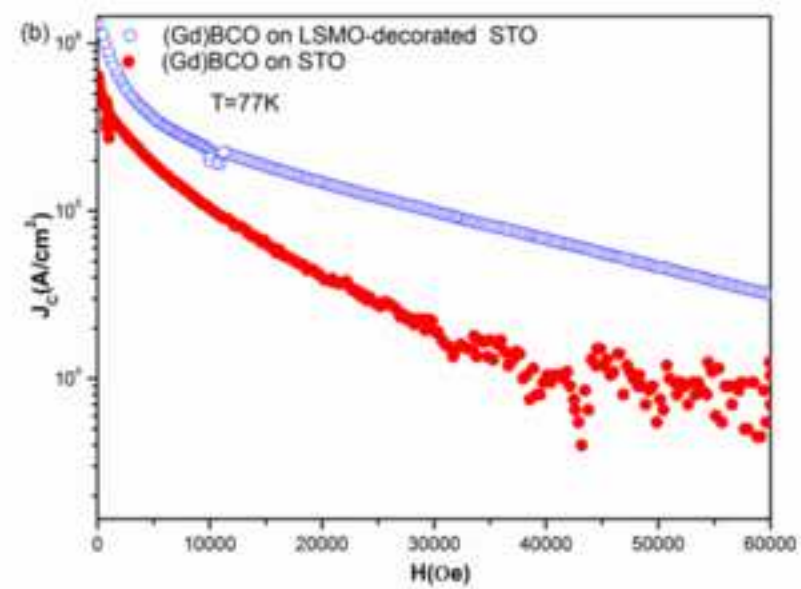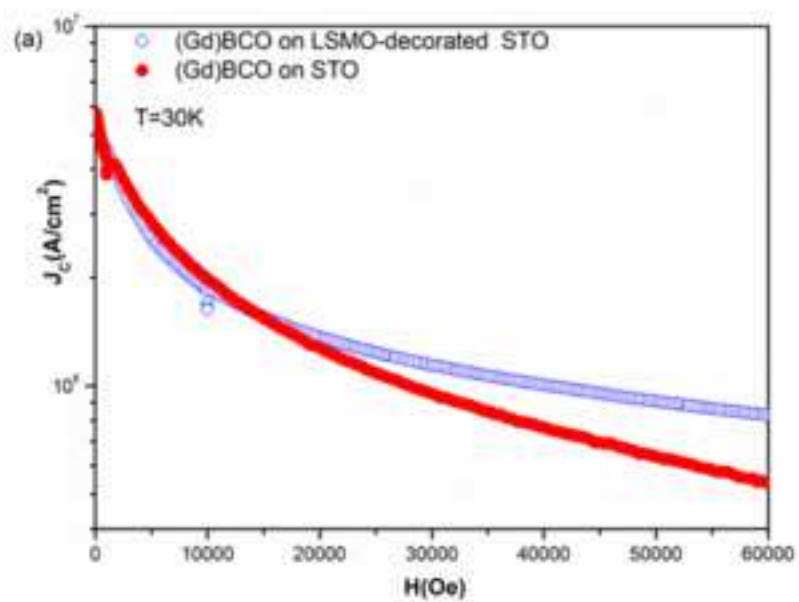

Figure 7



Name of Material/ Equipment	Company	Catalog Number	Comments/Description
Sputter Deposition System	Shenyang scientific instruments Limited by Share Ltd	Bespoke	
SrTiO <sub>3</sub> Single Crystal Substrate	Hefei Kejing crystal material technology Co., Ltd	Single-sided epi-polished	(001) orientation
La <sub>0.67</sub> Sr <sub>0.33</sub> MnO <sub>3</sub> sputtering target	Hefei Kejing crystal material technology Co., Ltd	Bespoke	60 mm diameter
GdBa <sub>2</sub> Cu <sub>3</sub> O <sub>7-δ</sub> sputtering target	Hefei Kejing crystal material technology Co., Ltd	Bespoke	60 mm diameter
Atomic Force Microscope	Brüker	Dimension Icon	
X-ray Diffractometer	Brüker	D8 Discover	
Physical Property Measurement System	Quantum Design	PPMS 9	

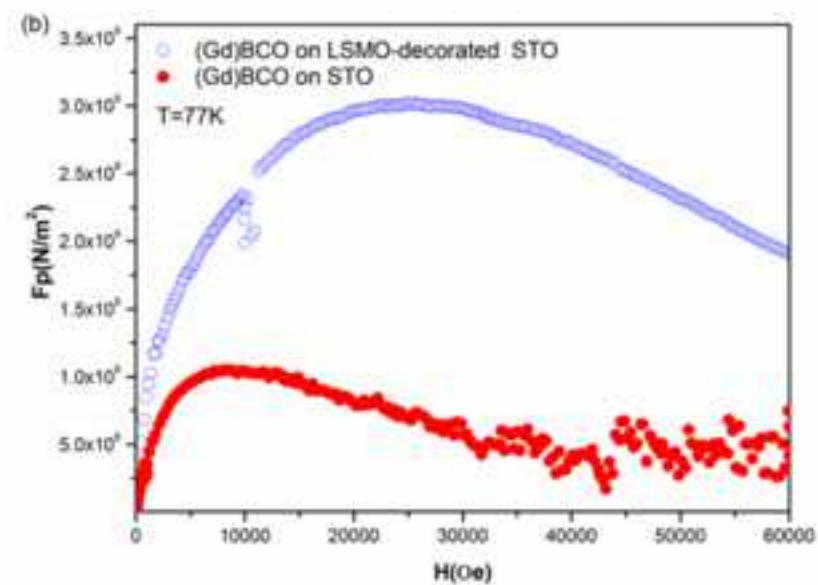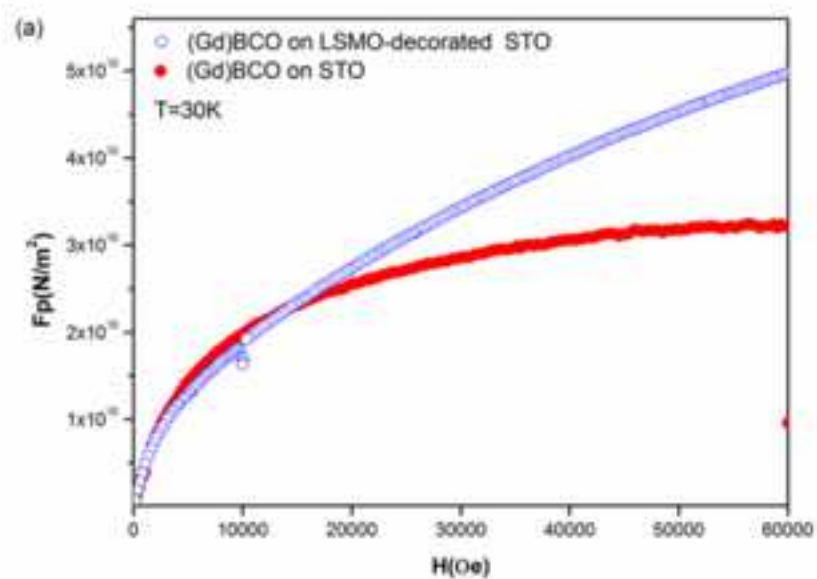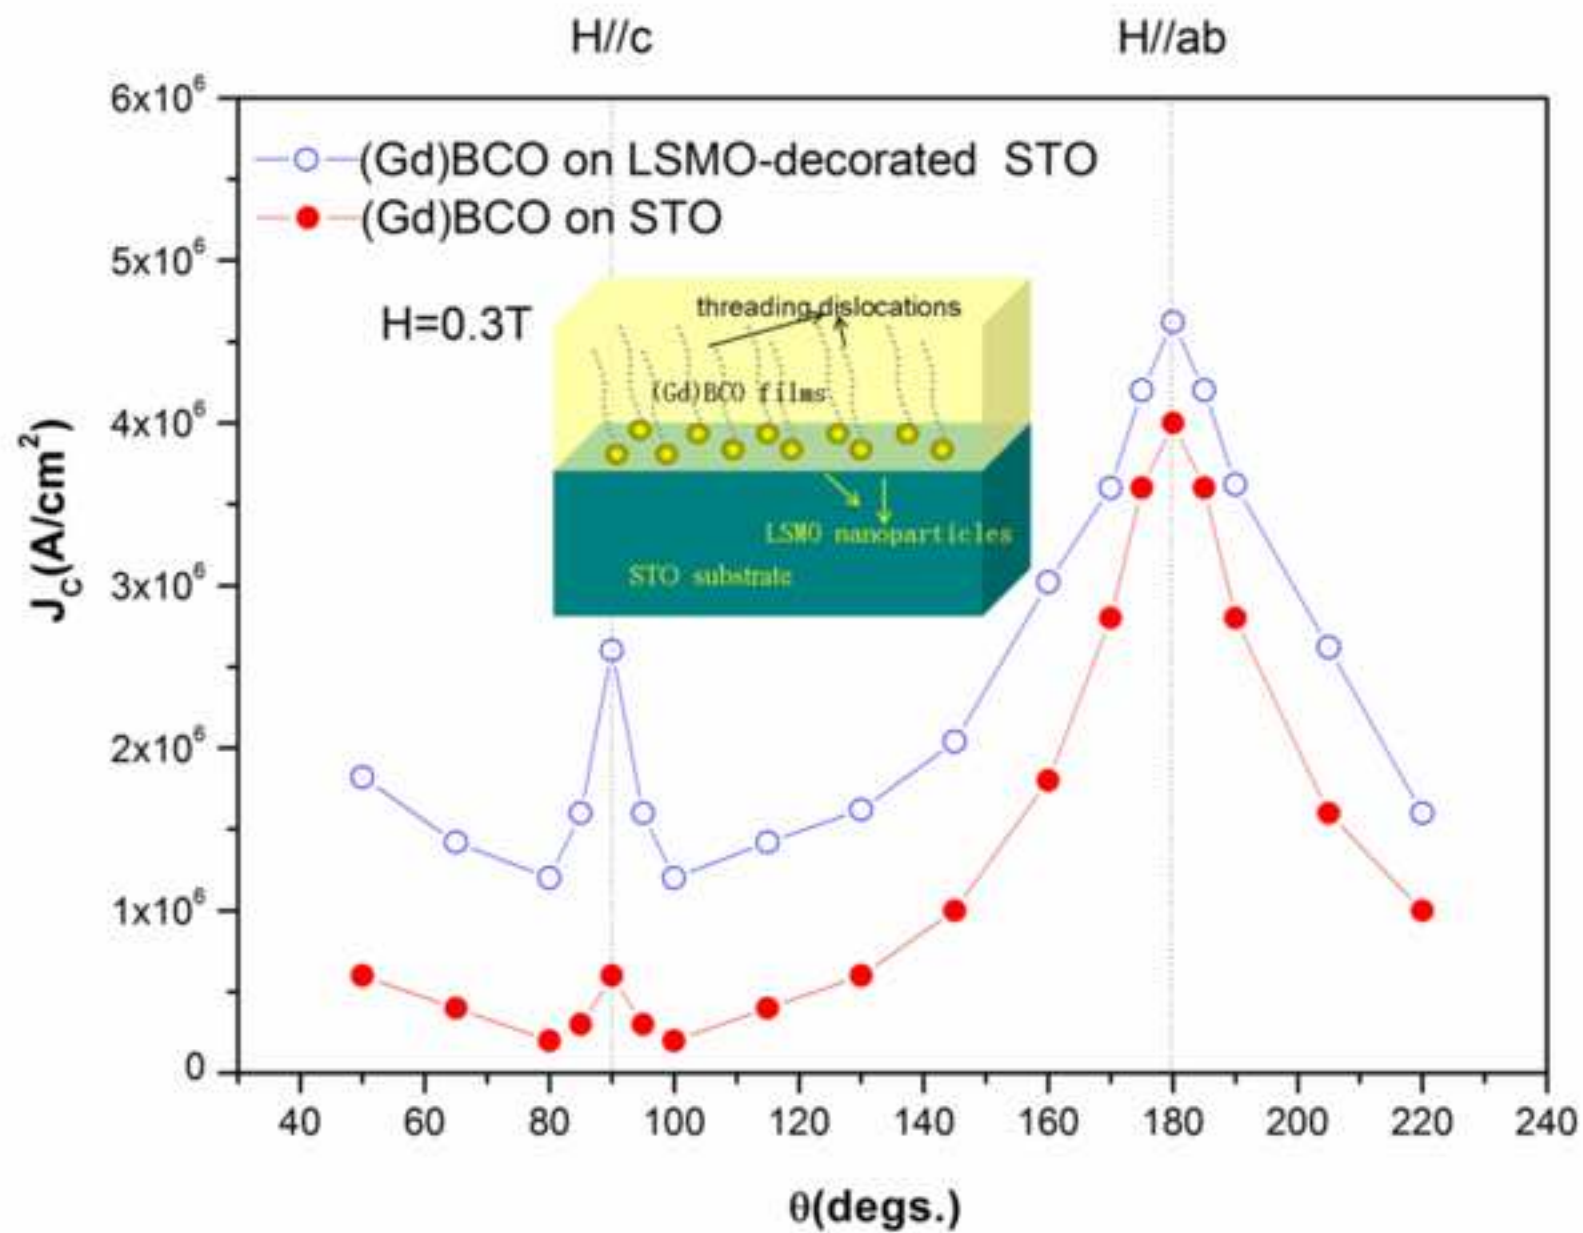

1 Alewife Center #200  
Cambridge, MA 02140  
tel. 617.945.9051  
www.jove.com

## ARTICLE AND VIDEO LICENSE AGREEMENT

Title of Article:

RF magnetron sputtering of  $\text{GdBa}_2\text{Cu}_3\text{O}_{7-x}$  /  $\text{La}_{0.67}\text{Sr}_{0.33}\text{MnO}_3$  Quasi-bilayer films on  $\text{SrTiO}_3$  (STO) single-crystal substrates

Author(s):

Ying Wang<sup>1, 2\*</sup>, Yijie Li<sup>2</sup>, Linfei Liu<sup>2</sup>, Da Xu<sup>2</sup>, Xiaojing Luo Xu<sup>1</sup>

Item 1 (check one box): The Author elects to have the Materials be made available (as described at

<http://www.jove.com/author>) via: ☐ Standard Access ☐ Open Access

Item 2 (check one box):

- ☐ The Author is NOT a United States government employee.
- ☐ The Author is a United States government employee and the Materials were prepared in the course of his or her duties as a United States government employee.
- ☐ The Author is a United States government employee but the Materials were NOT prepared in the course of his or her duties as a United States government employee.

### ARTICLE AND VIDEO LICENSE AGREEMENT

1. **Defined Terms.** As used in this Article and Video License Agreement, the following terms shall have the following meanings: “**Agreement**” means this Article and Video License Agreement; “**Article**” means the article specified on the last page of this Agreement, including any associated materials such as texts, figures, tables, artwork, abstracts, or summaries contained therein; “**Author**” means the author who is a signatory to this Agreement; “**Collective Work**” means a work, such as a periodical issue, anthology or encyclopedia, in which the Materials in their entirety in unmodified form, along with a number of other contributions, constituting separate and independent works in themselves, are assembled into a collective whole; “**CRC License**” means the Creative Commons Attribution-Non Commercial-No Derivs 3.0 Unported Agreement, the terms and conditions of which can be found at: <http://creativecommons.org/licenses/by-nc-nd/3.0/legalcode>; “**Derivative Work**” means a work based upon the Materials or upon the Materials and other pre-existing works, such as a translation, musical arrangement, dramatization, fictionalization, motion picture version, sound recording, art reproduction, abridgment, condensation, or any other form in which the Materials may be recast, transformed, or adapted; “**Institution**” means the institution, listed on the last page of this Agreement, by which the Author was employed at the time of the creation of the Materials; “**JOVE**” means MyJove Corporation, a Massachusetts corporation and the publisher of *The Journal of Visualized Experiments*; “**Materials**” means the Article and / or the Video; “**Parties**” means the Author and JOVE; “**Video**” means any video(s) made by the Author, alone or in conjunction with any other parties, or by JOVE or its affiliates or agents, individually or in collaboration with the Author or any other parties, incorporating all or any portion of the Article, and in which the Author may or may not appear.

2. **Background.** The Author, who is the author of the Article, in order to ensure the dissemination and protection of the Article, desires to have the JOVE publish the Article and create and transmit videos based on the Article. In furtherance of such goals, the Parties desire to memorialize in this Agreement the respective rights of each Party in and to the Article and the Video.

3. **Grant of Rights in Article.** In consideration of JOVE agreeing to publish the Article, the Author hereby grants to JOVE, subject to **Sections 4** and **7** below, the exclusive, royalty-free, perpetual (for the full term of copyright in the Article, including any extensions thereto) license (a) to publish, reproduce, distribute, display and store the Article in all forms, formats and media whether now known or hereafter developed (including without limitation in print, digital and electronic form) throughout the world, (b) to translate the Article into other languages, create adaptations, summaries or extracts of the Article or other Derivative Works (including, without limitation, the Video) or Collective Works based on all or any portion of the Article and exercise all of the rights set forth in (a) above in such translations, adaptations, summaries, extracts, Derivative Works or Collective Works and (c) to license others to do any or all of the above. The foregoing rights may be exercised in all media and formats, whether now known or hereafter devised, and include the right to make such modifications as are technically necessary to exercise the rights in other media and formats. If the “Open Access” box has been checked in **Item 1** above, JOVE and the Author hereby grant to the public all such rights in the Article as provided in, but subject to all limitations and requirements set forth in, the CRC License.

## ARTICLE AND VIDEO LICENSE AGREEMENT

4. Retention of Rights in Article. Notwithstanding the exclusive license granted to JoVE in **Section 3** above, the Author shall, with respect to the Article, retain the non-exclusive right to use all or part of the Article for the non-commercial purpose of giving lectures, presentations or teaching classes, and to post a copy of the Article on the Institution's website or the Author's personal website, in each case provided that a link to the Article on the JoVE website is provided and notice of JoVE's copyright in the Article is included. All non-copyright intellectual property rights in and to the Article, such as patent rights, shall remain with the Author.

5. Grant of Rights in Video – Standard Access. This **Section 5** applies if the "Standard Access" box has been checked in **Item 1** above or if no box has been checked in **Item 1** above. In consideration of JoVE agreeing to produce, display or otherwise assist with the Video, the Author hereby acknowledges and agrees that, Subject to **Section 7** below, JoVE is and shall be the sole and exclusive owner of all rights of any nature, including, without limitation, all copyrights, in and to the Video. To the extent that, by law, the Author is deemed, now or at any time in the future, to have any rights of any nature in or to the Video, the Author hereby disclaims all such rights and transfers all such rights to JoVE.

6. Grant of Rights in Video – Open Access. This **Section 6** applies only if the "Open Access" box has been checked in **Item 1** above. In consideration of JoVE agreeing to produce, display or otherwise assist with the Video, the Author hereby grants to JoVE, subject to **Section 7** below, the exclusive, royalty-free, perpetual (for the full term of copyright in the Article, including any extensions thereto) license (a) to publish, reproduce, distribute, display and store the Video in all forms, formats and media whether now known or hereafter developed (including without limitation in print, digital and electronic form) throughout the world, (b) to translate the Video into other languages, create adaptations, summaries or extracts of the Video or other Derivative Works or Collective Works based on all or any portion of the Video and exercise all of the rights set forth in (a) above in such translations, adaptations, summaries, extracts, Derivative Works or Collective Works and (c) to license others to do any or all of the above. The foregoing rights may be exercised in all media and formats, whether now known or hereafter devised, and include the right to make such modifications as are technically necessary to exercise the rights in other media and formats. For any Video to which this Section 6 is applicable, JoVE and the Author hereby grant to the public all such rights in the Video as provided in, but subject to all limitations and requirements set forth in, the CRC License.

7. Government Employees. If the Author is a United States government employee and the Article was prepared in the course of his or her duties as a United States government employee, as indicated in **Item 2** above, and any of the licenses or grants granted by the Author hereunder exceed the scope of the 17 U.S.C. 403, then the rights granted hereunder shall be limited to the maximum rights permitted under such

statute. In such case, all provisions contained herein that are not in conflict with such statute shall remain in full force and effect, and all provisions contained herein that do so conflict shall be deemed to be amended so as to provide to JoVE the maximum rights permissible within such statute.

8. Likeness, Privacy, Personality. The Author hereby grants JoVE the right to use the Author's name, voice, likeness, picture, photograph, image, biography and performance in any way, commercial or otherwise, in connection with the Materials and the sale, promotion and distribution thereof. The Author hereby waives any and all rights he or she may have, relating to his or her appearance in the Video or otherwise relating to the Materials, under all applicable privacy, likeness, personality or similar laws.

9. Author Warranties. The Author represents and warrants that the Article is original, that it has not been published, that the copyright interest is owned by the Author (or, if more than one author is listed at the beginning of this Agreement, by such authors collectively) and has not been assigned, licensed, or otherwise transferred to any other party. The Author represents and warrants that the author(s) listed at the top of this Agreement are the only authors of the Materials. If more than one author is listed at the top of this Agreement and if any such author has not entered into a separate Article and Video License Agreement with JoVE relating to the Materials, the Author represents and warrants that the Author has been authorized by each of the other such authors to execute this Agreement on his or her behalf and to bind him or her with respect to the terms of this Agreement as if each of them had been a party hereto as an Author. The Author warrants that the use, reproduction, distribution, public or private performance or display, and/or modification of all or any portion of the Materials does not and will not violate, infringe and/or misappropriate the patent, trademark, intellectual property or other rights of any third party. The Author represents and warrants that it has and will continue to comply with all government, institutional and other regulations, including, without limitation all institutional, laboratory, hospital, ethical, human and animal treatment, privacy, and all other rules, regulations, laws, procedures or guidelines, applicable to the Materials, and that all research involving human and animal subjects has been approved by the Author's relevant institutional review board.

10. JoVE Discretion. If the Author requests the assistance of JoVE in producing the Video in the Author's facility, the Author shall ensure that the presence of JoVE employees, agents or independent contractors is in accordance with the relevant regulations of the Author's institution. If more than one author is listed at the beginning of this Agreement, JoVE may, in its sole discretion, elect not take any action with respect to the Article until such time as it has received complete, executed Article and Video License Agreements from each such author. JoVE reserves the right, in its absolute and sole discretion and without giving any reason therefore, to accept or decline any work submitted to JoVE. JoVE and its employees, agents and independent contractors shall have

## ARTICLE AND VIDEO LICENSE AGREEMENT

full, unfettered access to the facilities of the Author or of the Author's institution as necessary to make the Video, whether actually published or not. JoVE has sole discretion as to the method of making and publishing the Materials, including, without limitation, to all decisions regarding editing, lighting, filming, timing of publication, if any, length, quality, content and the like.

11. **Indemnification.** The Author agrees to indemnify JoVE and/or its successors and assigns from and against any and all claims, costs, and expenses, including attorney's fees, arising out of any breach of any warranty or other representations contained herein. The Author further agrees to indemnify and hold harmless JoVE from and against any and all claims, costs, and expenses, including attorney's fees, resulting from the breach by the Author of any representation or warranty contained herein or from allegations or instances of violation of intellectual property rights, damage to the Author's or the Author's institution's facilities, fraud, libel, defamation, research, equipment, experiments, property damage, personal injury, violations of institutional, laboratory, hospital, ethical, human and animal treatment, privacy or other rules, regulations, laws, procedures or guidelines, liabilities and other losses or damages related in any way to the submission of work to JoVE, making of videos by JoVE, or publication in JoVE or elsewhere by JoVE. The Author shall be responsible for, and shall hold JoVE harmless from, damages caused by lack of sterilization, lack of cleanliness or by contamination due to the making of a video by JoVE its employees, agents or independent contractors. All sterilization, cleanliness or decontamination procedures shall be solely the responsibility of the Author and shall be undertaken at the Author's

expense. All indemnifications provided herein shall include JoVE's attorney's fees and costs related to said losses or damages. Such indemnification and holding harmless shall include such losses or damages incurred by, or in connection with, acts or omissions of JoVE, its employees, agents or independent contractors.

12. **Fees.** To cover the cost incurred for publication, JoVE must receive payment before production and publication the Materials. Payment is due in 21 days of invoice. Should the Materials not be published due to an editorial or production decision, these funds will be returned to the Author. Withdrawal by the Author of any submitted Materials after final peer review approval will result in a US\$1,200 fee to cover pre-production expenses incurred by JoVE. If payment is not received by the completion of filming, production and publication of the Materials will be suspended until payment is received.

13. **Transfer, Governing Law.** This Agreement may be assigned by JoVE and shall inure to the benefits of any of JoVE's successors and assignees. This Agreement shall be governed and construed by the internal laws of the Commonwealth of Massachusetts without giving effect to any conflict of law provision thereunder. This Agreement may be executed in counterparts, each of which shall be deemed an original, but all of which together shall be deemed to be one and the same agreement. A signed copy of this Agreement delivered by facsimile, e-mail or other means of electronic transmission shall be deemed to have the same legal effect as delivery of an original signed copy of this Agreement.

A signed copy of this document must be sent with all new submissions. Only one Agreement required per submission.

### CORRESPONDING AUTHOR:

Name:	Ying Wang		
Department:	Department of Physics, Mathematics		
Institution:	Shanghai University of Electric Power		
Article Title:	RF magnetron sputtering of GdBa <sub>2</sub> Cu <sub>3</sub> O <sub>7-x</sub> / La <sub>0.67</sub> Sr <sub>0.33</sub> MnO <sub>3</sub> Quasi-bilayer films on SrTiO <sub>3</sub> (STO) single-crystal substrates		
Signature:	Ying Wang	Date:	2018.2.27

Please submit a signed and dated copy of this license by one of the following three methods:

- 1) Upload a scanned copy of the document as a pdf on the JoVE submission site;
- 2) Fax the document to +1.866.381.2236;
- 3) Mail the document to JoVE / Attn: JoVE Editorial / 1 Alewife Center #200 / Cambridge, MA 02139

For questions, please email [submissions@jove.com](mailto:submissions@jove.com) or call +1.617.945.9051

Dear Dr. Phillip Steindel:

Thank you very much for your kind letter. We have revised the manuscript according to the suggestions made by the Editors. The origin vision of our Article No is JoVE58069. The changes we have made are listed below:

**Editorial comments:**

1. Unfortunately, there are still a few areas of the manuscript that overlap with previous work, including possibly the authors' own. See attached iThenticate report and revise the following: lines 103–106 177–213, and 234–236.

Answer (line107- 109; line181-217; line239-241): According to the suggestions of the editors, we have revised the full text carefully. The details are shown in the text with red colors.

2. There are still some areas of the manuscript where the intended meaning is unclear (see notes in attached manuscript, although there may be other issues); please edit and proofread further.

Answer (line44-45(A1); line103 (A2); line150-151 (A3); line125-127(A4); line171-172(A5)):

According to the suggestions of the editors, we have revised the areas of the manuscript where the intended meaning is unclear carefully.

Commented [A1] (line41–42): This is unclear. Wide-band what? Entangled electronic what? Half-metallic ferromagnetism.

Answer (line44-45(A1)): According to the suggestions of the editors, we have revised wide-band, half-metallic ferromagnet, entangled electronic as wide-band gap, half-metallic ferromagnetism and entangled electronic states, respectively.

Commented [A2] (line100–101): Do you mean ‘used’ , or is it adapted in some non-standard way?

Answer (line103 (A1)): According to the suggestions of the editors, we have revised ‘adapted’ to ‘used’.

Commented [A3] (line105): How is this done?

Answer (line150-151 (A3)): The  $\text{GdBa}_2\text{Cu}_3\text{O}_{7-\delta}$  target prepared process is provided as follows:

Mount the  $\text{GdBa}_2\text{Cu}_3\text{O}_{7-\delta}$  target in the magnetron gun, then reassemble the gun. Deposit any (Gd) BCO films, using steps similar to steps 1.4-2.8.

Commented [A4] (line124–125): How exactly is this done?

Answer (line125-127 (A4)): According to the suggestions of the editors, we have revised as follows:

If the instant value is getting smaller than 25Pa, clockwise rotation it, until the pressure to be settled to a stable value.

Commented [A5] (line169–170): This is unclear; do you mean the diameters/heights ranged between those values.

Answer (line171-172 (A5)): According to the suggestions of the editors, we have revised ‘changed’ to ‘ranged’.

Additionally, we have proofread the article further, and edited the full text carefully, including not properly English expressions and other issues in our article. The details are shown in the text with red colors.

3. In the manuscript, please provide explicit captions for each figure in a separate section.

Answer (List of Figures captions): According to the suggestions of the editors, we have provided

explicit captions for each figure in a separate section (List of Figures captions).

4. Figure 1: Please use ' $\mu\text{m}$ ' instead of 'um' and add spaces between numbers and units (e.g., '0 nm'); also, 'nnm' appears to be a mistake. Lastly, panels c and d do not exist in the current submission.

Answer (Figure 1, line 174): According to the suggestions of the editors, we have revised the 'um' to ' $\mu\text{m}$ ', revised 'nnm' to 'nm'. Also, we have added spaces between numbers and units. panels c and d have been mentioned in line 174.

We are grateful to you and the reviewers for helpful comments. I hope that you and the reviewers will find these changes acceptable. I look forward to hearing from you again.

Sincerely,

Sincerely yours,

Ying Wang

Department of Physics, Mathematics, Shanghai University of Electric Power, 28# Xue Hai Road,  
Shanghai 201300 P.R. China

Email: 2006000081@shiep.edu.cn

Phone: +86-21-68020533 Fax: +86-21-68020533



Figure S1



## ELSEVIER LICENSE TERMS AND CONDITIONS

Oct 07, 2018

---

---

This Agreement between Mr. Ying Wang ("You") and Elsevier ("Elsevier") consists of your license details and the terms and conditions provided by Elsevier and Copyright Clearance Center.

License Number	4443530895839
License date	Oct 07, 2018
Licensed Content Publisher	Elsevier
Licensed Content Publication	Ceramics International
Licensed Content Title	Improvement of flux pinning in GdBa <sub>2</sub> Cu <sub>3</sub> O <sub>7-δ</sub> thin film by nanoscale ferromagnetic La <sub>0.67</sub> Sr <sub>0.33</sub> MnO <sub>3</sub> pretreatment of substrate surface
Licensed Content Author	Ying Wang,Yijie Li,Linfei Liu,Da Xu
Licensed Content Date	Jan 1, 2018
Licensed Content Volume	44
Licensed Content Issue	1
Licensed Content Pages	6
Start Page	225
End Page	230
Type of Use	reuse in a journal/magazine
Requestor type	author of new work
Intended publisher of new work	Other
Portion	figures/tables/illustrations
Number of figures/tables/illustrations	7
Format	both print and electronic

Are you the author of this Elsevier article? Yes

Will you be translating? No

Original figure numbers figures1,2,3,4,5,6,7

Title of the article Radio Frequency Magnetron Sputtering of GdBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub>/La<sub>0.67</sub>Sr<sub>0.33</sub>MnO<sub>3</sub> Quasi-bilayer Films on SrTiO<sub>3</sub> (STO) Single-crystal Substrates

Publication new article is in Journal of visualized experiments : JoVE

Publisher of the new article JoVE

Author of new article Ying Wang<sup>1,2,3</sup>, Yijie Li<sup>3</sup>, Linfei Liu<sup>3</sup>, Da Xu<sup>3</sup>, Xiaojing Luo<sup>1,2</sup>

Expected publication date Dec 2018


Estimated size of new article (number of pages) 9

Requestor Location Mr. Ying Wang  
28# Xue Hai Road  
  
Shanghai, Shanghai 201300  
China  
Attn: Mr. Ying Wang

Publisher Tax ID GB 494 6272 12

Customer VAT ID CN1231000042500631XQ

Total 0.00 USD

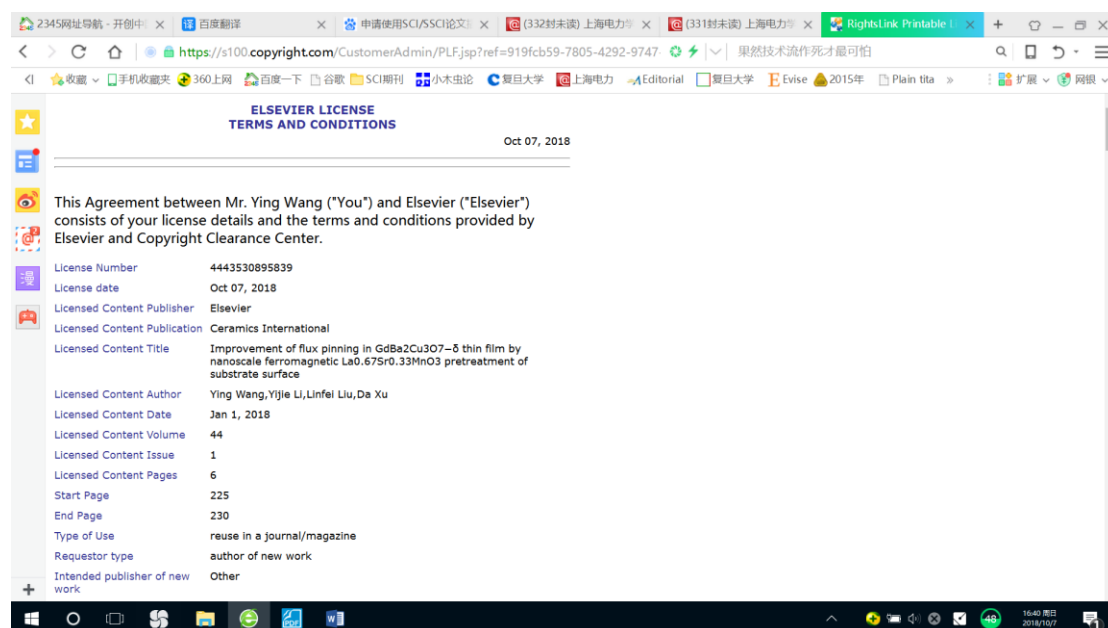

**ELSEVIER LICENSE TERMS AND CONDITIONS**  
Oct 07, 2018

This Agreement between Mr. Ying Wang ("You") and Elsevier ("Elsevier") consists of your license details and the terms and conditions provided by Elsevier and Copyright Clearance Center.

License Number	4443530895839
License date	Oct 07, 2018
Licensed Content Publisher	Elsevier
Licensed Content Publication	Ceramics International
Licensed Content Title	Improvement of flux pinning in GdBa <sub>2</sub> Cu <sub>3</sub> O <sub>7-5</sub> thin film by nanoscale ferromagnetic La <sub>0.67</sub> Sr <sub>0.33</sub> MnO <sub>3</sub> pretreatment of substrate surface
Licensed Content Author	Ying Wang, Yijie Li, Linfei Liu, Da Xu
Licensed Content Date	Jan 1, 2018
Licensed Content Volume	44
Licensed Content Issue	1
Licensed Content Pages	6
Start Page	225
End Page	230
Type of Use	reuse in a journal/magazine
Requestor type	author of new work
Intended publisher of new work	Other