

Journal of Visualized Experiments

Angle-resolved photoemission spectroscopy at ultra-low temperatures

--Manuscript Draft--

Manuscript Number:	JoVE50129R1
Full Title:	Angle-resolved photoemission spectroscopy at ultra-low temperatures
Article Type:	Methods Article - JoVE Produced Video
Corresponding Author:	Sergey Borisenko IFW-Dresden Dresden, Saxony GERMANY
Corresponding Author Secondary Information:	
Corresponding Author's Institution:	IFW-Dresden
Corresponding Author's Secondary Institution:	
First Author:	Sergey Borisenko
First Author Secondary Information:	
Order of Authors Secondary Information:	
Abstract:	<p>The physical properties of a material are defined by its electronic structure. Electrons in solids are characterized by energy (E) and momentum (k) and the probability to find them in a particular state with given E and k is described by the spectral function $A(k, E)$. This function can be directly measured in an experiment based on the well-known photoelectric effect, for the explanation of which Albert Einstein received the Nobel Prize back in 1921. In the photoelectric effect the light shone on a surface ejects electrons from the material. According to Einstein, energy conservation allows one to determine the energy of an electron inside the sample, provided the energy of the light photon and kinetic energy of the outgoing photoelectron are known. Momentum conservation makes it also possible to estimate k relating it to the momentum of the photoelectron by measuring the angle at which the photoelectron left the surface. The modern version of this technique is called Angle-Resolved Photoemission Spectroscopy (ARPES) and exploits both conservation laws in order to determine the electronic structure, i. e. energy and momentum of electrons inside the solid. In order to resolve the details crucial for understanding the topical problems of condensed matter physics, three quantities need to be minimized: uncertainty* in photon energy, uncertainty in kinetic energy of photoelectrons and temperature of the sample. In our approach we combine three recent achievements in the field of synchrotron radiation, surface science and cryogenics. We use synchrotron radiation with tunable photon energy contributing an uncertainty of the order of 1 meV, an electron energy analyzer which detects the kinetic energies with a precision of the order of 1 meV and a He3 cryostat which allows us to keep the temperature of the sample below 1 K. We discuss the exemplary results obtained on single crystals of Sr2RuO4 and some other materials. The electronic structure of this material can be determined with an unprecedented clarity.</p>
Corresponding Author E-Mail:	s.borisenko@ifw-dresden.de
Other Authors:	Volodymyr Zabolotnyy Alexander Kordyuk Danil Evtushinsky Timur Kim

	Emanuela Carleschi
	Bryan Doyle
	Rosalba Fittipaldi
	Mario Cuoco
	Antonio Vecchione
	Helmut Berger

Angle-resolved photoemission spectroscopy at ultra-low temperatures

S. V. Borisenko¹, V. B. Zabolotnyy¹, A. A. Kordyuk^{1,2}, D. V. Evtushinsky¹, T. K. Kim^{1,3}, E. Carleschi⁴,
B. P. Doyle⁴, R. Fittipaldi⁵, M. Cuoco⁵, A. Vecchione⁵, H. Berger⁶

¹*Institute for Solid State Research, IFW-Dresden, P. O. Box 270116, D-01171 Dresden, Germany*

²*Institute of Metal Physics of National Academy of Sciences of Ukraine, 03142 Kyiv, Ukraine*

³*Diamond Light Source LTD, Didcot, UK*

⁴*Department of Physics, University of Johannesburg, P. O. Box 524, Auckland Park 2006, South Africa*

⁵*CNR-SPIN, and Dipartimento di Fisica "E. R. Caianiello", Università di Salerno, I-84084 Fisciano (Salerno) Italy*

⁶*Institute of Physics of Complex Matter, EPFL, 1015 Lausanne, Switzerland*

The overall goal of this method is to determine the low-energy electronic structure of solids at ultra-low temperatures using Angle-Resolved Photoemission Spectroscopy with synchrotron radiation.

The physical properties of a material are defined by its electronic structure. Electrons in solids are characterized by energy (ω) and momentum (\mathbf{k}) and the probability to find them in a particular state with given ω and \mathbf{k} is described by the spectral function $A(\mathbf{k}, \omega)$. This function can be directly measured in an experiment based on the well-known photoelectric effect, for the explanation of which Albert Einstein received the Nobel Prize back in 1921. In the photoelectric effect the light shone on a surface ejects electrons from the material. According to Einstein, energy conservation allows one to determine the energy of an electron inside the sample, provided the energy of the light photon and kinetic energy of the outgoing photoelectron are known. Momentum conservation makes it also possible to estimate \mathbf{k} relating it to the momentum of the photoelectron by measuring the angle at which the photoelectron left the surface. The modern version of this technique is called Angle-Resolved Photoemission Spectroscopy (ARPES) and exploits both conservation laws in order to determine the electronic structure, i. e. energy and momentum of electrons inside the solid. In order to resolve the details crucial for understanding the topical problems of condensed matter physics, three quantities need to be minimized: uncertainty* in photon energy, uncertainty in kinetic energy of photoelectrons and temperature of the sample.

In our approach we combine three recent achievements in the field of synchrotron radiation, surface science and cryogenics. We use synchrotron radiation with tunable photon energy contributing an uncertainty of the order of 1 meV, an electron energy analyzer which detects the kinetic energies with a precision of the order of 1 meV and a He³ cryostat which allows us to keep the temperature of the sample below 1 K. We discuss the exemplary results obtained on single crystals of Sr₂RuO₄ and

some other materials. The electronic structure of this material can be determined with an unprecedented clarity.

INTRODUCTION

Nowadays ARPES is widely used to determine the electronic structure of solids. Usually, different variations of this method are defined by the source of the radiation needed to excite the electrons. We use synchrotron radiation since it offers a unique opportunity to tune the polarization and the excitation photon energy in a wide energy range and is characterized by high intensity, small bandwidth (uncertainty in energy $h\nu$) and it can be focused to a narrow beam to collect photoelectrons from a spot of a few tens of microns. Synchrotron radiation is generated in electron storage rings forcing electrons circulating in the ring with an energy of the order of 2 GeV ** to pass through periodic arrangements of strong magnets (undulators). The magnetic field deflects the electrons and when such fast electrons change their direction they emit radiation. Exactly this radiation is then directed into the so called beamline where it is further monochromatized by a diffraction grating and focused on the surface of the sample by several mirrors. There are many such facilities around the world. Our end-station is located at one of the beamlines of the BESSY storage ring which belongs to the Helmholtz-Zentrum Berlin.

The heart of this ARPES facility is the electron-energy analyzer (Fig.1). Since we are interested in both the kinetic energy and angle at which electrons leave the surface, it is very convenient to detect them in one measurement. A very simple principle makes this approach a reality. As in a basic experiment with an optical lens, which focuses a plane wave into the point in the back focal plane thus performing spatial Fourier transformation, the electron optical lens projects electrons which left the surface at particular angle to a point in the focal plane (Fig. 1). In such a way we gain access to the reciprocal, i.e. momentum, space. The distance from the forward direction in the focal plane corresponds to the angle and thus to the momentum of the photoelectron. Now the electrons have to be analyzed in terms of energy. For this purpose the entrance slit of the hemispherical analyzer is placed exactly in the focal plane of the electron optical lens. Voltages on two hemispheres are chosen such that only electrons with particular kinetic energy (pass energy) will be guided exactly in the middle of two hemispheres and land on the central line of the two dimensional detector. Those which are faster will hit the detector closer to the outer hemisphere; those which are slower will be deflected towards the inner hemisphere. In such a way we can get the photoemission intensity distribution as a function of angle and kinetic energy simultaneously.

The main advantage of our approach over existing methods is the use of the He^3 cryomanipulator. There are at least two reasons to carry out the measurements at low temperatures. The higher the temperature of the material, the more smeared out the electronic states become in energy and momentum. To determine the electronic structure with high precision this temperature broadening has to be avoided. Also, many physical properties are temperature dependent, some ordering phenomena set in at low temperatures and the knowledge of the electronic structure in the ground state of the system, i.e. at $T=0$, is of fundamental importance. One of the most effective ways to cool down the sample down to tenths of a Kelvin is to liquefy He^3 gas. In many experiments reaching sub-Kelvin temperatures is not a problem, since thermal radiation, the main enemy of ultra-low temperatures, can be effectively shielded. Unfortunately, this is not the case in photoemission experiments. We need to provide free access for the incoming light and outgoing electrons. This is realized by specially designed slits in three radiation shields, having different temperatures. In order

to compensate for the heat load caused by the photon beam and room-temperature radiation, the cooling power of the cryostat should be very high. This is achieved by the very large pumping speed of two pumps which reduce the vapor pressure above the liquid He³, thus cooling the cold finger and sample. The design specifications of our He³ system make it the most powerful worldwide. It is perhaps the only place on the planet where one can see a 1 K cold surface through a room temperature window, the “coldest visible”.

The sketch of the modern photoemission experiment is shown in Fig.1. The synchrotron beam (dashed green line) illuminates the 1 K cold surface of the sample and excites photoelectrons. Electrons are projected to the entrance slit of the hemispherical analyzer, sorted in terms of angle (yellow, magenta and cyan traces correspond to different tilt angles) and then are analyzed in terms of kinetic energy. Fig. 2 shows the typical intensity distribution as a function of tilt angle and kinetic energy. Such an intensity distribution is indeed expected as the comparison with band structure calculations of this material shows (right panel). This is our window into reciprocal space.

By scanning voltages on the lens and hemispheres and rotating the sample around the vertical axis (polar angle) we can explore the broad binding energy range as well as wide regions of the reciprocal space with unprecedented detail. In particular, plotting intensity at the Fermi level as a function of both components of the in-plane momentum, calculated from tilt and polar angles, we have direct access to the Fermi surface (FS).

1.

2. Mounting the Sample

- 2.1. This experiment uses synchrotron radiation produced by the BESSY storage ring of Helmholtz-Zentrum Berlin. The photons travel a beamline to our end-station where a sample is mounted.
- 2.2. Begin with a single crystal of the material to be investigated, here strontium ruthenate. Use silver-based epoxy to glue the sample to the sample holder. The silver-based epoxy ensures good thermal and electrical contact.
- 2.3. Glue an aluminum top-post to the surface of the single-crystal. The top-post will be used to cleave the sample in ultra-high vacuum to expose an atomically clean surface.
- 2.4. Mount the sample holder in the load lock.

3. Achieving Ultra-high Vacuum and Thermal Isolation

- 3.1. Begin evacuating the load lock to minimize contamination of the ultra-high vacuum chamber.
- 3.2. Monitor the pressure. Once a pressure of about 10^{-8} mbar has been achieved, transfer the assembly to the preparation chamber, and subsequently to the main chamber. The cold finger and sample holder have been specially designed to guarantee the best possible thermal contact with the helium pot.
- 3.3. These demonstration versions show how this is achieved by using conical surfaces to increase the area of contact. The conical surfaces are pressed against one another and the sample holder and cold finger are firmly fixed in place using a titanium nut and bolt.

4. Positioning and Cooling the Sample

- 4.1. The next step is to orient the sample within the cold finger along the azimuth using the transfer arm. Fix the position of the sample by tightening the nut while applying a counterforce with the supporting arm attached to the opposite side of the chamber.
- 4.2. Cleave the sample by moving the manipulator upwards so that the top-post is removed by interaction with the supporting arm.
- 4.3. With the beam shutter closed, move the sample into position in the beamline using the manipulator. Once the sample is in place, make sure the cryoshields are closed properly.
- 4.4. Start pumping on the 1-K pot and circulate the helium-3 gas in order to cool the sample to the base temperature. The temperature is measured close to the sample and will not change during the experiment.
- 4.5. Open the beam shutter of the beamline. Use the micrometer screws on the apparatus to adjust the position of the sample so that it is at the focus of the analyzer lens. This adjustment is crucial.

5. Collecting Data

- 5.1. Once the setup is ready, switch to the angle-resolved mode of the analyzer and record the spectrum in swept mode. This will generate data for two-dimensional energy-angle plots.
- 5.2. Construct a Fermi surface map using the data. Select polar angles that correspond to Fermi level crossings for study of the superconducting gap of strontium ruthenate.
- 5.3. Record high-resolution spectra at the chosen polar angles above and below the superconducting transition temperature of strontium ruthenate to investigate the behavior of the superconducting gap.

REPRESENTATIVE RESULTS

The ultra-low temperatures of our setup together with the high resolution of the beamline and analyzer allow us to record spectra with very high overall resolution. This is illustrated in Fig. 3. The usual test of the energy resolution is to measure the width of the Fermi edge of a metal. In this case it is a freshly evaporated indium film. The full width at half maximum (FWHM) of the Gaussian, which when convoluted with the step-function precisely describes the edge, is of the order of 2 meV. Of more importance for detailed studies of the low-energy electronic structure of solids is the angle-resolved spectrum of the dispersing feature. Such an example is shown in the middle panel of Fig. 3. A very sharp superconducting peak is observed in the iron-based superconductor LiFeAs [1] representing one of the sharpest features ever detected by ARPES. The same holds for momentum resolution. The FWHM of 0.23° is the record value for the wide angular mode of electron energy analyzers. The system has been designed to combine three achievements, 1 meV bandwidth of the beamline, 1 meV resolution of the analyzer and 1 K temperature of the sample. This aim gave the name to our system “1-cubed ARPES”. If all the three components were minimized, one would expect the $\text{FWHM} \sim 1.46$ meV. Our current measurements show that overall resolution of the order of 2 meV can be achieved.

Another representative result is our investigation of the electronic structure of the superconductor Sr_2RuO_4 with critical temperature 1.35 K. This material is a well-known oxide possessing a wide spectrum of interesting physical properties. It was the first discovered superconducting oxide after the cuprates [2]. Its superconducting state is unusual: electrons coupled in pairs have their spins oriented in the same direction. This is the so called triplet superconductivity. It still remains not well understood and the main problem is to define the symmetry of the superconducting order parameter. In order to do that, the superconducting energy gap should be determined as a function of momentum – the exact task for ARPES. Because such low temperatures needed for superconductivity were not accessible in photoemission experiments before, it was not possible to address this problem. Here we make an attempt to do this. First of all, one needs to determine the Fermi surface. For this purpose we have recorded many cuts at different polar angles. Some of them are shown for illustration in Fig. 4. Now, if we consider intensity only in the vicinity of the Fermi level, and plot it as a function of both angles, we will obtain the locus of Fermi momenta, i.e. the Fermi surface map. Such a Fermi surface map is shown in Fig.5 together with the calculated Fermi surface [3]. The agreement is very good, but the experimental data show many more features. Some of them are unexpected and unusual [4]. Now we can try to measure the superconducting gap. For this we have to record the spectra above and below the critical temperature, i.e. 1.35 K. In Fig.6 we show such pairs of spectra. We indeed observe some changes, compatible with the opening of the energy gap, but even the present energy resolution (or perhaps also the temperature, which can be higher right at the surface of the sample) does not allow us to draw a definite conclusion as for the energy gap in Sr_2RuO_4 .

FIGURES

Figure 1. Schematic of the experimental setup.

Figure 2. **Left panel.** Example of photoemission intensity distribution as a function of kinetic energy and angle. The band structure of the solid is directly seen. **Right panel.** Results of the band structure calculations for the same material. Theoretical data are taken from [5].

Figure 3. Performance of the experimental end-station. **Left panel.** Fermi edge of freshly evaporated indium film. **Middle panel.** Energy distribution curve (EDC) in a superconducting sample of LiFeAs . Data are taken from [1]. **Right panel.** Momentum distribution curve (MDC) at the Fermi level of ZrTe_3 . Anticipated overall energy resolution of the system is expressed by the formula. The actual performance of the system is very close to the one we initially aimed for.

Figure 4. Energy-momentum cuts recorded at different polar angles (step 10) for Sr_2RuO_4 .

Figure 5. Fermi surface map of Sr_2RuO_4 taken using 80 eV linearly polarized light at $\sim 1\text{K}$.

Figure 6. **a, b** Typical spectra taken to study the superconducting gap of Sr_2RuO_4 . Red arrow indicates the momentum corresponding to a single energy distribution curve (EDC). $T = 970\text{ mK}$. **c, d** Shift of the leading edge of the integrated EDC. Momentum window is represented by the width of the red arrow. The gap corresponds to a FS point on the band near the BZ diagonal. **e** Shift of the k_F EDC as a function of temperature from another point on the FS. **f** Typical temperature behavior of the binding energy of the leading edge in the vicinity of the crossing of two FSs.

DISCUSSION

As is shown above, the implemented method is very efficient in studying the low-energy electronic structure of single crystals. Recent instrumental improvements have turned ARPES from a mere characterization and band-mapping tool into a sophisticated many-body spectroscopy. A modern experiment delivers information about the electronic structure of a solid or a nano-object with a new level of precision. Access to the Fermi surface in the case of a metal, energy gaps of semiconductors and insulators, their surface states, band structures and momentum dependent Fermi velocities allows one to characterize the electronic structure on a general level. Comparison with ab-initio calculations yields bandwidth- and Fermi velocity renormalizations and thus determines the complexity of the material in terms of the strength of correlations. Fine structures near the Fermi level often provide the possibility to detect the fingerprints of interaction between electrons and other degrees of freedom, like phonons, plasmons, spin-fluctuations etc. Systematic momentum dependent studies can identify the dominant interaction and single out, for example, a pairing mediator in superconductors or density wave systems. More thorough investigations involve the determination of the symmetry of the order parameter, thus providing critical tests for existing theories or stimulating new approaches on a fundamental level.

As in every experimental method, there are certain drawbacks. It is known that photoelectrons are strongly scattered inside the crystal, thus having a relatively short inelastic mean free path. As a result, the escape depth can be very small, down to several lattice constants. This defines the sensitivity of the method to the surface and in some cases the electronic structure of the surface is indeed different from the bulk [6]. However, ARPES offers many tools to monitor this situation. One of them is the use of various excitation photon energies. As has been mentioned previously, for a given photon energy it is possible to also estimate the component of momentum perpendicular to the surface. Observed periodic structures in ARPES spectra allow one to determine absolute k_z and the corresponding momentum resolution gives uncertainty of this quantity. In such a way the experimental value of the escape depth can be estimated from the uncertainty principle $\delta k_z * \delta z \sim 1$. The next tool to control the surface sensitivity of the method is variable polarization of the light. It was demonstrated earlier that using circularly polarized light it is possible to distinguish between surface and bulk contributions to the photoemission signal [7]. Another advantage of using various polarizations and photon energies delivered by the synchrotron light source is the possibility to disentangle matrix element effects from genuine features of the spectral function. The matrix element is a transition probability which can suppress photoemission signal in particular regions of momentum space and result in misinterpretation of the ARPES spectra [8-10].

Obviously, the method is not very suitable for strongly 3D materials, which are difficult to cleave *in situ* and obtain atomically clean and flat surfaces. Finally, ARPES on insulators is much more complicated since it is necessary to compensate charging occurring because the flux of outgoing electrons cannot be compensated by electrical contact with the sample holder [11].

ACKNOWLEDGEMENTS

We are grateful to Rolf Follath for the help at the beamline. This work was supported by the DFG priority program SPP1458, grants ZA 654/1-1, BO1912/3-1 and BO1912/2-2. E.C. and B.P.D. thank the Faculty of Science at the University of Johannesburg for travel funding.

DISCLOSURES

The authors declare that they have no competing financial interests.

SAMPLES

ZrTe₃, TiSe₂, Sr₂RuO₄

REFERENCES

- [1] S.V. Borisenko et al., *Symmetry* **4**, 251-264 (2012).
- [2] Y. Maeno, H. Hashimoto, K. Yoshida, S. Nishizaki, T. Fujita, J. G. Bednorz, and F. Lichtenberg, *Nature (London)* **372**, 532 (1994).
- [3] D. J. Singh, *Phys. Rev. B* **52**, 1358 (1995).
- [4] V. B. Zabolotnyy et al. *New Journal of Physics* **14** (2012) Nr. 6, S. 63039/1-14.
- [5] K. Stöwe and F. Wagner, *Journal of Solid State Chemistry* **138**, 160-168 (1998).
- [6] V. B. Zabolotnyy et al. *Phys. Rev. B* **76**, 064519 (2007).
- [7] V. B. Zabolotnyy et al. *Phys. Rev. B* **76**, 024502 (2007).
- [8] A. A. Kordyuk, S. V. Borisenko, T. K. Kim, K. A. Nenkov, M. Knupfer, J. Fink, M. S. Golden, H. Berger, and R. Follath, *Phys. Rev. Lett.* **89**, 077003 (2002).
- [9] D. S. Inosov, J. Fink, A. A. Kordyuk, S. V. Borisenko, V. B. Zabolotnyy, R. Schuster, M. Knupfer, B. Büchner, R. Follath, H. A. Dürr, W. Eberhardt, V. Hinkov, B. Keimer, and H. Berger, *Phys. Rev. Lett.* **99**, 237002 (2007).
- [10] D. S. Inosov, R. Schuster, A. A. Kordyuk, J. Fink, S. V. Borisenko, V. B. Zabolotnyy, D. V. Evtushinsky, M. Knupfer, B. Büchner, R. Follath, and H. Berger, *Phys. Rev. B* **77**, 212504 (2008).
- [11] S. Hüfner, *Photoelectron Spectroscopy, Principles and Applications*, Springer Verlag Heidelberg, 2nd Edition (1996).

* Under “uncertainty” we understand the experimenter's best *estimate* of how far an experimental quantity might be from the "true value."

** The low-energy ring can have an energy of ~0.8 GeV, the high-energy one – up to 8 GeV.

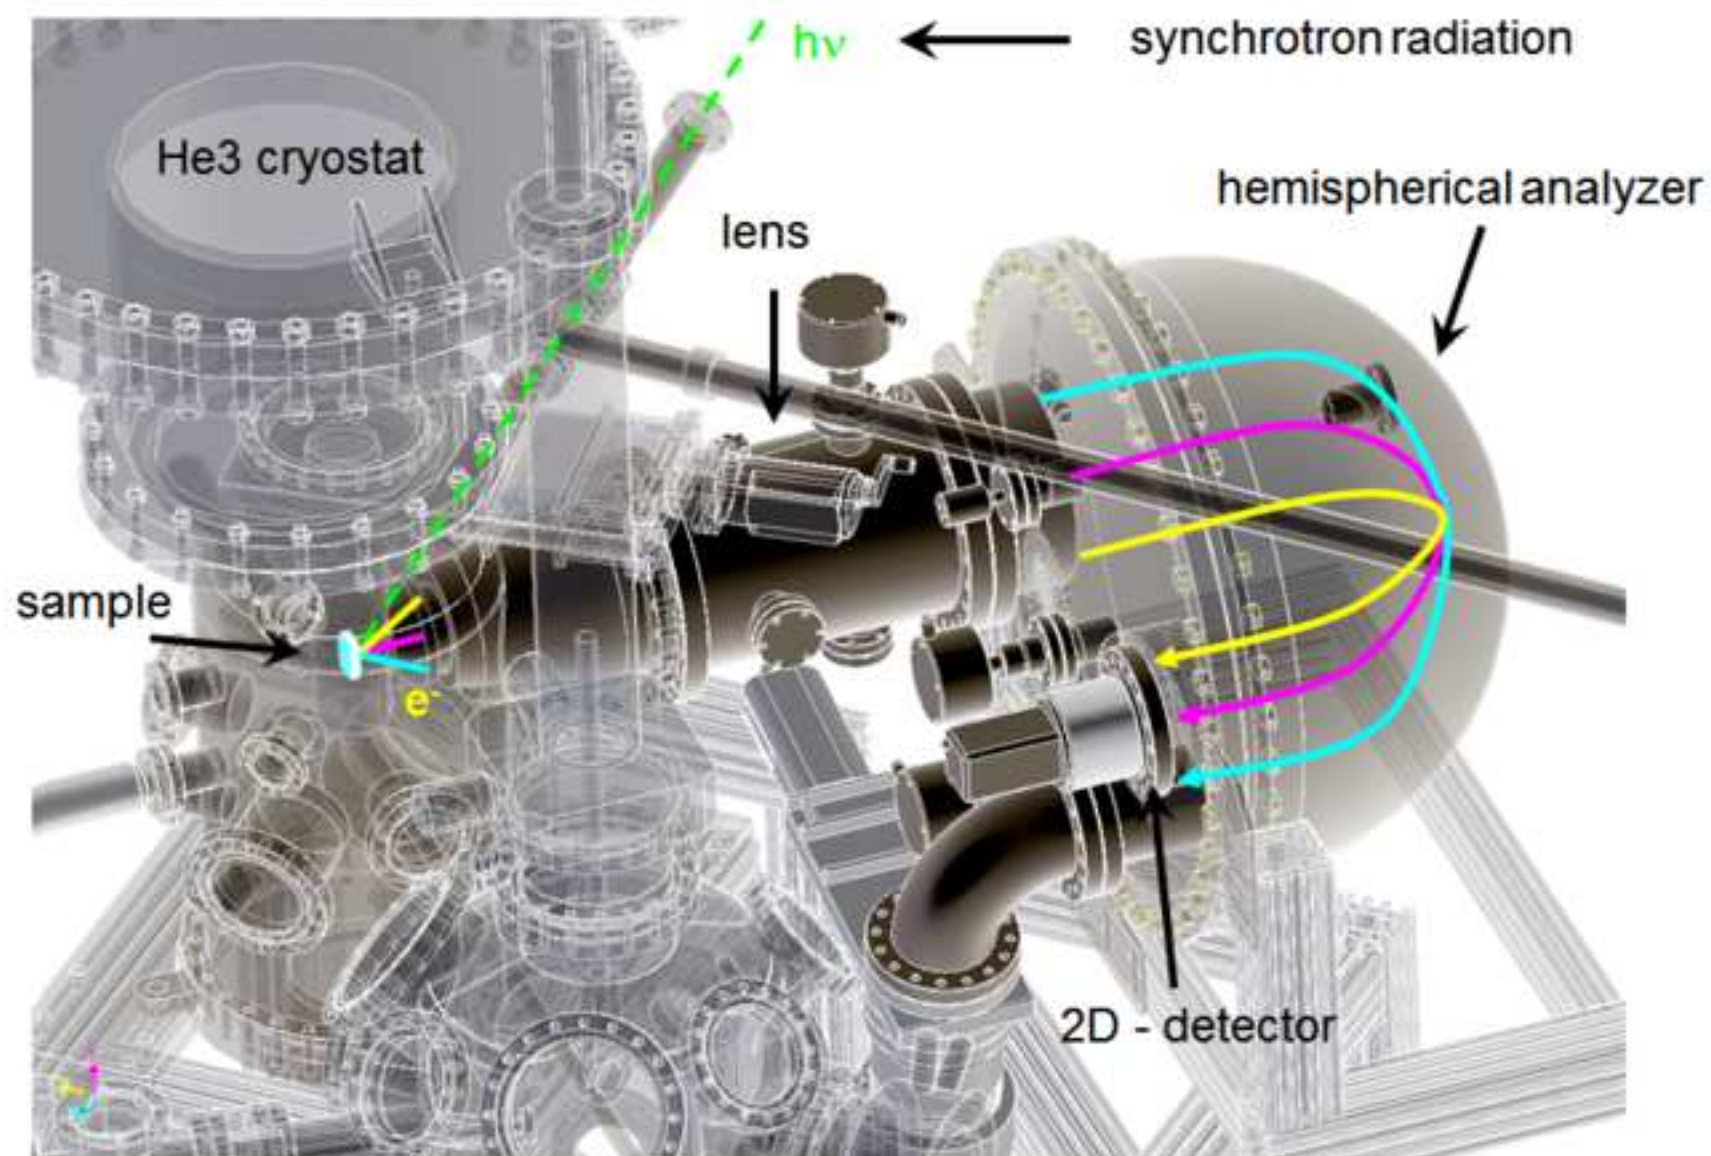


Figure 1

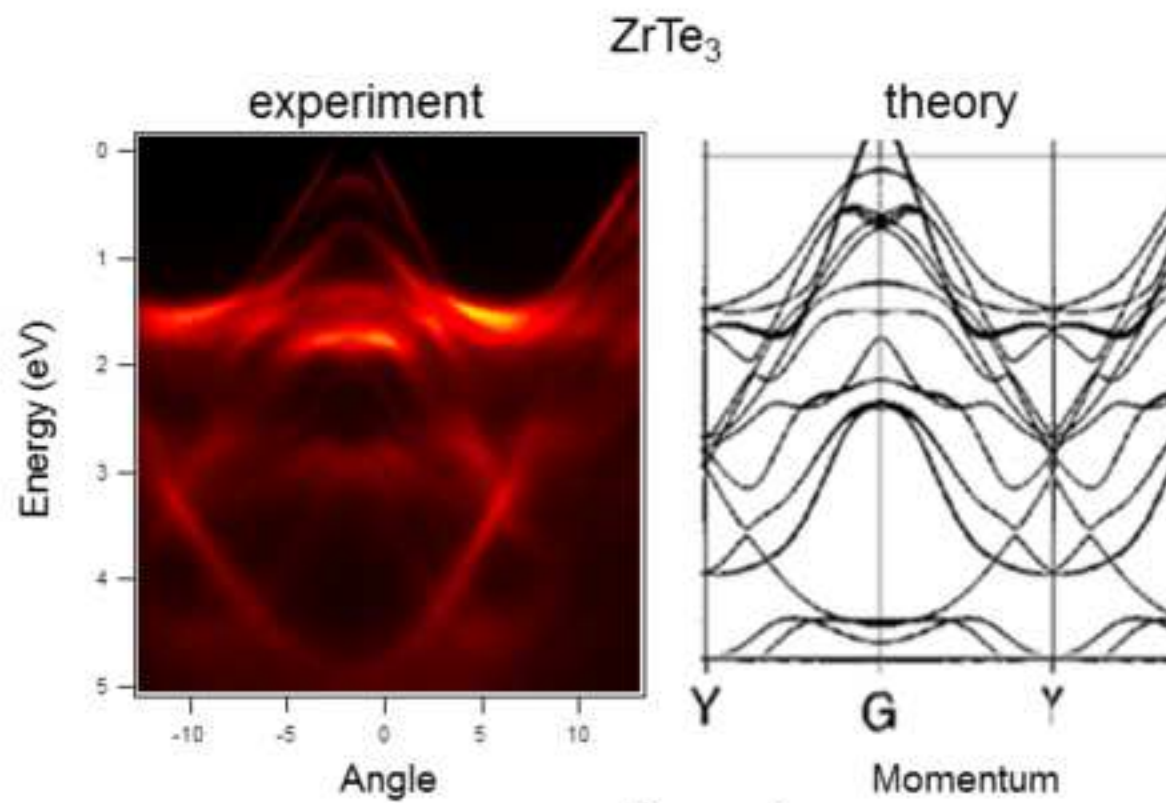


Figure 2

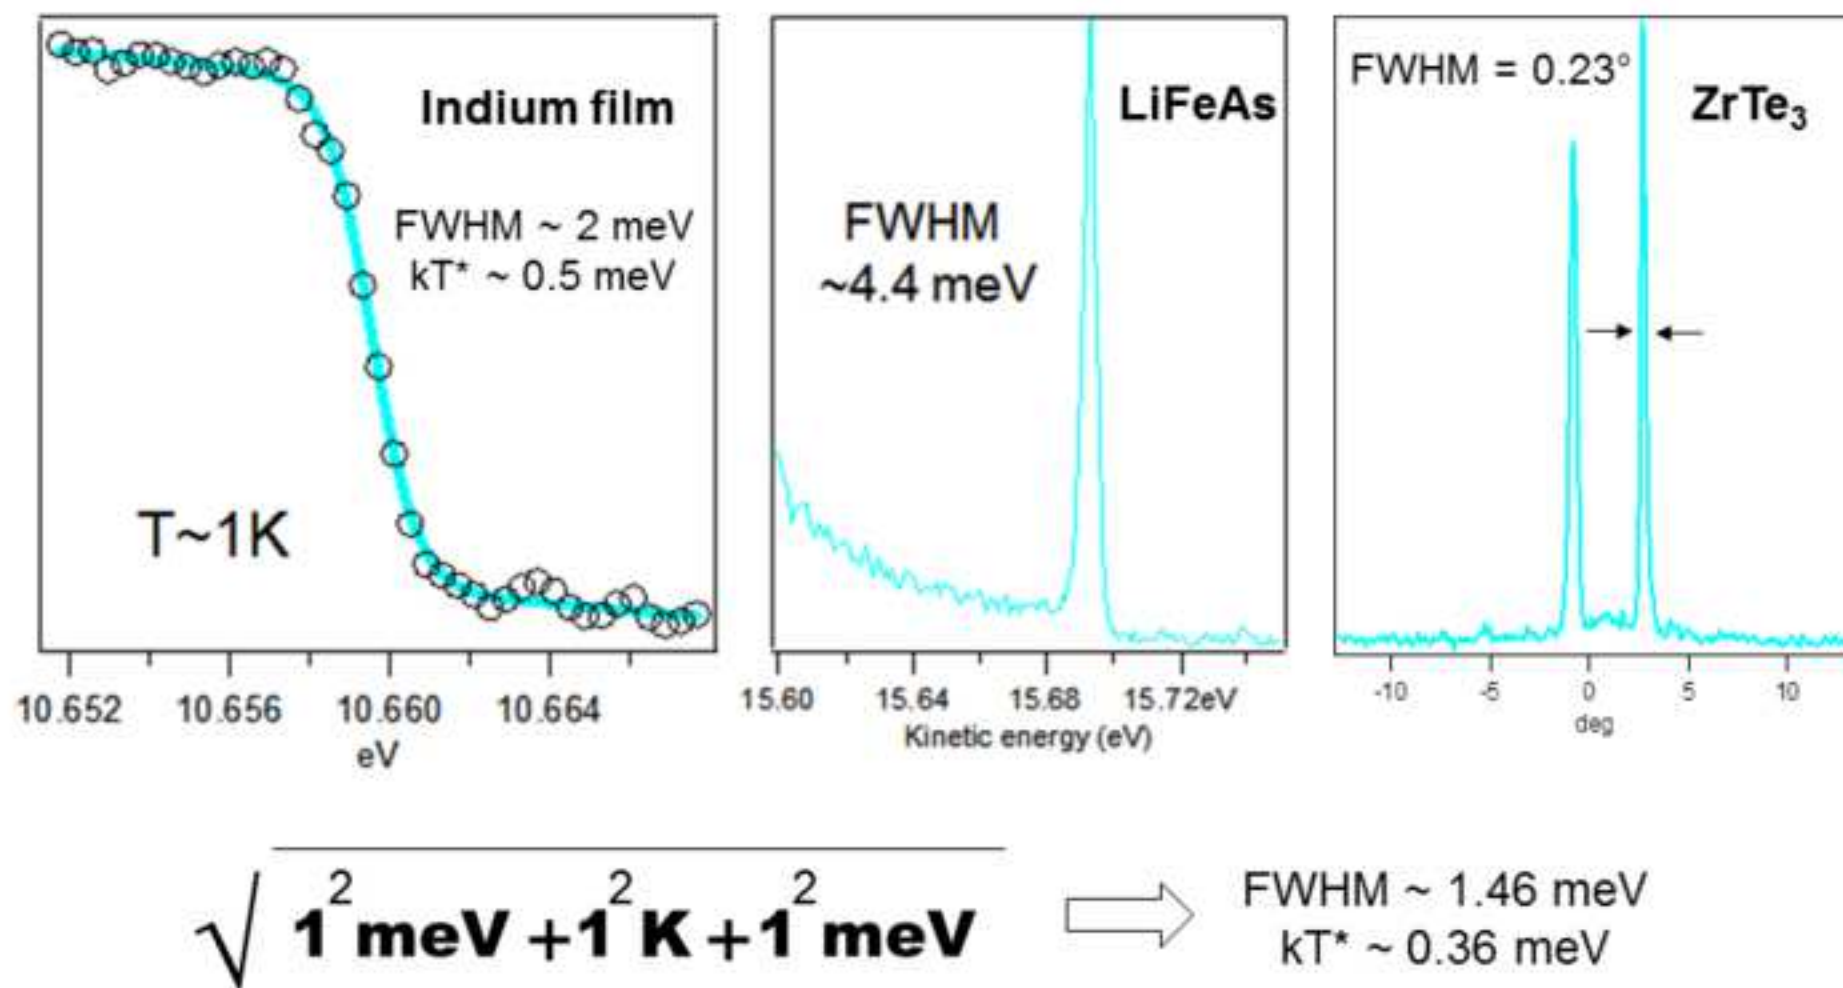


Figure 3

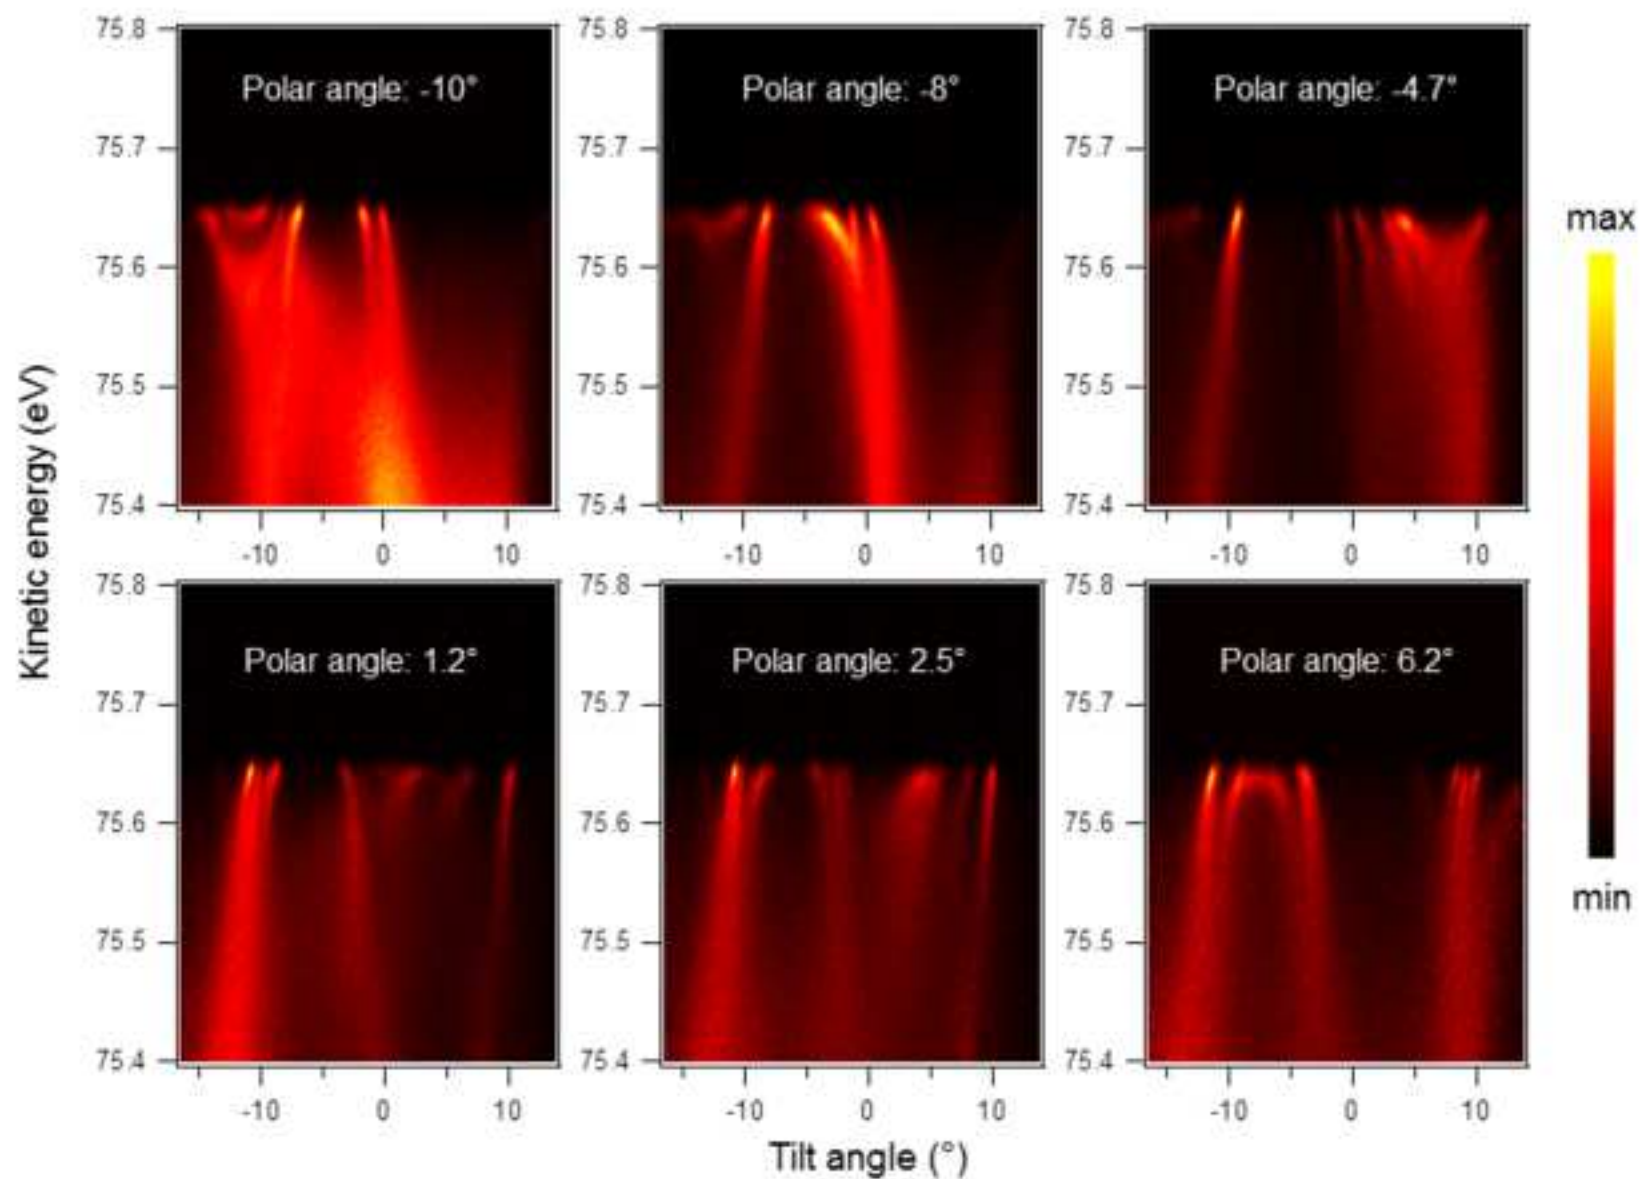


Figure 4

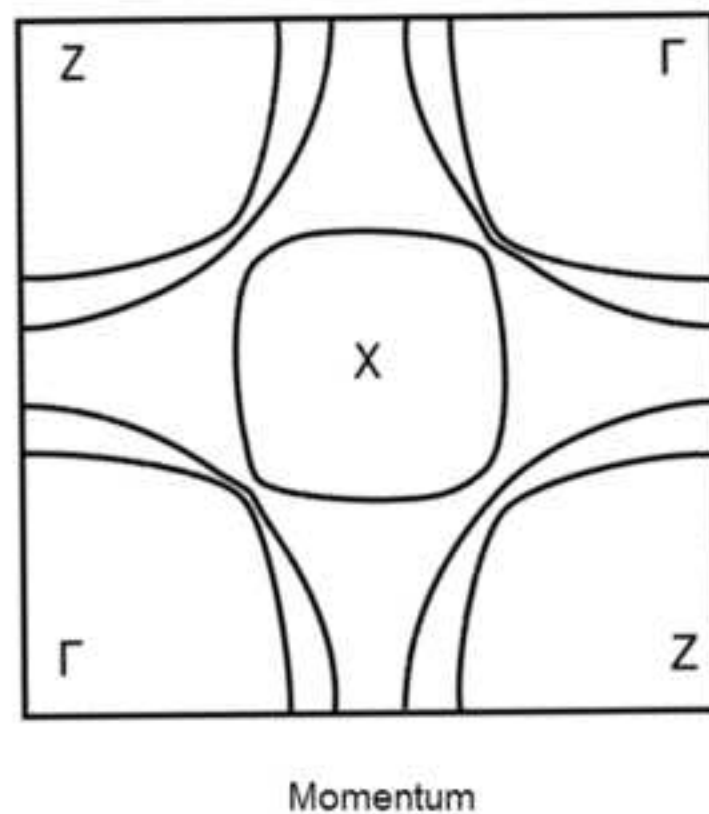
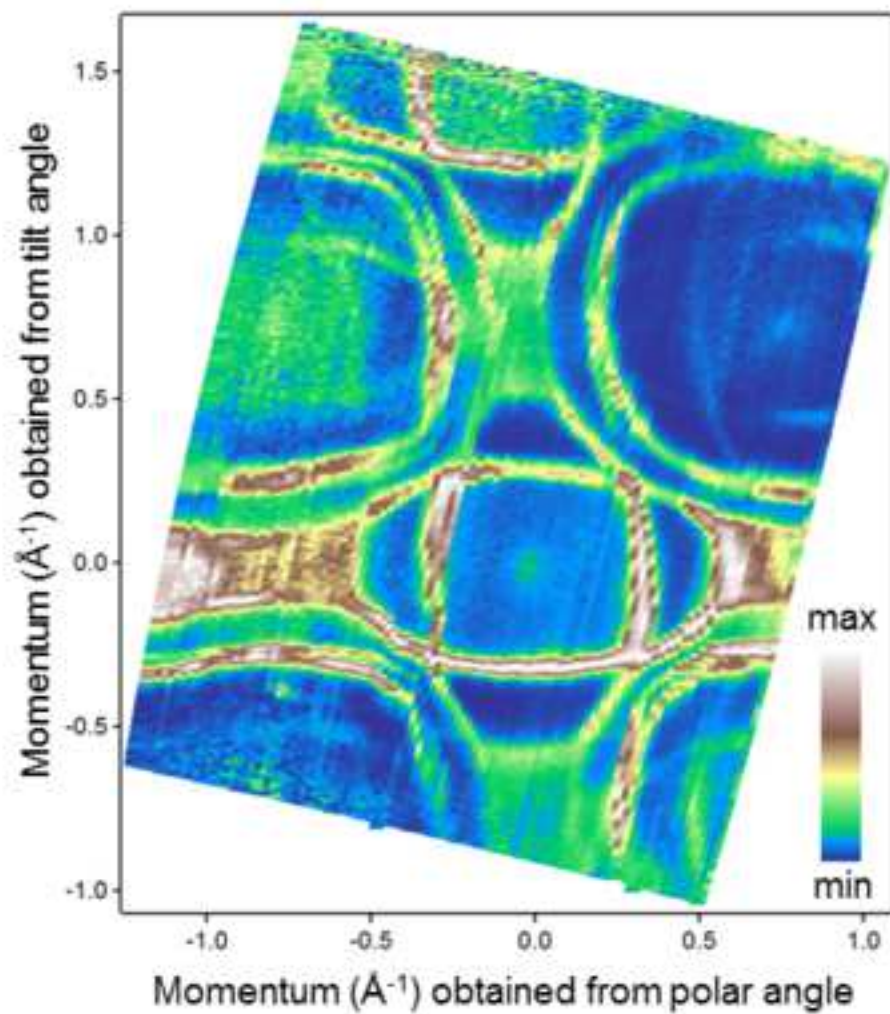


Figure 5

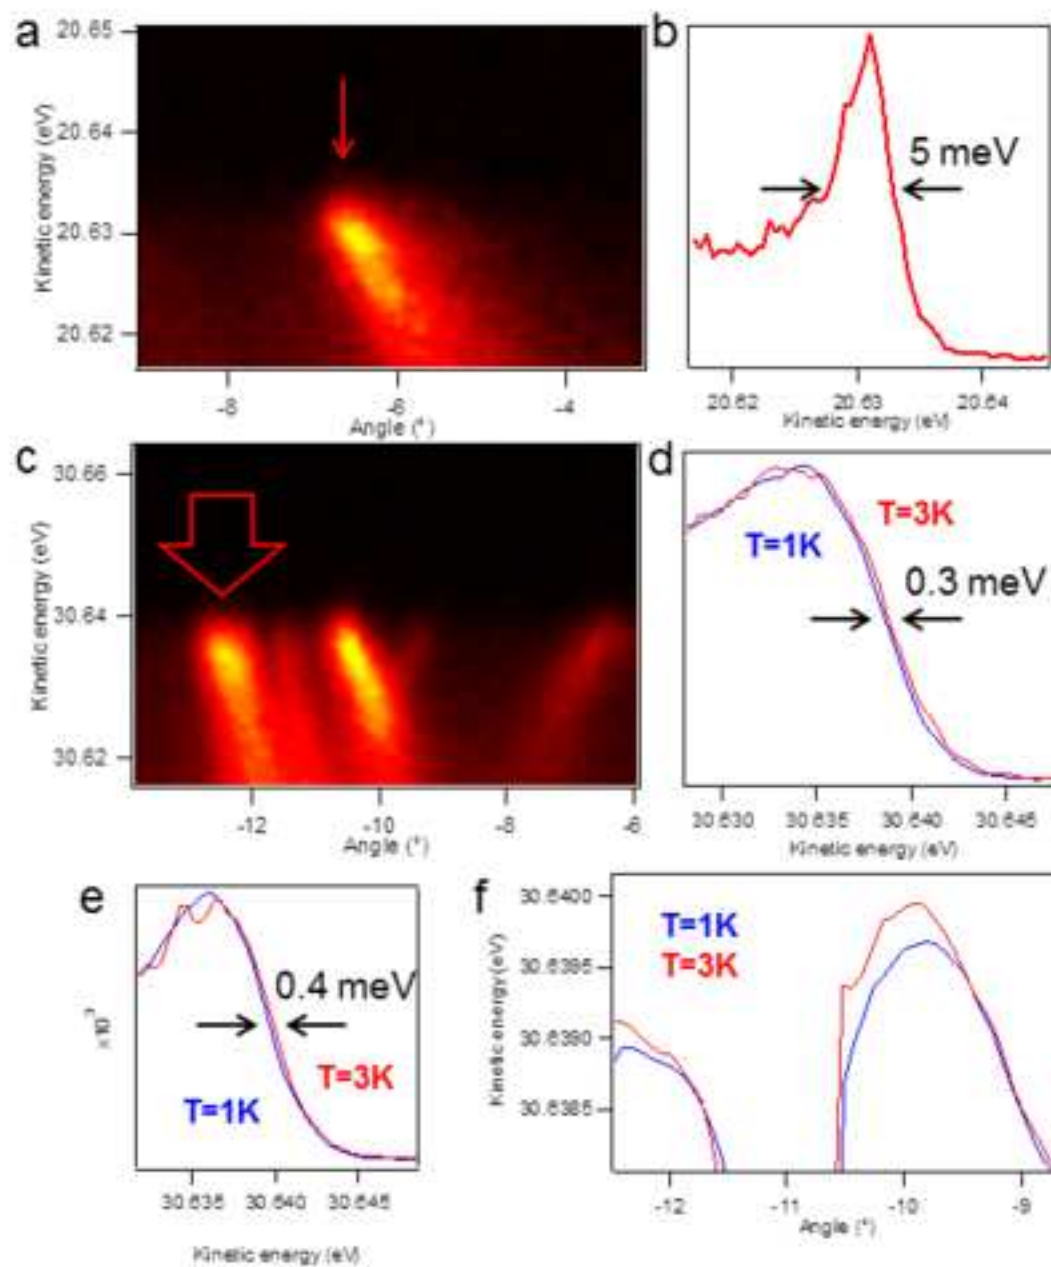


Figure 6

*Table of Reagents/ Materials Used
[Click here to download Table of Reagents/ Materials Used: JoVE_Materials.xlsx](#)

Name of Reagent/Material	Company	Catalogue Number	Comments
Single crystals of ZrTe3 and TiSe2			grown by Dr Helmut Berger, EPFL, Lausanne
Single crystals of Sr2RuO4			grown by the group of Dr Antonio Vecchione



17 Sellers Street
Cambridge, MA 02139
Tel: +1 617 945 9057
www.JoVE.com

ARTICLE AND VIDEO LICENSE AGREEMENT

Manuscript #:

Title of Article:

FERMI SURFACE MAPPING OF Sr_2RuO_4 AT LOW TEMPERATURES

Author(s):

S.V. BORISENKO ET AL.

Item 1 (check one box): The Author elects to have the Materials be made available (as described at <http://www.jove.com/publish>) via: ☒ Standard Access ☐ Open Access

Item 2 (check one box):

☒ The Author is NOT a United States government employee.

☐ The Author is a United States government employee and the Materials were prepared in the course of his or her duties as a United States government employee.

☐ The Author is a United States government employee but the Materials were NOT prepared in the course of his or her duties as a United States government employee.


ARTICLE AND VIDEO LICENSE AGREEMENT

1. **Defined Terms.** As used in this Article and Video License Agreement, the following terms shall have the following meanings: "**Agreement**" means this Article and Video License Agreement; "**Article**" means the article specified on the last page of this Agreement, including any associated materials such as texts, figures, tables, artwork, abstracts, or summaries contained therein; "**Author**" means the author who is a signatory to this Agreement; "**Collective Work**" means a work, such as a periodical issue, anthology or encyclopedia, in which the Materials in their entirety in unmodified form, along with a number of other contributions, constituting separate and independent works in themselves, are assembled into a collective whole; "**CRC License**" means the Creative Commons Attribution-Non Commercial-No Derivs 3.0 Unported Agreement, the terms and conditions of which can be found at: <http://creativecommons.org/licenses/by-nc-nd/3.0/legalcode>; "**Derivative Work**" means a work based upon the Materials or upon the Materials and other pre-existing works, such as a translation, musical arrangement, dramatization, fictionalization, motion picture version, sound recording, art reproduction, abridgment, condensation, or any other form in which the Materials may be recast, transformed, or adapted; "**Institution**" means the institution, listed on the last page of this Agreement, by which the Author was employed at the time of the creation of the Materials; "**JoVE**" means MyJoVE Corporation, a Massachusetts corporation and the publisher of *The Journal of Visualized Experiments*; "**Materials**" means the Article and / or the Video; "**Parties**" means the Author and JoVE; "**Video**" means any video(s) made by the Author, alone or in conjunction with any other parties, or by JoVE or its affiliates or agents, individually or in collaboration with the Author or any other parties,

incorporating all or any portion of the Article, and in which the Author may or may not appear.

2. **Background.** The Author, who is the author of the Article, in order to ensure the dissemination and protection of the Article, desires to have the JoVE publish the Article and create and transmit videos based on the Article. In furtherance of such goals, the Parties desire to memorialize in this Agreement the respective rights of each Party in and to the Article and the Video.

3. **Grant of Rights in Article.** In consideration of JoVE agreeing to publish the Article, the Author hereby grants to JoVE, subject to **Sections 4 and 7** below, the exclusive, royalty-free, perpetual (for the full term of copyright in the Article, including any extensions thereto) license (a) to publish, reproduce, distribute, display and store the Article in all forms, formats and media whether now known or hereafter developed (including without limitation in print, digital and electronic form) throughout the world, (b) to translate the Article into other languages, create adaptations, summaries or extracts of the Article or other Derivative Works (including, without limitation, the Video) or Collective Works based on all or any portion of the Article and exercise all of the rights set forth in (a) above in such translations, adaptations, summaries, extracts, Derivative Works or Collective Works and (c) to license others to do any or all of the above. The foregoing rights may be exercised in all media and formats, whether now known or hereafter devised, and include the right to make such modifications as are technically necessary to exercise the rights in other media and formats. If the "Open Access" box has been checked in **Item 1** above, JoVE and the Author hereby grant to the public all such rights in the Article



17 Sellers Street
Cambridge, MA 02139
tel: +1 617 945 9051
www.JoVE.com

ARTICLE AND VIDEO LICENSE AGREEMENT

as provided in, but subject to all limitations and requirements set forth in, the CRC License.

4. **Retention of Rights in Article.** Notwithstanding the exclusive license granted to JoVE in **Section 3** above, the Author shall, with respect to the Article, retain the non-exclusive right to use all or part of the Article for the non-commercial purpose of giving lectures, presentations or teaching classes, and to post a copy of the Article on the Institution's website or the Author's personal website, in each case provided that a link to the Article on the JoVE website is provided and notice of JoVE's copyright in the Article is included. All non-copyright intellectual property rights in and to the Article, such as patent rights, shall remain with the Author.

5. **Grant of Rights in Video – Standard Access.** This **Section 5** applies if the "Standard Access" box has been checked in **Item 1** above or if no box has been checked in **Item 1** above. In consideration of JoVE agreeing to produce, display or otherwise assist with the Video, the Author hereby acknowledges and agrees that, Subject to **Section 7** below, JoVE is and shall be the sole and exclusive owner of all rights of any nature, including, without limitation, all copyrights, in and to the Video. To the extent that, by law, the Author is deemed, now or at any time in the future, to have any rights of any nature in or to the Video, the Author hereby disclaims all such rights and transfers all such rights to JoVE.

6. **Grant of Rights in Video – Open Access.** This **Section 6** applies only if the "Open Access" box has been checked in **Item 1** above. In consideration of JoVE agreeing to produce, display or otherwise assist with the Video, the Author hereby grants to JoVE, subject to **Section 7** below, the exclusive, royalty-free, perpetual (for the full term of copyright in the Article, including any extensions thereto) license (a) to publish, reproduce, distribute, display and store the Video in all forms, formats and media whether now known or hereafter developed (including without limitation in print, digital and electronic form) throughout the world, (b) to translate the Video into other languages, create adaptations, summaries or extracts of the Video or other Derivative Works or Collective Works based on all or any portion of the Video and exercise all of the rights set forth in (a) above in such translations, adaptations, summaries, extracts, Derivative Works or Collective Works and (c) to license others to do any or all of the above. The foregoing rights may be exercised in all media and formats, whether now known or hereafter devised, and include the right to make such modifications as are technically necessary to exercise the rights in other media and formats. For any Video to which this **Section 6** is applicable, JoVE and the Author hereby grant to the public all such rights in the Video as provided in, but subject to all limitations and requirements set forth in, the CRC License.

7. **Government Employees.** If the Author is a United States government employee and the Article was prepared in the course of his or her duties as a United States government employee, as indicated in **Item 2** above, and any of the licenses or grants granted by the Author hereunder exceed the

scope of the 17 U.S.C. 403, then the rights granted hereunder shall be limited to the maximum rights permitted under such statute. In such case, all provisions contained herein that are not in conflict with such statute shall remain in full force and effect, and all provisions contained herein that do so conflict shall be deemed to be amended so as to provide to JoVE the maximum rights permissible within such statute.

8. **Likeness, Privacy, Personality.** The Author hereby grants JoVE the right to use the Author's name, voice, likeness, picture, photograph, image, biography and performance in any way, commercial or otherwise, in connection with the Materials and the sale, promotion and distribution thereof. The Author hereby waives any and all rights he or she may have, relating to his or her appearance in the Video or otherwise relating to the Materials, under all applicable privacy, likeness, personality or similar laws.

9. **Author Warranties.** The Author represents and warrants that the Article is original, that it has not been published, that the copyright interest is owned by the Author (or, if more than one author is listed at the beginning of this Agreement, by such authors collectively) and has not been assigned, licensed, or otherwise transferred to any other party. The Author represents and warrants that the author(s) listed at the top of this Agreement are the only authors of the Materials. If more than one author is listed at the top of this Agreement and if any such author has not entered into a separate Article and Video License Agreement with JoVE relating to the Materials, the Author represents and warrants that the Author has been authorized by each of the other such authors to execute this Agreement on his or her behalf and to bind him or her with respect to the terms of this Agreement as if each of them had been a party hereto as an Author. The Author warrants that the use, reproduction, distribution, public or private performance or display, and/or modification of all or any portion of the Materials does not and will not violate, infringe and/or misappropriate the patent, trademark, intellectual property or other rights of any third party. The Author represents and warrants that it has and will continue to comply with all government, institutional and other regulations, including, without limitation all institutional, laboratory, hospital, ethical, human and animal treatment, privacy, and all other rules, regulations, laws, procedures or guidelines, applicable to the Materials, and that all research involving human and animal subjects has been approved by the Author's relevant institutional review board.

10. **JoVE Discretion.** If the Author requests the assistance of JoVE in producing the Video in the Author's facility, the Author shall ensure that the presence of JoVE employees, agents or independent contractors is in accordance with the relevant regulations of the Author's institution. If more than one author is listed at the beginning of this Agreement, JoVE may, in its sole discretion, elect not take any action with respect to the Article until such time as it has received complete, executed Article and Video License Agreements from each such author. JoVE reserves the right, in its absolute and sole discretion and without giving any reason therefore, to accept or decline any work submitted to JoVE. JoVE and its



17 Sellers Street
Cambridge, MA 02139
tel. +1.617.945.9051
www.JoVE.com

ARTICLE AND VIDEO LICENSE AGREEMENT

employees, agents and independent contractors shall have full, unfettered access to the facilities of the Author or of the Author's institution as necessary to make the Video, whether actually published or not. JoVE has sole discretion as to the method of making and publishing the Materials, including, without limitation, to all decisions regarding editing, lighting, filming, timing of publication, if any, length, quality, content and the like.

11. Indemnification. The Author agrees to indemnify JoVE and/or its successors and assigns from and against any and all claims, costs, and expenses, including attorney's fees, arising out of any breach of any warranty or other representations contained herein. The Author further agrees to indemnify and hold harmless JoVE from and against any and all claims, costs, and expenses, including attorney's fees, resulting from the breach by the Author of any representation or warranty contained herein or from allegations or instances of violation of intellectual property rights, damage to the Author's or the Author's institution's facilities, fraud, libel, defamation, research, equipment, experiments, property damage, personal injury, violations of institutional, laboratory, hospital, ethical, human and animal treatment, privacy or other rules, regulations, laws, procedures or guidelines, liabilities and other losses or damages related in any way to the submission of work to JoVE, making of videos by JoVE, or publication in JoVE or elsewhere by JoVE. The Author shall be responsible for, and shall hold JoVE harmless from, damages caused by lack of sterilization, lack of cleanliness or by contamination due to the making of a video by JoVE its employees, agents or independent contractors. All sterilization, cleanliness or decontamination procedures shall be solely the responsibility

of the Author and shall be undertaken at the Author's expense. All indemnifications provided herein shall include JoVE's attorney's fees and costs related to said losses or damages. Such indemnification and holding harmless shall include such losses or damages incurred by, or in connection with, acts or omissions of JoVE, its employees, agents or independent contractors.

12. Fees. To cover the cost incurred for publication, JoVE must receive payment before production and publication the Materials. Payment is due in 21 days of invoice. Should the Materials not be published due to an editorial or production decision, these funds will be returned to the Author. Withdrawal by the Author of any submitted Materials after final peer review approval will result in a US\$1,200 fee to cover pre-production expenses incurred by JoVE. If payment is not received by the completion of filming, production and publication of the Materials will be suspended until payment is received.

13. Transfer, Governing Law. This Agreement may be assigned by JoVE and shall inure to the benefits of any of JoVE's successors and assignees. This Agreement shall be governed and construed by the internal laws of the Commonwealth of Massachusetts without giving effect to any conflict of law provision thereunder. This Agreement may be executed in counterparts, each of which shall be deemed an original, but all of which together shall be deemed to be one and the same agreement. A signed copy of this Agreement delivered by facsimile, e-mail or other means of electronic transmission shall be deemed to have the same legal effect as delivery of an original signed copy of this Agreement.

A signed copy of this document must be sent with all new submissions.

AUTHOR:

Name:

SERGEY BORTSENKO

Department:

ELECTRONIC AND OPTICAL PROPERTIES

Institution:

IFW - DRESDEN

Article Title:

FERMI SURFACE MAPPING OF Sr_2RuO_4 AT LOW TEMPERATURES

Signature:

Date:

04.06.2012

Please submit a signed and dated copy of this license by one of the following three methods:

- 1) Upload a scanned copy of the document as a pdf on the JoVE submission site;
- 2) Fax the document to +1.866.381.2236; or
- 3) Mail the document to JoVE / Attn: JoVE Editorial / 17 Sellers St / Cambridge, MA 02139

For questions, please email editorial@jove.com or call +1.617.945.9051.

We are grateful to all referees for careful review of our manuscript. We are glad that all three recommend the publication and in the following respond to the comments and questions raised by the referees. We modify the manuscript in accordance with most of the recommendations and hope that the paper is now suitable for publication in JOVE.

Reviewer #1

The main concern of Reviewer #1 is the Fig.6. The purpose of Fig.6 is to illustrate the performance of the system. We do actually observe signatures of the gap opening as shift of the leading edges of the spectra. This is a conventional presentation of ARPES data showing the opening of the gap. We could not, however, exclude that this shift is the temperature effect and therefore described it accordingly in the text. The latter however does not compromise the performance of the system. We would therefore like to keep this figure.

1. Yes, the temperature is measured during the experiments. We have added to the protocol a corresponding sentence when showing the temperature.
2. We intentionally kept kinetic energy and angle in some of the plots to illustrate that the raw data are collected exactly in these coordinates. We hope it is clear from the text that binding energy and momentum can be re-calculated afterwards.
3. We would like to keep the Fig.1 in its present form as it represents a realistic setup.
4. We have mentioned other materials in the abstract in the revised version.

Reviewer #2

Major Concern

We have followed the recommendation of the referee and added a reference to the well-known textbook.

Minor Concern

We have explained the term “uncertainty” in the footnote of the amended version of the manuscript.

We have changed the title and mentioned the word “photoemission”.

Reviewer #3

Major Concerns

1. The paper describes a particular method to determine the electronic structure of solids. It is though based on the very general photoemission technique, which we described in order to introduce the reader to the subject. We did not aim to introduce ARPES as a general technique, but only an ultra-low temperature modification of it.

2. Yes, the paper describes only our work.

Minor Concerns

3. Again, we did not intend to give an overview of what kind of ARPES equipment is available in the world. We fully realize that taken apart, some of the numbers can be better. The advantage of our approach is the combined resolution and temperature which, to our best knowledge, have no rivals so far.
4. We added required clarification as a second footnote.
5. We have modified this sentence according to the suggestion of the referee.
6. We are pretty sure this is true, but we added “perhaps” to soften the statement.
7. We meant exactly the possibility to change pass energy, which is necessary if one wants to “explore the broad binding energy range as well as wide regions of the reciprocal space with unprecedented detail”.
8. We are pretty sure it was indeed the first superconducting oxide after the cuprates.
9. Here the referee cites one of our own works. The other paper reports symmetrized data, which we always avoid to perform and present instead only raw data.
10. We agree, and used very accurate wording when describing Fig.6. As mentioned earlier, much more work is needed to unambiguously resolve the gaps in this very complicated material.
11. We are not quite sure what exactly is meant here. Presumably a very insignificant for a general reader detail (the order of the traces should perhaps be inverted).
12. We have modified Fig.5 as requested.